

INTERNATIONAL STANDARD



**Semiconductor devices – Micro-electromechanical devices –
Part 29: Electromechanical relaxation test method for freestanding conductive
thin films under room temperature**

IECNORM.COM : Click to view the full PDF of IEC 62047-29:2017



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2017 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
Fax: +41 22 919 03 00
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

IEC Catalogue - webstore.iec.ch/catalogue

The stand-alone application for consulting the entire bibliographical information on IEC International Standards, Technical Specifications, Technical Reports and other documents. Available for PC, Mac OS, Android Tablets and iPad.

IEC publications search - www.iec.ch/searchpub

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and also once a month by email.

Electropedia - www.electropedia.org

The world's leading online dictionary of electronic and electrical terms containing 20 000 terms and definitions in English and French, with equivalent terms in 16 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary

65 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: csc@iec.ch.

IECNORM.COM : Click to view the full text of IEC 60347-22:2017

INTERNATIONAL STANDARD



**Semiconductor devices – Micro-electromechanical devices –
Part 29: Electromechanical relaxation test method for freestanding conductive
thin films under room temperature**

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 31.080.99

ISBN 978-2-8322-5046-4

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD.....	3
1 Scope	5
2 Normative references	5
3 Terms and symbols	5
3.1 Terms and definitions.....	5
3.2 Symbols and designations	6
4 Test piece	7
4.1 General.....	7
4.2 Shape of a test piece	7
4.3 Measurement of dimensions	7
5 Test principle and test apparatus.....	7
5.1 Test principle	7
5.2 Test environment	7
5.3 Test machine	7
5.4 Test procedure.....	8
5.5 Data analysis	8
6 Test report.....	9
Annex A (informative) Electromechanical relaxation test example of freestanding Au film	10
A.1 Testing overview	10
A.2 Testing results	11
Figure 1 – Freestanding test piece	6
Figure 2 – Experimental setup	8
Figure A.1 – Photograph of test equipment and a schematic for experimental setup	10
Figure A.2 – Electromechanical relaxation data of freestanding Au film with a thickness of 1 µm	12
Table 1 – Symbols and designations of a test piece	6

INTERNATIONAL ELECTROTECHNICAL COMMISSION

SEMICONDUCTOR DEVICES – MICRO-ELECTROMECHANICAL DEVICES –

Part 29: Electromechanical relaxation test method for freestanding conductive thin films under room temperature

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 62047-29 has been prepared by subcommittee 47F: Micro-electromechanical systems, of IEC technical committee 47: Semiconductor devices.

The text of this International Standard is based on the following documents:

FDIS	Report on voting
47F/295/FDIS	47F/298/RVD

Full information on the voting for the approval of this International Standard can be found in the report on voting indicated in the above table.

This document has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all parts in the IEC 62047 series, published under the general title *Semiconductor devices – Micro-electromechanical devices*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

A bilingual version of this publication may be issued at a later date.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

IECNORM.COM : Click to view the full PDF of IEC 62047-29:2017

SEMICONDUCTOR DEVICES – MICRO-ELECTROMECHANICAL DEVICES –

Part 29: Electromechanical relaxation test method for freestanding conductive thin films under room temperature

1 Scope

This part of IEC 62047 specifies a relaxation test method for measuring electromechanical properties of freestanding conductive thin films for micro-electromechanical systems (MEMS) under controlled strain and room temperature. Freestanding thin films of conductive materials are extensively utilized in MEMS, opto-electronics, and flexible/wearable electronics products. Freestanding thin films in the products experience external and internal stresses which could be relaxed even under room temperature during a period of operation, and this relaxation leads to time-dependent variation of electrical performances of the products. This test method is valid for isotropic, homogeneous, and linearly viscoelastic materials.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 62047-2:2006, *Semiconductor devices – Micro-electromechanical devices – Part 2: Tensile testing method of thin film materials*

IEC 62047-3:2006, *Semiconductor devices – Micro-electromechanical devices – Part 3: Thin film standard test piece for tensile testing*

IEC 62047-8:2011, *Semiconductor devices – Micro-electromechanical devices – Part 8: Strip bending test method for tensile property measurement of thin films*

IEC 62047-21:2014, *Semiconductor devices – Micro-electromechanical devices – Part 21: Test method for Poisson's ratio of thin film MEMS materials*

IEC 62047-22:2014, *Semiconductor devices – Micro-electromechanical devices – Part 22: Electromechanical tensile test method for conductive thin films on flexible substrates*

3 Terms and symbols

3.1 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1.1

gauge factor

G_F

ratio of the relative change in electrical resistance R to the change in mechanical strain ($\Delta\varepsilon$)

Note 1 to entry: Gauge factor is defined as $G_F = (\Delta R/R)/\Delta\varepsilon$, where ΔR is the change in resistance, R is the unstrained resistance, $\Delta\varepsilon$ is the change in the mechanical strain. R and ΔR are expressed in ohms and $\Delta\varepsilon$ in $\mu\text{m}/\text{m}$.

3.1.2

piezoresistive coefficient


π

ratio of the relative change in electrical resistivity ρ , to the change in applied mechanical stress

Note 1 to entry: Piezoresistive coefficient is defined as $\pi = (\Delta\rho/\rho)/\Delta\sigma$, where $\Delta\rho$ is the change in resistivity, ρ the unstressed resistivity, $\Delta\sigma$ the applied mechanical stress. Stress is expressed in Pascal [Pa].

3.2 Symbols and designations

The shape of a test piece and symbols are presented in Figure 1 and Table 1, respectively. The overall shape of the test piece is similar to a conventional thin film or sheet test piece for strip bending test (see IEC 62047-8:2011), and it has a freestanding structure and four electric contacts for electrical measurements.

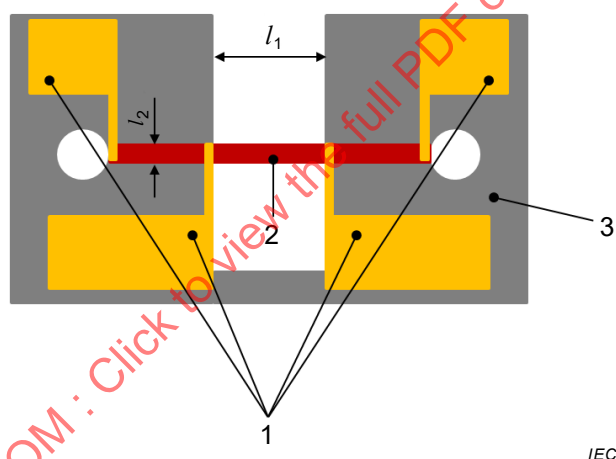

Key

- 1 electrical contacts for four wire measurement
- 2 test piece
- 3 substrate

Figure 1 – Freestanding test piece

Table 1 – Symbols and designations of a test piece

Symbol	Unit	Designation
l_1	μm	Gauge length for strain and resistance change measurements
l_2	μm	Width of a test piece
h	μm	Thickness of a test piece

4 Test piece

4.1 General

A test piece shall be prepared using the same fabrication process as the target film of an actual MEMS device. Shaping the test piece shall be performed to prevent formation of cracks, flaws, or delamination in the test piece.

4.2 Shape of a test piece

The shape of a test piece is shown in Figure 1. Because the change in electrical resistance is related to strain or stress, electrical resistance shall be measured in a region of uniform strain. The electrical resistance shall be measured using four wire method, and this requires four electric contacts on the test piece. To eliminate the effect of the fixed boundary near the grips, the gauge length (l_1) shall be at least 20 times larger than the width (l_2). The width shall be more than 10 times the thickness (h).

4.3 Measurement of dimensions

Gauge length (l_1), width (l_2), and thickness (h) should be measured with an error of less than $\pm 5\%$. The thickness should be measured according to Annex C of IEC 62047-2:2006 and in Clause 6 of IEC 62047-3:2006.

5 Test principle and test apparatus

5.1 Test principle

The test is performed by applying a prescribed tensile strain to a test piece and by measuring the change in electrical resistance under constant strain for a testing period. Both the electrical resistance and the mechanical stress relax as time, and the ratio of these two quantities characterizes the piezoresistive behaviour of a tested material. To this end, the tensile strain induced by the tensile load shall be uniform in a pre-defined gauge section and shall be in the elastic region of the test piece. The actuator of the test machine shall be controlled with a feedback loop to keep the strain constant since the strain in thin films usually creeps even under room temperature, and this leads to deviation of strain in the test piece. To measure the change in electrical resistance under constant strain, the gauge section for measuring mechanical strain shall be coincident with or scalable to that for measuring electrical resistance.

5.2 Test environment

Because electrical properties are temperature sensitive, fluctuations in temperature during the test shall be controlled to be less than $\pm 2\text{ }^\circ\text{C}$. Flexible substrates made of certain polymeric materials can be sensitive to humidity; thus, the change in relative humidity (RH) in the testing laboratory shall be controlled to be less than $\pm 5\%$ RH for such materials.


5.3 Test machine

The test machine is similar to a conventional tensile test machine except that it is capable of feedback control of applied strain and measurement of electrical resistance during the test. The electrical resistance shall be measured with four wire method (Kelvin method) to exclude the effects of parasitic resistances from contact and lead wires. The electrical current for the four wire method measurement shall be as small as possible to prevent the test piece from heating, but to provide sufficient measurement resolution and accuracy. A schematic of the test machine is shown in Figure 2. A noncontact strain measurement method like digital image correlation shall be used to measure the strain not to disturb a test piece. The measured strain signal shall be connected to the test machine for the feedback control.

5.4 Test procedure

The test procedure is as follows:

- Fix a test piece to the relaxation test machine. The longitudinal direction of the test piece shall be aligned with the actuating direction of the test apparatus, and the deviation angle shall be less than 1° as described in 4.4 of IEC 62047-8:2011.
- Verify the electrical measurement unit as well as the loadcell and strain measurement unit. The three signals of force, strain and resistance shall be recorded simultaneously (see 5.3 of IEC 62047-22:2014). The loadcell shall be accurate to the nominal value within 0,25 %.
- Apply a tensile strain up to a predetermined level in a short period. The straining period is typically less than 1 s for metallic conductors, but shall be shorter when the target material is highly time-dependent. The predetermined strain level shall be chosen in an elastic range of the test piece. For example, when the maximum elastic strain of the test piece is E_{el} [$\mu\text{m}/\text{m}$], the strain levels can be chosen as $E_{el}/4$, $2E_{el}/4$, $3E_{el}/4$, and E_{el} .
- Hold the applied strain for a testing period, and measure the force and resistance signals simultaneously. During this holding period, the strain shall be controlled to be constant, and this shall be verified using a strain measurement technique such as digital image correlation. The strain resolution shall be less than $E_{el}/500$, and the measured strain shall be accurate to the nominal value of the maximum strain within 0,2 %.
- Unload the test piece after the testing period. After testing, carefully remove the test piece from the test apparatus to prevent any additional damage on the test piece. If possible, preserve the test piece for investigation using electron and optical microscopes.

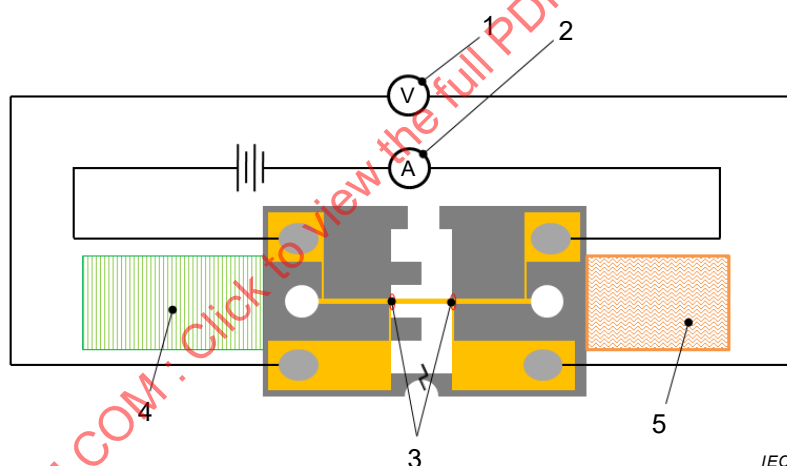

Key

- | | |
|---|--|
| 1 | voltmeter |
| 2 | current source |
| 3 | markers for strain measurement |
| 4 | actuator for applying a load to the test piece |
| 5 | loadcell |

Figure 2 – Experimental setup

5.5 Data analysis

The piezoresistive coefficient (π) is obtained from the ratio between two relaxation data of electrical resistance and mechanical stress. See Annex A for the test example of freestanding Au thin film. The relaxation modulus is obtained by dividing the relaxation data of mechanical stress with the applied strain. The gauge factor is directly measured by using IEC 62047-22:2014, and is obtained from $(1+2\nu+\pi E)$, where ν is Poisson's ratio (should be measured by using IEC 62047-21:2014), and E is Young's modulus (should be measured by using IEC 62047-2:2006).

6 Test report

The test report shall contain the following information:

- a) reference to this International Standard;
- b) test piece identification number;
- c) test piece preparation procedures;
- d) test piece dimensions and their measurement method;
- e) description of the testing apparatus;
- f) measured properties and results: piezoresistive coefficient, stress relaxation curve (stress versus time), controlled strain curve (strain versus time), electrical relaxation curve (resistance change versus time).


IECNORM.COM : Click to view the full PDF of IEC 62047-29:2017

Annex A (informative)


Electromechanical relaxation test example of freestanding Au film

A.1 Testing overview

The testing equipment shown in Figure A.1 is utilized to measure electromechanical relaxation of freestanding Au thin film. A piezoelectric actuator applies tensile strain to the freestanding Au film and the corresponding force and electrical resistance are measured simultaneously by a load cell and an electrical measurement system. The applied strain is measured by correlation with the images obtained by an optical microscope and an imaging camera. The piezoelectric actuator is controlled to maintain the applied strain constant.

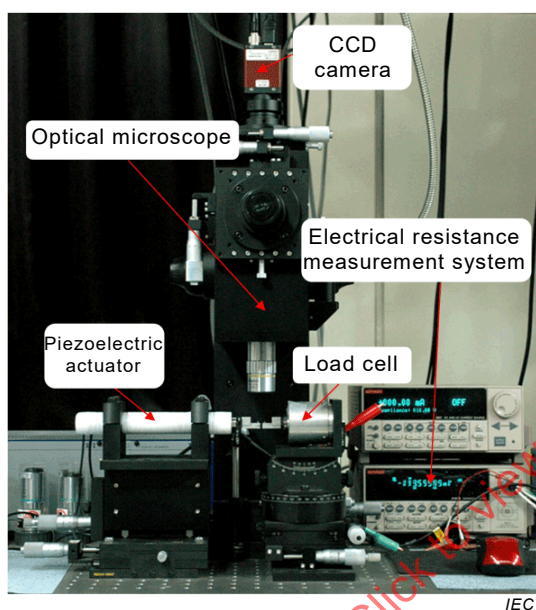

a) Photograph of test equipment

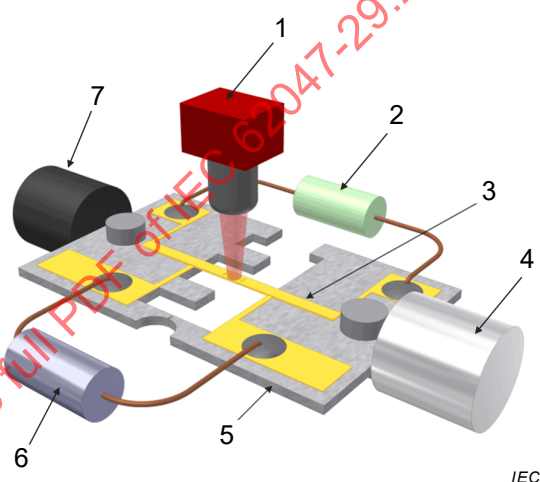

b) Schematic for experimental setup

Key

- 1 optical system for strain measurement
- 2 current source
- 3 gold specimen
- 4 load cell
- 5 substrate
- 6 voltmeter
- 7 piezoelectric actuator

Figure A.1 – Photograph of test equipment and a schematic for experimental setup