

# TECHNICAL REPORT



**Electrical insulating materials – Thermal endurance properties –  
Part 7-2: Accelerated determination of relative thermal endurance using  
analytical test methods (RTEA) – Results of the round robin tests to validate  
procedures of IEC TS 60216-7-1 by non-isothermal kinetic analysis of  
thermogravimetric data**



## THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2024 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Secretariat  
3, rue de Varembe  
CH-1211 Geneva 20  
Switzerland

Tel.: +41 22 919 02 11  
[info@iec.ch](mailto:info@iec.ch)  
[www.iec.ch](http://www.iec.ch)

### About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

### About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

#### IEC publications search - [webstore.iec.ch/advsearchform](http://webstore.iec.ch/advsearchform)

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

#### IEC Just Published - [webstore.iec.ch/justpublished](http://webstore.iec.ch/justpublished)

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

#### IEC Customer Service Centre - [webstore.iec.ch/csc](http://webstore.iec.ch/csc)

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: [sales@iec.ch](mailto:sales@iec.ch).

#### IEC Products & Services Portal - [products.iec.ch](http://products.iec.ch)

Discover our powerful search engine and read freely all the publications previews, graphical symbols and the glossary. With a subscription you will always have access to up to date content tailored to your needs.

#### Electropedia - [www.electropedia.org](http://www.electropedia.org)

The world's leading online dictionary on electrotechnology, containing more than 22 500 terminological entries in English and French, with equivalent terms in 25 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IECNORM.COM : Click to view the full PDF IEC 60216-7-2:2024

# TECHNICAL REPORT



**Electrical insulating materials – Thermal endurance properties –  
Part 7-2: Accelerated determination of relative thermal endurance using  
analytical test methods (RTEA) – Results of the round robin tests to validate  
procedures of IEC TS 60216-7-1 by non-isothermal kinetic analysis of  
thermogravimetric data**

INTERNATIONAL  
ELECTROTECHNICAL  
COMMISSION

ICS 19.020; 29.020; 29.035.01

ISBN 978-2-8322-9692-9

**Warning! Make sure that you obtained this publication from an authorized distributor.**

## CONTENTS

|                                                                                                       |    |
|-------------------------------------------------------------------------------------------------------|----|
| FOREWORD.....                                                                                         | 4  |
| INTRODUCTION.....                                                                                     | 6  |
| 1 Scope.....                                                                                          | 7  |
| 2 Normative references .....                                                                          | 7  |
| 3 Terms and definitions .....                                                                         | 7  |
| 4 Test specimens .....                                                                                | 8  |
| 5 Test apparatus .....                                                                                | 9  |
| 5.1 Thermogravimetric analyser (TGA) .....                                                            | 9  |
| 5.2 Purge gas supplied into the TGA furnace .....                                                     | 9  |
| 6 Test procedures .....                                                                               | 10 |
| 6.1 General.....                                                                                      | 10 |
| 6.2 Preconditioning of test samples .....                                                             | 10 |
| 6.3 TGA tests with multiple heating rates .....                                                       | 10 |
| 6.4 Calculation of the activation energy ( $E_a$ ) .....                                              | 10 |
| 6.5 Determination of thermal endurance using TGA .....                                                | 11 |
| 6.5.1 General .....                                                                                   | 11 |
| 6.5.2 Determination of $RTE_A$ by given degree of conversion from reference material (Method A) ..... | 11 |
| 6.5.3 Determination of $TI_A$ by fixed degree of conversion at 0,05 (Method B) .....                  | 12 |
| 7 Round robin test results.....                                                                       | 12 |
| 7.1 TGA test results.....                                                                             | 12 |
| 7.2 Degree of conversion correlated to the activation energy from conventional heat ageing data ..... | 12 |
| 7.3 $HIC_A$ determined by Method A and Method B .....                                                 | 13 |
| 7.4 $RTE_A$ determined by Method A and $TI_A$ by Method B.....                                        | 14 |
| 7.5 Difference between $RTE_A$ and $TI$ determined by the conventional heat ageing tests .....        | 16 |
| 8 Observations from the round robin test results.....                                                 | 18 |
| 8.1 General.....                                                                                      | 18 |
| 8.2 Sample weight variation .....                                                                     | 18 |
| 8.3 Humidity and hydrolysis of the sample .....                                                       | 20 |
| 8.4 Considerations on repeatability of TGA curves.....                                                | 20 |
| 8.5 Baseline drift and responsiveness to heating rates of TGA.....                                    | 21 |
| 9 Conclusion .....                                                                                    | 25 |
| Annex A (informative) Additional round robin studies with polybutylene terephthalate .....            | 26 |
| A.1 Objectives.....                                                                                   | 26 |
| A.2 Test specimens.....                                                                               | 26 |
| A.3 Test apparatus.....                                                                               | 26 |
| A.4 Test procedures.....                                                                              | 27 |
| A.5 Test results .....                                                                                | 27 |
| A.6 Observations .....                                                                                | 32 |
| Bibliography.....                                                                                     | 35 |

Figure 1 – Fitting curve of plots between degree of conversion and activation energy determined by ISO 11358-2 [3] (example)..... 11

|                                                                                                                                    |    |
|------------------------------------------------------------------------------------------------------------------------------------|----|
| Figure 2 – Correlation between the initial sample mass of sample A and the difference of $RTE_A$ ( $TI_A$ ) from $TI$ .....        | 19 |
| Figure 3 – Correlation between the initial sample mass of sample B and the difference of $RTE_A$ ( $TI_A$ ) from $TI$ .....        | 19 |
| Figure 4 – Overlay charts of TGA curves in multiple heating rates in multiple laboratories (enlarged).....                         | 22 |
| Figure 5 – Logarithm plots for activation energy calculation .....                                                                 | 23 |
| Figure 6 – Fitting curves of degree of conversion versus activation energy by TGA .....                                            | 24 |
| Figure A.1 – Effect of sample amount on $E_a$ (data provided by laboratory E) .....                                                | 33 |
| Figure A.2 – Summary of factors affecting the TGA kinetic study for determination of $RTE_A$ and $TI_A$ .....                      | 34 |
| Table 1 – Heat ageing properties of the test specimens by the conventional procedure described in IEC 60216-5 [4].....             | 9  |
| Table 2 – Degree of conversion identical to the activation energy of the conventional heat ageing.....                             | 13 |
| Table 3 – $HIC_A$ determined by Method A and Method B for dielectric strength .....                                                | 13 |
| Table 4 – $HIC_A$ determined by Method A and Method B for tensile strength .....                                                   | 14 |
| Table 5 – $HIC_A$ determined by Method A and Method B for impact strength .....                                                    | 14 |
| Table 6 – $RTE_A$ determined by Method A and $TI_A$ by Method B for dielectric strength .....                                      | 15 |
| Table 7 – $RTE_A$ determined by Method A and $TI_A$ by Method B for tensile strength .....                                         | 15 |
| Table 8 – $RTE_A$ determined by Method A and $TI_A$ by Method B for impact strength .....                                          | 16 |
| Table 9 – Difference between $RTE_A$ or $TI_A$ , and $TI$ for dielectric strength .....                                            | 16 |
| Table 10 – Difference between $RTE_A$ or $TI_A$ , and $TI$ for tensile strength .....                                              | 17 |
| Table 11 – Difference between $RTE_A$ or $TI_A$ , and $TI$ for impact strength .....                                               | 17 |
| Table 12 – Comparison of degree of conversion with original or rerun data at 8 K/min .....                                         | 21 |
| Table A.1 – Heat ageing properties of the PBT test specimens by the conventional procedure in accordance with IEC 60216-5 [4]..... | 26 |
| Table A.2 – Degrees of conversion at the activation energy identical to that from conventional heat ageing .....                   | 27 |
| Table A.3 – $HIC_A$ determined by Method A and Method B for dielectric strength .....                                              | 28 |
| Table A.4 – $HIC_A$ determined by Method A and Method B for tensile strength.....                                                  | 28 |
| Table A.5 – $HIC_A$ determined by Method A and Method B for impact strength.....                                                   | 29 |
| Table A.6 – $RTE_A$ determined by Method A and $TI_A$ by Method B for dielectric strength .....                                    | 29 |
| Table A.7 – $RTE_A$ determined by Method A and $TI_A$ by Method B for tensile strength.....                                        | 30 |
| Table A.8 – $RTE_A$ determined by Method A and $TI_A$ by Method B for impact strength.....                                         | 30 |
| Table A.9 – Difference between $RTE_A$ or $TI_A$ , and $TI$ for dielectric strength .....                                          | 31 |
| Table A.10 – Difference between $RTE_A$ or $TI_A$ , and $TI$ for tensile strength.....                                             | 31 |
| Table A.11 – Difference between $RTE_A$ or $TI_A$ , and $TI$ for impact strength.....                                              | 32 |

## INTERNATIONAL ELECTROTECHNICAL COMMISSION

**ELECTRICAL INSULATING MATERIALS –  
THERMAL ENDURANCE PROPERTIES –****Part 7-2: Accelerated determination of relative thermal endurance using  
analytical test methods (RTEA) – Results of the round robin tests to  
validate procedures of IEC TS 60216-7-1 by non-isothermal kinetic  
analysis of thermogravimetric data**

## FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) IEC draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). IEC takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, IEC had not received notice of (a) patent(s), which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at <https://patents.iec.ch>. IEC shall not be held responsible for identifying any or all such patent rights.

IEC TR 60216-7-2 has been prepared by IEC technical committee 112: Evaluation and qualification of electrical insulating materials and systems. It is a Technical Report.

This second edition cancels and replaces the first edition published in 2016. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) Annex A (informative) has been added to provide a round robin test with a different polymer type – polybutylene terephthalate (PBY) – as an additional use case of the method in accordance with IEC TS 60216-7-1;
- b) Tables 3 to 11 have been corrected by adding units, and texts have been refined for more technical clarifications of the procedures and observations.

The text of this Technical Report is based on the following documents:

| Draft       | Report on voting |
|-------------|------------------|
| 112/651/DTR | 112/658/RVDTR    |

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this Technical Report is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at [www.iec.ch/members\\_experts/refdocs](http://www.iec.ch/members_experts/refdocs). The main document types developed by IEC are described in greater detail at [www.iec.ch/publications](http://www.iec.ch/publications).

A list of all parts in the IEC 60216 series, published under the general title *Electrical insulating materials – Thermal endurance properties*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under [webstore.iec.ch](http://webstore.iec.ch) in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn, or
- revised.

**IMPORTANT – The "colour inside" logo on the cover page of this document indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.**

## INTRODUCTION

IEC technical committee 112, (IEC TC 112) has been working on the development of IEC TS 60216-7-1 [1]<sup>1</sup> that considers the use of activation energy determined through thermal analytical tools plus abbreviated conventional heat ageing to determine a thermal index on a polymeric compound. At the same time, the Underwriters Laboratories Long-Term Thermal Aging Forum (UL LTТА Forum) has been discussing alternative methods that can speed up the determination of a thermal index. Members of the IEC TC 112 and of the UL LTТА Forum have made joint efforts to determine whether the Technical Specification developed by IEC TC 112 can be used to offer an alternative method of evaluating polymeric compounds for a thermal index.

Members of IEC TC 112 and the UL LTТА Forum decided to conduct a round robin test (RRT) using thermogravimetric analysis (TGA) according to ISO 11358-2 [3] on a known compound, with a known activation energy determined through conventional ageing with a view to validate the acceptability of IEC TS 60216-7-1, and to determine whether a similar thermal index can be calculated. The round robin testing was conducted with conventional TGA by multiple heating rates. However, running isothermal tests can be a follow-up of this RRT.

---

<sup>1</sup> Numbers in square brackets refer to the Bibliography.

## ELECTRICAL INSULATING MATERIALS – THERMAL ENDURANCE PROPERTIES –

### Part 7-2: Accelerated determination of relative thermal endurance using analytical test methods (RTEA) – Results of the round robin tests to validate procedures of IEC TS 60216-7-1 by non-isothermal kinetic analysis of thermogravimetric data

#### 1 Scope

This part of IEC 60216 is intended to validate the procedures of IEC TS 60216-7-1 in providing a similar temperature index to conventional methods used in other parts of the IEC 60216 series.

The round robin test results do not provide statistical analysis for precision. The round robin test focuses on preliminary studies to understand the evaluation and calculation procedures, influence on apparatus, and data variance among laboratories before determination of precision.

#### 2 Normative references

There are no normative references in this document.

#### 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

##### 3.1

##### **activation energy**

Arrhenius activation energy

$E_a$

empirical parameter characterizing the exponential temperature dependence of the reaction rate constant

##### 3.2

##### **end-point**

limit for a diagnostic property value based on which the thermal endurance is evaluated

##### 3.3

##### **time to end-point**

##### **failure time**

time to reach the end-point or conventional failure

### 3.4 relative temperature endurance index RTE

numerical value of the temperature in degrees Celsius at which the estimated time to end-point of the candidate material is the same as the estimated time to end-point of the reference material at a temperature equal to its assessed temperature index

Note 1 to entry:  $RTE_A$  is the relative temperature endurance index calculated through the analytical procedure.

### 3.5 temperature endurance index TI

numerical value of the temperature in degrees Celsius derived from the thermal endurance relationship at a time of 20 000 h (or other specified time)

Note 1 to entry:  $TI_A$  is the temperature index calculated through the analytical procedure.

[SOURCE: IEC 60050-212:2010, 212-12-11 [2], modified – "characterizing the thermal capability of an insulating material or an insulation system" has been replaced with "derived from the thermal endurance relationship at a time of 20 000 h (or other specified time)" and the two notes to entry have been replaced by a new note to entry.]

### 3.6 halving interval HIC

numerical value of the temperature interval in kelvin which expresses the halving of the time to end-point taken at the temperature equal to TI

Note 1 to entry:  $HIC_A$  is the halving interval calculated through the analytical procedure.

### 3.7 degree of conversion $\alpha$

quantity of products present at a particular time and temperature during a reaction compared with the final quantity of the products

[SOURCE: ISO 11358-2:2021, 3.3 [3], modified – The symbol "C" has been replaced with " $\alpha$ " and the notes to entry have been deleted.]

## 4 Test specimens

For the round robin test, one generic type of polymer, liquid crystal polyester (LCP), was pre-selected. Although it is known that materials can undergo more than one transition, the round robin test verified the assumption that one single thermal degradation reaction is predominant and directly correlated to the end-point of dielectric strength as a diagnostic property.

NOTE Since different materials can undergo more than one transition, the validity of results obtained from the evaluation of thermal endurance properties using TGA are assessed for the different materials.

LCP originally has very little entwining of molecules exhibiting crystalline properties as a liquid. Hence, there is less thermal transformation between solid and liquid, or between oven ageing conditions of conventional thermal endurance test and TGA conditions at higher temperature ranges. In addition, LCP molecular chains align themselves when moulded, and this generates a self-reinforcing effect, thereby resulting in high mechanical and electrical stress resistance.

In this round robin, two LCP materials (LCP sample A, LCP sample B) were chosen as test samples which already have the conventional heat oven ageing data of dielectric strength, tensile strength, and impact strength to validate the acceptability of whether or not  $RTE_A$  can be similar to RTE. Both sample A and sample B consist of 30 % glass fibres reinforced materials. Configurations of monomers are the only differences between the samples which influence the difference in thermal resistance, as shown in Table 1.

The samples were homogenized by freeze-pulverization from test plaques. 100 mg each of freeze-pulverized powders from the same batch were prepared and provided to eleven testing laboratories for evaluation, after pre-drying at 140 °C for 4 h.

**Table 1 – Heat ageing properties of the test specimens by the conventional procedure described in IEC 60216-5 [4]**

| Temperature<br>in ovens | Time to end-point at<br>50 % retention of initial<br>dielectric strength |                 | Time to end-point at<br>50 % retention of initial<br>tensile strength |                 | Time to end-point at<br>50 % retention of initial<br>impact strength |                 |
|-------------------------|--------------------------------------------------------------------------|-----------------|-----------------------------------------------------------------------|-----------------|----------------------------------------------------------------------|-----------------|
|                         | h                                                                        |                 | h                                                                     |                 | h                                                                    |                 |
| °C                      | LCP<br>Sample A                                                          | LCP<br>Sample B | LCP<br>Sample A                                                       | LCP<br>Sample B | LCP<br>Sample A                                                      | LCP<br>Sample B |
| 290                     |                                                                          | 1 141           |                                                                       | 1 215           |                                                                      | 1 860           |
| 285                     | 2 896                                                                    |                 | 1 789                                                                 |                 | 2 870                                                                |                 |
| 280                     |                                                                          | 1 917           |                                                                       | 3 229           |                                                                      | 2 655           |
| 275                     | 5 591                                                                    |                 | 3 083                                                                 |                 | 4 164                                                                |                 |
| 270                     |                                                                          | 4 300           |                                                                       | 4 597           |                                                                      | 3 920           |
| 265                     | 8 255                                                                    |                 | 6 706                                                                 |                 | 8 412                                                                |                 |
| 260                     |                                                                          | 5 848           |                                                                       | 7 625           |                                                                      | 6 640           |
| 250                     |                                                                          |                 |                                                                       |                 |                                                                      | 9 600           |
| TI (°C)                 | 250,0                                                                    | 241,5           | 249,1                                                                 | 246,2           | 249,1                                                                | 234,7           |
| $E_a$ (kJ/mol)          | 130,6                                                                    | 142,3           | 165,2                                                                 | 145,9           | 134,5                                                                | 102,9           |

## 5 Test apparatus

### 5.1 Thermogravimetric analyser (TGA)

A thermogravimetric analyser (TGA) in accordance with ISO 11358-1 [5] was used for the determination of  $RTE_A$  concerning the test samples. In fact, a number of commercial instruments suitable for the measurement are available and various models of TGAs were used for evaluation of the test samples by the participating laboratories. Before the RRT, weight and temperature calibrations were implemented based on ISO 11358-1 and TGA apparatus manufacturer's guidance.

### 5.2 Purge gas supplied into the TGA furnace

For purge gas into the TGA furnace, air was chosen to assume oxidative thermal degradation, as well as degradation of electrical and mechanical strengths with test specimens in oven ageing. Most of the laboratory participants selected dry air (water content less than 1 ppm<sup>2</sup>), but air supplied from the facility (compressed air with or without an air dryer) was used in a few laboratories.

<sup>2</sup> ppm = parts per million.

## 6 Test procedures

### 6.1 General

Thermal analysis with TGA of the test samples was evaluated with reference to ISO 11358-2 [3] and IEC TS 60216-7-1 in principle. A few modifications of test conditions and more detailed procedures were added as follows.

### 6.2 Preconditioning of test samples

5 mg  $\pm$  0,5 mg of the test sample were initially measured in each laboratory and mounted on the empty pan in the furnace opened. Then the furnace was closed and pre-conditioned in equilibrium at 100 °C for 1 h before heating tests were started. The weight value just before the heating test (time at 0 s in the heating run, or 60 min at the end of the equilibrium) was used for calculation on the degree of conversion.

NOTE ISO 11358-2 [3] requires using test samples of identical mass  $\pm$ 1 % of the initial weight in multiple heating conditions which is much narrower than the above. Influence on the initial mass deviation is taken into consideration in 7.2.

### 6.3 TGA tests with multiple heating rates


Multiple heating rates testing at 1 K/min, 2 K/min, 4 K/min, 6 K/min and 8 K/min were selected for evaluation which resulted in the lowest and highest heating rates differing by a factor of 8, in accordance with ISO 11358-2 [3]. Evaluation temperature range was set between 100 °C and 700 °C. Each heating rate test was run one time each for sample A and sample B, but 8 K/min was evaluated twice as an approximate check and to consider repeatability.

### 6.4 Calculation of the activation energy ( $E_a$ )

After TGA data with multiple heating rates were obtained, the activation energies were calculated for given degrees of conversion in accordance with Equation (2) in ISO 11358-2:2021 [3]. Then, both values of degree of conversion and the activation energies were plotted between 1 % and 19 % with 2 % interval of degree of conversion and a cubic curve fitting approximately was performed as shown in Figure 1. Equation (2) in ISO 11358-2:2021 [3] was used for the selection of appropriate activation energy and degree of conversion to determine RTE<sub>A</sub>.

For example, if the activation energy of a reference material was already determined as 150 kJ/mol by the conventional heat ageing (e.g. dielectric strength), the corresponding degree of conversion of the reference material can be read and obtained with the equation of the fitting curve graph (see Figure 1). Then the corresponding degree of conversion for this reference material can be used for reading the activation energy of a candidate material from another graph which was also evaluated with ISO 11358-2 [3] and had a similar degree of conversion versus the activation energy fitting curve for the candidate material.

All TGA raw data were submitted by eleven participating laboratories and analysis with ISO 11358-2 [3] was carried out by one of the laboratories with the analytical tool, to avoid any discrepancy among various software calculations.

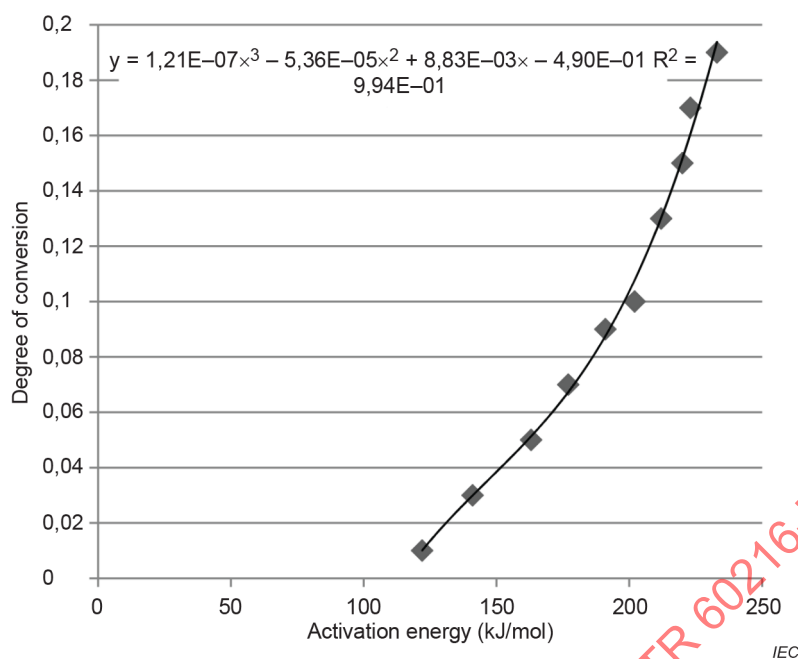

**Figure 1 – Fitting curve of plots between degree of conversion and activation energy determined by ISO 11358-2 [3] (example)**

## 6.5 Determination of thermal endurance using TGA

### 6.5.1 General

The activation energy given by the above procedure can be used for the determination of  $RTE_A$  by calculating with time to end-point at the highest temperature, which was determined by the conventional heat ageing test under IEC 60216-5 [4], and procedures in accordance with IEC TS 60216-7-1.

In accordance with ISO 11358-2 [3], various activation energies can be obtained per certain degrees of conversion calculated with multiple heating rate data of TGA. Therefore, degrees of conversion were chosen appropriately to be correlated to thermal degradation derived by properties and the conventional heat ageing data which are described in 6.5.2 (Method A). On the other hand, the fixed degree of conversion at 0,05 and activation energy are sometimes used experimentally for prediction of end-point of properties [6], [7], which is described in 6.5.3 (Method B).

### 6.5.2 Determination of $RTE_A$ by given degree of conversion from reference material (Method A)

After the cubic approximation between the degree of conversion and the activation energy is determined (see 6.4), the degree of conversion for the reference material is given from the equation where the activation energy is the same as that from the Arrhenius equation of conventional heat ageing data. The activation energy of the candidate material is then determined from the cubic approximation of the candidate material where the degree of conversion for the candidate material is assumed to be the same as the given degree of conversion for the reference material. In Method A,  $RTE_A$  can be obtained.

**NOTE** The assumption that the degree of conversion for the candidate material is the same as the given degree of conversion for the reference material, is validated since the candidate material can be of the same type of the reference material.

### 6.5.3 Determination of $TI_A$ by fixed degree of conversion at 0,05 (Method B)

In Method B, the fixed degree of conversion at 0,05 can be selected to calculate the activation energy of the candidate material, with regard to practical experiences [7], [8]. In Method B it is unnecessary to use reference material data to determine the activation energy of the candidate material in accordance with ISO 11358-2 [3] and the thermal indices of materials can be determined as  $TI_A$  by the activation energy when the degree of conversion is 0,05.

In this round robin test,  $TI_A$  and  $RTE_A$  at 20 000 h of LCP sample A and sample B were determined by using Method A and Method B respectively.

## 7 Round robin test results

### 7.1 TGA test results

All the raw TGA test data were obtained from eleven laboratories (a, b, c, d, e, f, g, h, i, j and k). Figure 4 shows typical examples of overlay TGA curves at multiple heating rates magnified to show the degrees of conversion between 0 and 0,02. Figure 5 provides typical examples of logarithm graphs between reciprocal temperatures and heating rates for certain degrees of conversions. Figure 6 shows cubic approximation between degree of conversions and activation energies to read appropriate activation energy for the determination of  $RTE_A$  or  $TI_A$ .

### 7.2 Degree of conversion correlated to the activation energy from conventional heat ageing data

Degrees of conversion at the activation energy identical to that from conventional heat ageing were determined with reference to ISO 11358-2 [3] and IEC TS 60216-7-1 which are shown in Table 2.

It was observed that both sample A and sample B had very low initial thermal degradation under TGA (around 3 % or 4 % mass loss) which were correlated to thermal degradation of the dielectric strength under a heating oven, in terms of the identical activation energies. For reproducibility in laboratories, however, relatively high deviations are observed (around 30 % of the average degree of conversion) for both sample A and sample B. In addition, three laboratories (b, d, and j) were not able to obtain a degree of conversion identical to that of the activation energy of conventional heat ageing, because all of the activation energies were found to be higher than the ones determined by heat ageing in the considered range.

**Table 2 – Degree of conversion identical to the activation energy of the conventional heat ageing**

| Laboratory                                                                                                                             | Degree of conversion identical to activation energy of the conventional heating, sample A | Degree of conversion identical to activation energy of the conventional heating, sample B |
|----------------------------------------------------------------------------------------------------------------------------------------|-------------------------------------------------------------------------------------------|-------------------------------------------------------------------------------------------|
| a                                                                                                                                      | 0,032 7                                                                                   | 0,019 9                                                                                   |
| b                                                                                                                                      | N/A                                                                                       | 0,039 3                                                                                   |
| c                                                                                                                                      | 0,040 8                                                                                   | 0,043 7                                                                                   |
| d                                                                                                                                      | N/A                                                                                       | 0,037 8                                                                                   |
| e                                                                                                                                      | 0,037 7                                                                                   | 0,024 4                                                                                   |
| f                                                                                                                                      | 0,021 9                                                                                   | 0,040 6                                                                                   |
| g                                                                                                                                      | 0,036 7                                                                                   | 0,024 6                                                                                   |
| h                                                                                                                                      | 0,034 2                                                                                   | 0,037 1                                                                                   |
| i                                                                                                                                      | 0,051 5                                                                                   | 0,032 1                                                                                   |
| j                                                                                                                                      | N/A                                                                                       | 0,015 0                                                                                   |
| k                                                                                                                                      | 0,060 0                                                                                   | 0,031 1                                                                                   |
| Average                                                                                                                                | 0,032 7                                                                                   | 0,031 4                                                                                   |
| Standard deviation                                                                                                                     | 0,013 6                                                                                   | 0,009 3                                                                                   |
| NOTE N/A means that in the cubic approximation of activation versus the degree of conversion, the equation did not provide a solution. |                                                                                           |                                                                                           |

### 7.3 HIC<sub>A</sub> determined by Method A and Method B

HIC<sub>A</sub> determined by Method A and Method B according to IEC TS 60216-7-1 is shown in Table 3, Table 4 and Table 5 for dielectric strength, tensile strength and impact strength, respectively.

**Table 3 – HIC<sub>A</sub> determined by Method A and Method B for dielectric strength**

| Laboratory                                                                                                                             | Method A                     |                              | Method B                     |                              |
|----------------------------------------------------------------------------------------------------------------------------------------|------------------------------|------------------------------|------------------------------|------------------------------|
|                                                                                                                                        | HIC <sub>A</sub> of sample A | HIC <sub>A</sub> of sample B | HIC <sub>A</sub> of sample A | HIC <sub>A</sub> of sample B |
|                                                                                                                                        | K                            | K                            | K                            | K                            |
| a                                                                                                                                      | 10,4                         | 9,5                          | 9,8                          | 7,9                          |
| b                                                                                                                                      | 8,8                          | N/A                          | 8,6                          | 7,6                          |
| c                                                                                                                                      | 12,1                         | 11,7                         | 11,6                         | 10,6                         |
| d                                                                                                                                      | 8,6                          | N/A                          | 7,9                          | 9,7                          |
| e                                                                                                                                      | 14,4                         | 9,0                          | 12,6                         | 8,1                          |
| f                                                                                                                                      | 10,6                         | 16,7                         | 10,0                         | 9,1                          |
| g                                                                                                                                      | 13,5                         | 10,3                         | 10,0                         | 9,0                          |
| h                                                                                                                                      | 12,2                         | 9,2                          | 11,5                         | 7,0                          |
| i                                                                                                                                      | 20,7                         | 8,6                          | 13,0                         | 8,8                          |
| j                                                                                                                                      | 11,0                         | N/A                          | 9,1                          | 7,7                          |
| k                                                                                                                                      | 11,7                         | 12,7                         | 10,4                         | 9,6                          |
| Average                                                                                                                                | 12,2                         | 11,0                         | 10,4                         | 8,6                          |
| Standard deviation                                                                                                                     | 3,2                          | 2,5                          | 1,5                          | 1,0                          |
| NOTE N/A means that in the cubic approximation of activation versus the degree of conversion, the equation did not provide a solution. |                              |                              |                              |                              |

**Table 4 –  $HIC_A$  determined by Method A and Method B for tensile strength**

| Laboratory         | Method A            |                     | Method B            |                     |
|--------------------|---------------------|---------------------|---------------------|---------------------|
|                    | $HIC_A$ of sample A | $HIC_A$ of sample B | $HIC_A$ of sample A | $HIC_A$ of sample B |
|                    | K                   | K                   | K                   | K                   |
| a                  | 10,0                | 9,1                 | 9,6                 | 7,9                 |
| b                  | 8,7                 | 7,5                 | 8,3                 | 7,6                 |
| c                  | 11,5                | 9,3                 | 11,3                | 10,7                |
| d                  | 8,5                 | 16,4                | 7,9                 | 9,7                 |
| e                  | 13,9                | 7,8                 | 12,2                | 8,4                 |
| f                  | 10,1                | 8,8                 | 9,8                 | 9,2                 |
| g                  | 12,6                | 9,1                 | 9,7                 | 7,9                 |
| h                  | 11,9                | 6,3                 | 11,2                | 7,1                 |
| i                  | 18,8                | 7,9                 | 12,6                | 8,8                 |
| j                  | 10,1                | 11,0                | 8,8                 | 7,8                 |
| k                  | 11,1                | 9,3                 | 10,1                | 9,6                 |
| Average            | 11,6                | 9,3                 | 10,1                | 8,6                 |
| Standard deviation | 2,9                 | 2,6                 | 1,5                 | 1,1                 |

**Table 5 –  $HIC_A$  determined by Method A and Method B for impact strength**

| Laboratory         | Method A            |                     | Method B            |                     |
|--------------------|---------------------|---------------------|---------------------|---------------------|
|                    | $HIC_A$ of sample A | $HIC_A$ of sample B | $HIC_A$ of sample A | $HIC_A$ of sample B |
|                    | K                   | K                   | K                   | K                   |
| a                  | 9,3                 | 8,4                 | 9,8                 | 8,1                 |
| b                  | 8,3                 | 6,6                 | 8,5                 | 7,7                 |
| c                  | 20,5                | 11,6                | 11,6                | 11,0                |
| d                  | 10,0                | N/A                 | 8,1                 | 9,9                 |
| e                  | 12,7                | 9,2                 | 12,6                | 8,6                 |
| f                  | 11,6                | 16,6                | 10,0                | 9,4                 |
| g                  | 14,8                | 10,3                | 10,0                | 9,2                 |
| h                  | N/A                 | 8,0                 | 11,5                | 7,2                 |
| i                  | 32,4                | 8,9                 | 13,0                | 9,0                 |
| j                  | 10,5                | N/A                 | 9,0                 | 7,9                 |
| k                  | 12,2                | 16,4                | 10,4                | 9,8                 |
| Average            | 14,2                | 10,7                | 10,4                | 8,9                 |
| Standard deviation | 7,3                 | 3,6                 | 1,6                 | 1,1                 |

#### 7.4 $RTE_A$ determined by Method A and $TI_A$ by Method B

$RTE_A$  determined by Method A and  $TI_A$  by Method B are shown in Table 6, Table 7, and Table 8 for dielectric strength, tensile strength, and impact strength, respectively.

**Table 6 –  $RTE_A$  determined by Method A and  $Tl_A$  by Method B for dielectric strength**

| Laboratory         | Method A                  |                           | Method B                 |                          |
|--------------------|---------------------------|---------------------------|--------------------------|--------------------------|
|                    | $RTE_A$ of sample A<br>°C | $RTE_A$ of sample B<br>°C | $Tl_A$ of sample A<br>°C | $Tl_A$ of sample B<br>°C |
| a                  | 255,0                     | 249,2                     | 256,7                    | 256,4                    |
| b                  | 259,7                     | N/A                       | 260,4                    | 257,7                    |
| c                  | 249,9                     | 238,9                     | 251,2                    | 243,8                    |
| d                  | 260,2                     | N/A                       | 262,3                    | 248,2                    |
| e                  | 242,8                     | 251,4                     | 248,3                    | 255,2                    |
| f                  | 254,3                     | 213,7                     | 256,1                    | 250,7                    |
| g                  | 245,5                     | 245,3                     | 256,2                    | 251,4                    |
| h                  | 249,5                     | 250,5                     | 251,6                    | 260,1                    |
| i                  | 222,7                     | 253,0                     | 247,1                    | 252,4                    |
| j                  | 253,0                     | N/A                       | 258,8                    | 257,0                    |
| k                  | 251,1                     | 234,2                     | 254,9                    | 248,7                    |
| Average            | 249,3                     | 243,1                     | 254,9                    | 253,3                    |
| Standard deviation | 10,3                      | 13,2                      | 4,9                      | 4,9                      |

**Table 7 –  $RTE_A$  determined by Method A and  $Tl_A$  by Method B for tensile strength**

| Laboratory         | Method A                  |                           | Method B                 |                          |
|--------------------|---------------------------|---------------------------|--------------------------|--------------------------|
|                    | $RTE_A$ of sample A<br>°C | $RTE_A$ of sample B<br>°C | $Tl_A$ of sample A<br>°C | $Tl_A$ of sample B<br>°C |
| a                  | 250,7                     | 250,7                     | 252,4                    | 256,1                    |
| b                  | 255,6                     | 257,8                     | 256,8                    | 257,5                    |
| c                  | 245,8                     | 249,6                     | 246,1                    | 243,4                    |
| d                  | 256,2                     | 215,2                     | 258,2                    | 247,9                    |
| e                  | 236,3                     | 256,5                     | 242,8                    | 253,9                    |
| f                  | 250,5                     | 252,0                     | 251,7                    | 250,4                    |
| g                  | 241,4                     | 243,6                     | 251,8                    | 250,1                    |
| h                  | 243,8                     | 263,2                     | 246,6                    | 259,9                    |
| i                  | 216,9                     | 256,3                     | 241,5                    | 252,1                    |
| j                  | 250,6                     | 241,8                     | 255,2                    | 256,6                    |
| k                  | 247,0                     | 249,8                     | 250,4                    | 248,4                    |
| Average            | 244,9                     | 248,8                     | 250,3                    | 252,4                    |
| Standard deviation | 11,0                      | 12,7                      | 5,5                      | 4,9                      |

**Table 8 –  $RTE_A$  determined by Method A and  $TI_A$  by Method B for impact strength**

| Laboratory         | Method A                  |                           | Method B                 |                          |
|--------------------|---------------------------|---------------------------|--------------------------|--------------------------|
|                    | $RTE_A$ of sample A<br>°C | $RTE_A$ of sample B<br>°C | $TI_A$ of sample A<br>°C | $TI_A$ of sample B<br>°C |
| a                  | 257,8                     | 259,3                     | 256,3                    | 260,7                    |
| b                  | 260,7                     | 266,2                     | 260,1                    | 261,9                    |
| c                  | 222,3                     | 247,0                     | 250,7                    | 249,6                    |
| d                  | 255,7                     | N/A                       | 261,5                    | 253,6                    |
| e                  | 247,4                     | 256,4                     | 247,8                    | 258,8                    |
| f                  | 250,8                     | 227,1                     | 255,7                    | 255,7                    |
| g                  | 240,8                     | 252,1                     | 255,7                    | 256,4                    |
| h                  | N/A                       | 260,9                     | 251,1                    | 264,1                    |
| i                  | 179,8                     | 257,7                     | 246,6                    | 257,2                    |
| j                  | 254,3                     | N/A                       | 258,8                    | 261,2                    |
| k                  | 248,9                     | 227,6                     | 254,5                    | 254,0                    |
| Average            | 241,9                     | 250,5                     | 254,4                    | 257,6                    |
| Standard deviation | 24,4                      | 14,2                      | 4,9                      | 4,3                      |

**7.5 Difference between  $RTE_A$  and  $TI$  determined by the conventional heat ageing tests**

Differences between  $RTE_A$  or  $TI_A$  and  $TI$ , which is a numerical value remaining after  $TI$  is deducted from  $RTE_A$  or  $TI_A$ , are shown in Table 9, Table 10, and Table 11 for dielectric strength, tensile strength, and impact strength, respectively.

**Table 9 – Difference between  $RTE_A$  or  $TI_A$ , and  $TI$  for dielectric strength**

| Laboratory         | Method A                       |                                | Method B                      |                               |
|--------------------|--------------------------------|--------------------------------|-------------------------------|-------------------------------|
|                    | $RTE_A - TI$ of sample A<br>°C | $RTE_A - TI$ of sample B<br>°C | $TI_A - TI$ of sample A<br>°C | $TI_A - TI$ of sample B<br>°C |
| a                  | 5                              | 7,7                            | 6,7                           | 14,9                          |
| b                  | 9,7                            | N/A                            | 10,4                          | 16,2                          |
| c                  | -0,1                           | -2,6                           | 1,2                           | 2,3                           |
| d                  | 10,2                           | N/A                            | 12,3                          | 6,7                           |
| e                  | -7,2                           | 9,9                            | -1,7                          | 13,7                          |
| f                  | 4,3                            | -27,8                          | 6,1                           | 9,2                           |
| g                  | -4,5                           | 3,8                            | 6,2                           | 9,9                           |
| h                  | -0,5                           | 9,0                            | 1,6                           | 18,6                          |
| i                  | -27,3                          | 11,5                           | -2,9                          | 10,9                          |
| j                  | 3,0                            | N/A                            | 8,8                           | 15,5                          |
| k                  | 1,1                            | -7,3                           | 4,9                           | 7,2                           |
| Average            | -0,6                           | 0,5                            | 4,9                           | 11,4                          |
| Mean               | 1,1                            | 5,8                            | 6,1                           | 10,9                          |
| Standard deviation | 10,3                           | 13,2                           | 4,9                           | 4,9                           |

**Table 10 – Difference between  $RTE_A$  or  $TI_A$ , and TI for tensile strength**

| Laboratory         | Method A                      |                               | Method B                     |                              |
|--------------------|-------------------------------|-------------------------------|------------------------------|------------------------------|
|                    | $RTE_A$ -TI of sample A<br>°C | $RTE_A$ -TI of sample B<br>°C | $TI_A$ -TI of sample A<br>°C | $TI_A$ -TI of sample B<br>°C |
| a                  | 0,7                           | 9,2                           | 2,4                          | 14,6                         |
| b                  | 5,6                           | N/A                           | 6,8                          | 16,0                         |
| c                  | -4,7                          | 8,1                           | -3,9                         | 1,9                          |
| d                  | 6,2                           | N/A                           | 8,2                          | 6,4                          |
| e                  | -13,7                         | 15,0                          | -7,2                         | 12,4                         |
| f                  | 0,5                           | 10,5                          | 1,7                          | 8,9                          |
| g                  | -8,6                          | 2,1                           | 1,8                          | 8,6                          |
| h                  | -6,2                          | 21,7                          | -3,4                         | 18,4                         |
| i                  | -33,1                         | 14,8                          | -8,5                         | 10,6                         |
| j                  | 0,6                           | N/A                           | 5,2                          | 15,1                         |
| k                  | -3,0                          | 8,3                           | 0,4                          | 6,9                          |
| Average            | -5,1                          | 11,2                          | 0,3                          | 10,9                         |
| Mean               | -3,0                          | 9,8                           | 1,7                          | 10,6                         |
| Standard deviation | 11,0                          | 5,9                           | 5,5                          | 4,9                          |

**Table 11 – Difference between  $RTE_A$  or  $TI_A$ , and TI for impact strength**

| Laboratory         | Method A                      |                               | Method B                     |                              |
|--------------------|-------------------------------|-------------------------------|------------------------------|------------------------------|
|                    | $RTE_A$ -TI of sample A<br>°C | $RTE_A$ -TI of sample B<br>°C | $TI_A$ -TI of sample A<br>°C | $TI_A$ -TI of sample B<br>°C |
| a                  | 7,8                           | 17,8                          | 6,3                          | 19,2                         |
| b                  | 10,7                          | N/A                           | 10,1                         | 20,4                         |
| c                  | -27,7                         | 5,5                           | 0,7                          | 8,1                          |
| d                  | 5,7                           | N/A                           | 11,5                         | 12,1                         |
| e                  | -2,6                          | 14,9                          | -2,2                         | 17,3                         |
| f                  | 0,8                           | -14,4                         | 5,7                          | 14,2                         |
| g                  | -9,2                          | 10,6                          | 5,7                          | 14,9                         |
| h                  | N/A                           | 19,4                          | 1,1                          | 22,6                         |
| i                  | -70,2                         | 16,2                          | -3,4                         | 15,7                         |
| j                  | 4,3                           | N/A                           | 8,8                          | 19,7                         |
| k                  | -1,1                          | -13,9                         | 4,5                          | 12,5                         |
| Average            | -8,2                          | 7,0                           | 4,4                          | 16,1                         |
| Mean               | -0,1                          | 12,8                          | 5,7                          | 15,7                         |
| Standard deviation | 24,4                          | 13,8                          | 4,9                          | 4,3                          |

## 8 Observations from the round robin test results

### 8.1 General

In the round robin test, the following productive points were observed for the validation of IEC TS 60216-7-1:

- both  $RTE_A$  and  $TI_A$  determined in these round robin tests mostly had similar values to  $TI$  by conventional heat ageing with a difference in temperature of 20 °C or less in most cases, and
- Method A using the degree of conversion given by the calculation failed to provide solutions of  $RTE_A$  in a few laboratories and their standard deviations were also relatively high, whereas Method B using the fixed degree of conversion based on experiences at 0,05 provided lower standard variations between laboratories.

It is noted, however, that results show differences between the laboratories, with differences in temperature exceeding 20 °C in some instances of the report.

In particular, the difference of within 20 °C from the conventional heat ageing is useful, because the conventional RTE in accordance with the IEC 60216 series also contains this level of reproducibility issues due to variation factors of heating ovens, test plaques and lot-to-lot variation of materials, etc.

As a practical example of implementing long term thermal endurance evaluation according to IEC 60216-8 [9], a certification of the thermal endurance properties provides the industry with a temperature classification with some increments according to the temperature assigned such as 20 °C increments over 180 °C of RTI, 10 °C increments from 130 °C through 180 °C and 5 °C increments up to 130 °C [10].

As  $TI$  of the two LCP materials evaluated in this document have been determined over 180 °C, 20 °C or less difference between  $RTE_A$  or  $TI_A$  and  $TI$ , conformity with the temperature classification in accordance with the above conventional heat ageing methods can be established.

On the other hand, the round robin test also raised technical concerns as follows:

- laboratory i determined an  $RTE_A$  of the LCP sample A significantly different from those by other laboratories in all the three properties, and
- a few laboratories were not able to determine  $RTE_A$  of sample B, because the degree of conversion was not appropriately calculated from the fitting curve in 6.4.

The round robin test participants discussed the rationale, and the following potential factors which can have an influence on the above issues were raised and then checked as follows:


- 1) sample weight variation,
- 2) humidity and hydrolysis of the sample,
- 3) repeatability of TGA curves, and
- 4) baseline drift and spacing between multiple curves of TGA.

### 8.2 Sample weight variation

ISO 11358-2 [3] provides the tolerance of the sample weight per one run of TGA as  $\pm 1$  % with less than 10 mg, however, the round robin test applied a wider tolerance of 5 mg  $\pm$  0,5 mg (10 % tolerance). Therefore, the sample weight variation was identified as one of the potential variation factors.


The scatter plot between the standard deviation of sample mass and the difference between TI and  $RTE_A$  ( $TI_A$ ) was evaluated, however, less correlation was observed between the two factors which are shown in Figure 2 and Figure 3.

Because of these facts, the sample weight variation can be considered with respect to ISO 11358-2 [3], but not as a significant factor with regard to the technical concerns of reproducibility in laboratories mentioned above.

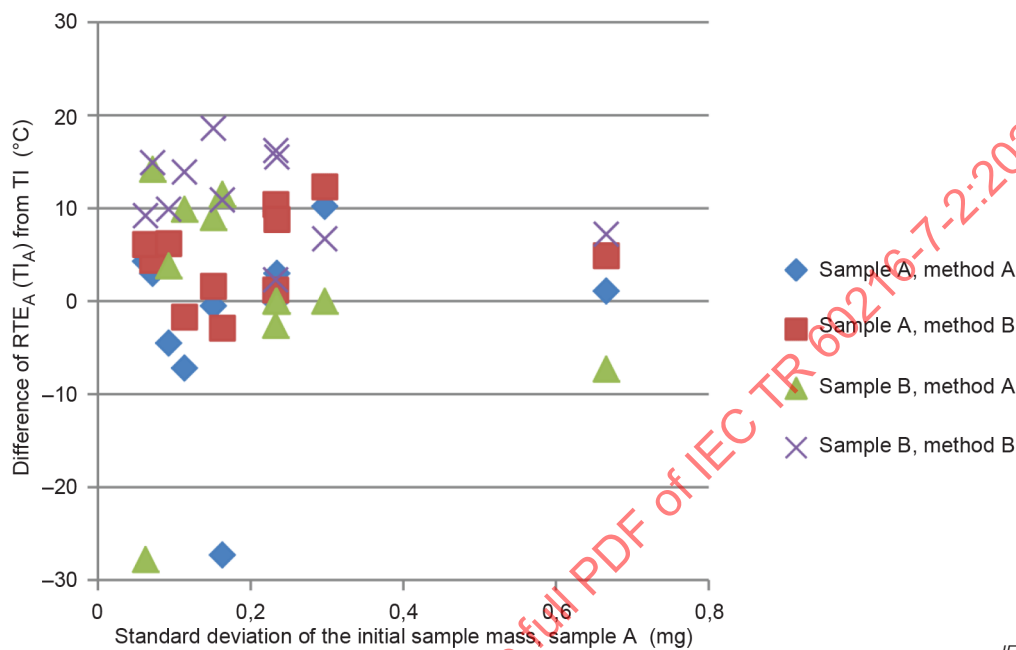

IEC

**Figure 2 – Correlation between the initial sample mass of sample A and the difference of  $RTE_A$  ( $TI_A$ ) from  $TI$**

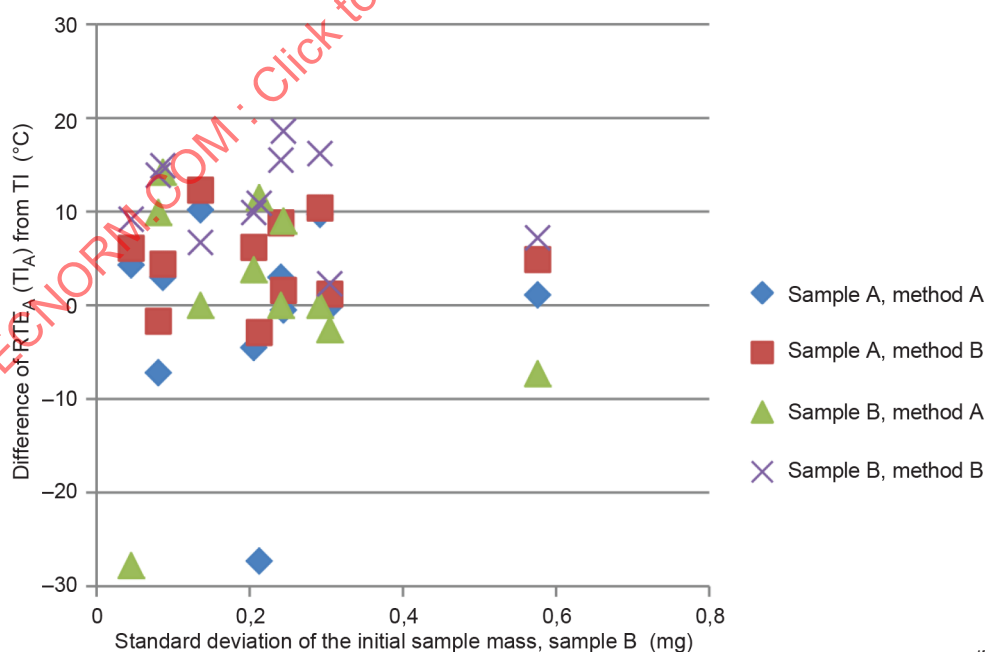

IEC

**Figure 3 – Correlation between the initial sample mass of sample B and the difference of  $RTE_A$  ( $TI_A$ ) from  $TI$**

### 8.3 Humidity and hydrolysis of the sample

The round robin test samples were liquid crystal polyesters, and since moisture can accelerate the polymer degradation with hydrolysis, humidity and hydrolysis were therefore pointed out as the factors potentially influencing the reproducibility at specific laboratories.

At first, all of samples A and samples B provided to the laboratories were homogenized and pre-dried at 140 °C for 4 h to remove absorbed water during freeze-pulverization and then put into vials before shipment. Natural moisture absorption of LCP is very small, for instance, the equilibrium moisture content of the LCP polymer is approximately 0,03 % (300 ppm) at 23 °C and 50 % RH. Sample A and sample B are 30 % glass filled grades and the actual equilibrium moisture after the vials are opened is expected to be lower than this value. In addition, the sample loaded to TGA was pre-conditioned at 100 °C for 1 h in the furnace. At the above point, absorbed moisture from the sample cannot be considered a major factor of  $RTE_A$  and  $TI_A$  variation.

Next, atmosphere in the TGA furnace can be another factor which has an influence on hydrolysis of the polymer around the thermal decomposition temperature in the TGA furnace. In fact it was different in each laboratory, because the round robin test requested participants to report, if possible, what kind of air was used to supply purge gas into the TGA furnace. Not all laboratories responded, however, and it was determined that some of the laboratories (a, b, and f) used dry air (moisture content guaranteed less than 1 ppm or 2 ppm) while others (laboratories e, g, and h) used compressed air with or without an air dryer. In fact, there was no relation observed between the specific laboratories mentioned above and the difference in air supply. However, dry air is useful and its use was recommended to all of the participants to decrease a side effect factor of reproducibility issues. For reference, dry air is given as an example of purge gas in ISO 11358-1.

### 8.4 Considerations on repeatability of TGA curves

In the round robin test based on IEC TS 60216-7-1 and ISO 11358-2 [3], multiple TGA curves with different heating rates were used for the calculation of the degree of conversion and the activation energy of the candidate material. If one TGA curve has low repeatability, correlation between the degree of conversion and the activation energy can also be changed to determine  $RTE_A$  or  $TI_A$ .

Taking this factor into consideration, supplemental measurement was rerun at 8 K/min for both sample A and sample B in every participating laboratory. A summary of the degree of conversion is shown in Table 12.

NOTE The rerun data at 8 K/min were not reported by laboratory i.

**Table 12 – Comparison of degree of conversion with original or rerun data at 8 K/min**

| Laboratory         | Degree of conversion for $E_a$<br>of sample A at 130,6 kJ/mol |                          | Degree of conversion for $E_a$<br>of sample B at 142,3 kJ/mol |                          |
|--------------------|---------------------------------------------------------------|--------------------------|---------------------------------------------------------------|--------------------------|
|                    | Original data at<br>8 K/min                                   | Rerun data at<br>8 K/min | Original data at<br>8 K/min                                   | Rerun data<br>at 8 K/min |
| a                  | 0,032 7                                                       | 0,084 7                  | 0,019 9                                                       | 0,019 5                  |
| b                  | N/A                                                           | N/A                      | 0,039 3                                                       | 0,033 6                  |
| c                  | 0,040 8                                                       | 0,022 1                  | 0,043 7                                                       | 0,038 4                  |
| d                  | N/A                                                           | N/A                      | 0,037 8                                                       | 0,037 2                  |
| e                  | 0,037 7                                                       | 0,051 7                  | 0,024 4                                                       | 0,024 4                  |
| f                  | 0,021 9                                                       | 0,020 5                  | 0,040 6                                                       | 0,040 1                  |
| g                  | 0,036 7                                                       | 0,035 1                  | 0,024 6                                                       | 0,020 9                  |
| h                  | 0,034 2                                                       | 0,037 2                  | 0,037 1                                                       | 0,017 2                  |
| i                  | 0,051 5                                                       | -                        | 0,032 1                                                       | -                        |
| j                  | N/A                                                           | N/A                      | 0,016 7                                                       | 0,013 7                  |
| k                  | 0,060 0                                                       | N/A                      | 0,031 1                                                       | 0,026 0                  |
| Average            | 0,039                                                         | 0,042                    | 0,032                                                         | 0,027                    |
| Standard deviation | 0,012                                                         | 0,024                    | 0,009                                                         | 0,010                    |


As shown in Table 12, two laboratories (a and e) had a significant change in the given degree of conversion for sample A by rerun data at 8 K/min, which exceeded the degree of conversion at 0,05 (Method B). Another laboratory k was not able to obtain the results of the degree of conversion for sample A, even though the laboratory obtained the given degree of conversion with the original data at 8 K/min. From those observations, it is suggested that the repeatability of TGA raw data can have a significant impact on the calculation of the degree of conversion which affects repeatable determination of  $RTE_A$  or  $TI_A$ , as well. In this study, only one test condition of heating rates (8 K/min) was retested for a preliminary review of repeatability check. It is suggested that the repeatability be further evaluated also with retesting at other heating rates for an assessment of the precision.

On the above point, population of the TGA raw curve data (e.g. evaluation of 2 or 3 runs at the same heating rate) and normalization of those raw data can be further considered before analysis in accordance with ISO 11358-2 [3] is conducted in each laboratory, if repeatability and reproducibility improvements are necessary.

It is suggested that repeatability of the TGA curve is checked at all heating rates to decrease variations of the degree of conversion and the activation energy determined by TGA.

### 8.5 Baseline drift and responsiveness to heating rates of TGA

To examine the remaining reasons why no result of degree of conversion and  $RTE_A$  by Method A was provided to sample A in three laboratories (b, d and j) for dielectric strength, the raw TGA curves, logarithm graphs according to ISO 11358-2 [3], and the fitting curve example given in Figure 1 were plotted as shown in Figure 4, Figure 5 and Figure 6 respectively, with the comparative examples of three other laboratories data which obtained a degree of conversion and  $RTE_A$ .

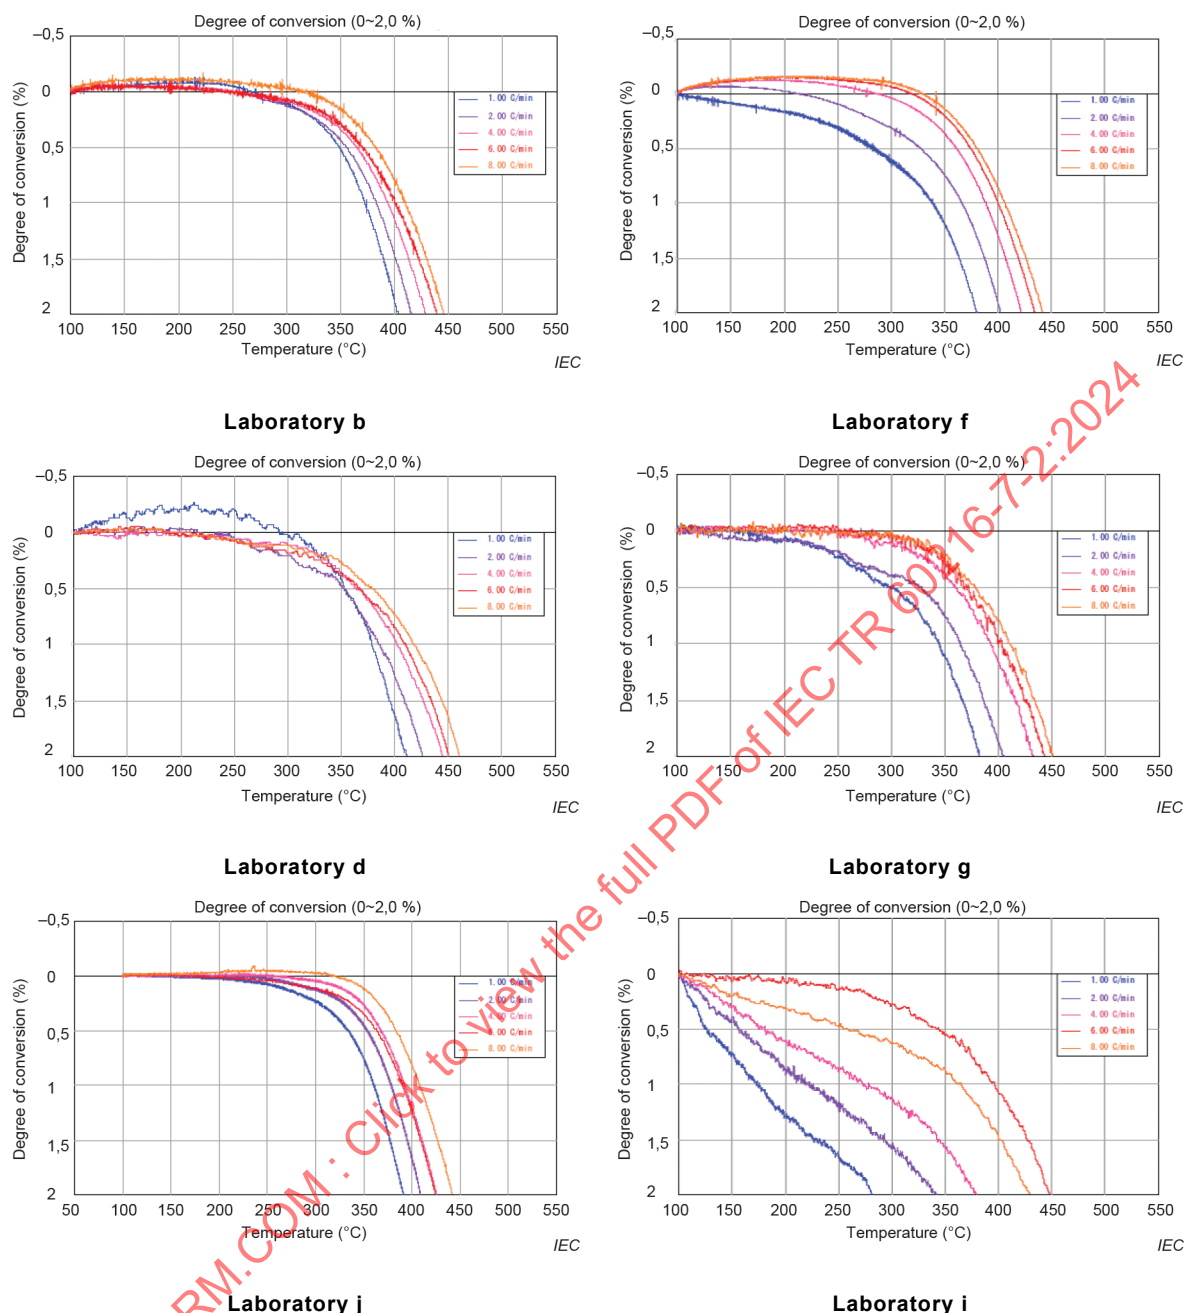

**Figure 4 – Overlay charts of TGA curves in multiple heating rates in multiple laboratories (enlarged)**

The three graphs on the left in Figure 4 and Figure 5 were evaluated in the laboratories which had no result of the degree of conversion to  $E_a$  and  $RTE_A$  to sample B in accordance with the fitting curve example given in Figure 1. The other three graphs on the right in Figure 4 and Figure 5 were tested in the laboratories which all obtained a result of the degree of conversion, although different trends were observed in the final determination of  $RTE_A$ . It was observed that the three graphs of overlay TGA curves on the left commonly showed a smaller difference between multiple heating rates (narrower range in temperature among the curves) than that of the three graphs on the right. It appears that the three graphs of logarithm on the left presented a steeper slope than that from the three graphs on the right. When the responsiveness of degradation to change in heating rates is significantly low, the activation energy is calculated at a significantly high value. And in fact, the data in Figure 4 and Figure 5 from those laboratories on the left gave higher activation energies in the whole range of degree of conversion in TGA, as shown in Figure 6.

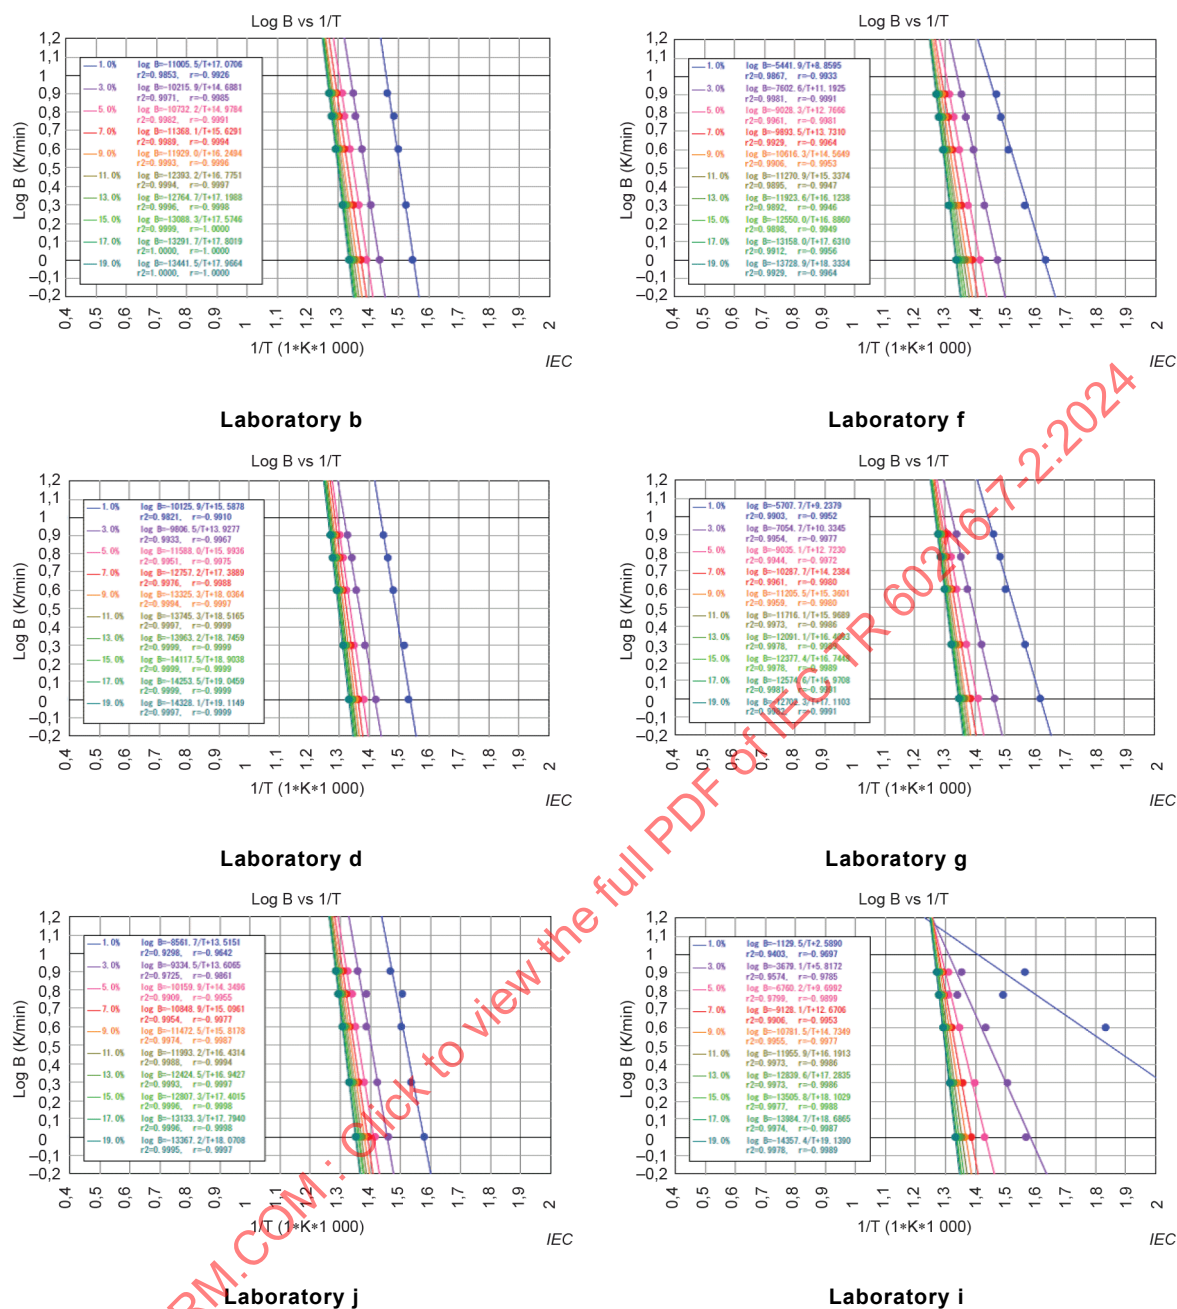


Figure 5 – Logarithm plots for activation energy calculation

It was not clarified why laboratories b, d, and j obtained lower differences between TGA curves in multiple heating rates, but it is suggested that repeatability of TGA curves in the same heating rate possibly affected the results as observed in 8.3. It was indeed confirmed that laboratory d and laboratory f in Figure 4 and Figure 5 above used an identical model of TGA apparatus with the same dry air conditions (moisture content less than 1 ppm) which cannot be considered as the rationale of responsiveness. In fact, these two laboratories showed similar TGA curves at 8 K/min, but it is suggested that the same approach of repeatability check be followed at lower heating rates for the next step, if further reproducibility improvement is needed.

The baseline drift of TGA curves (very slight increase in mass at initiation of heating) was observed in some laboratories but not in others. Obviously, the drift affects the difference in temperature at the same degree of conversion between the TGA curves of multiple heating rates, and it also has an influence on the unusual ascending order of the temperature to heating rates. Treatment or cancellation of the baseline can therefore be further discussed to decide on the next opportunity of investigation in order to fine tune the round robin test conditions.

Other observations showed that laboratory i had significantly different TGA curves than all the others, in terms of very rapid mass loss at initiation of heating from 100 °C, which gave very low activation energy at a small degree of conversion, as shown in Figure 6 and a significantly lower  $RTE_A$  to sample A. As no other laboratory showed a same or similar trend of the phenomena, their data are considered outside the scope of this document until additional information on apparatus and conditions during test is provided by the laboratory.

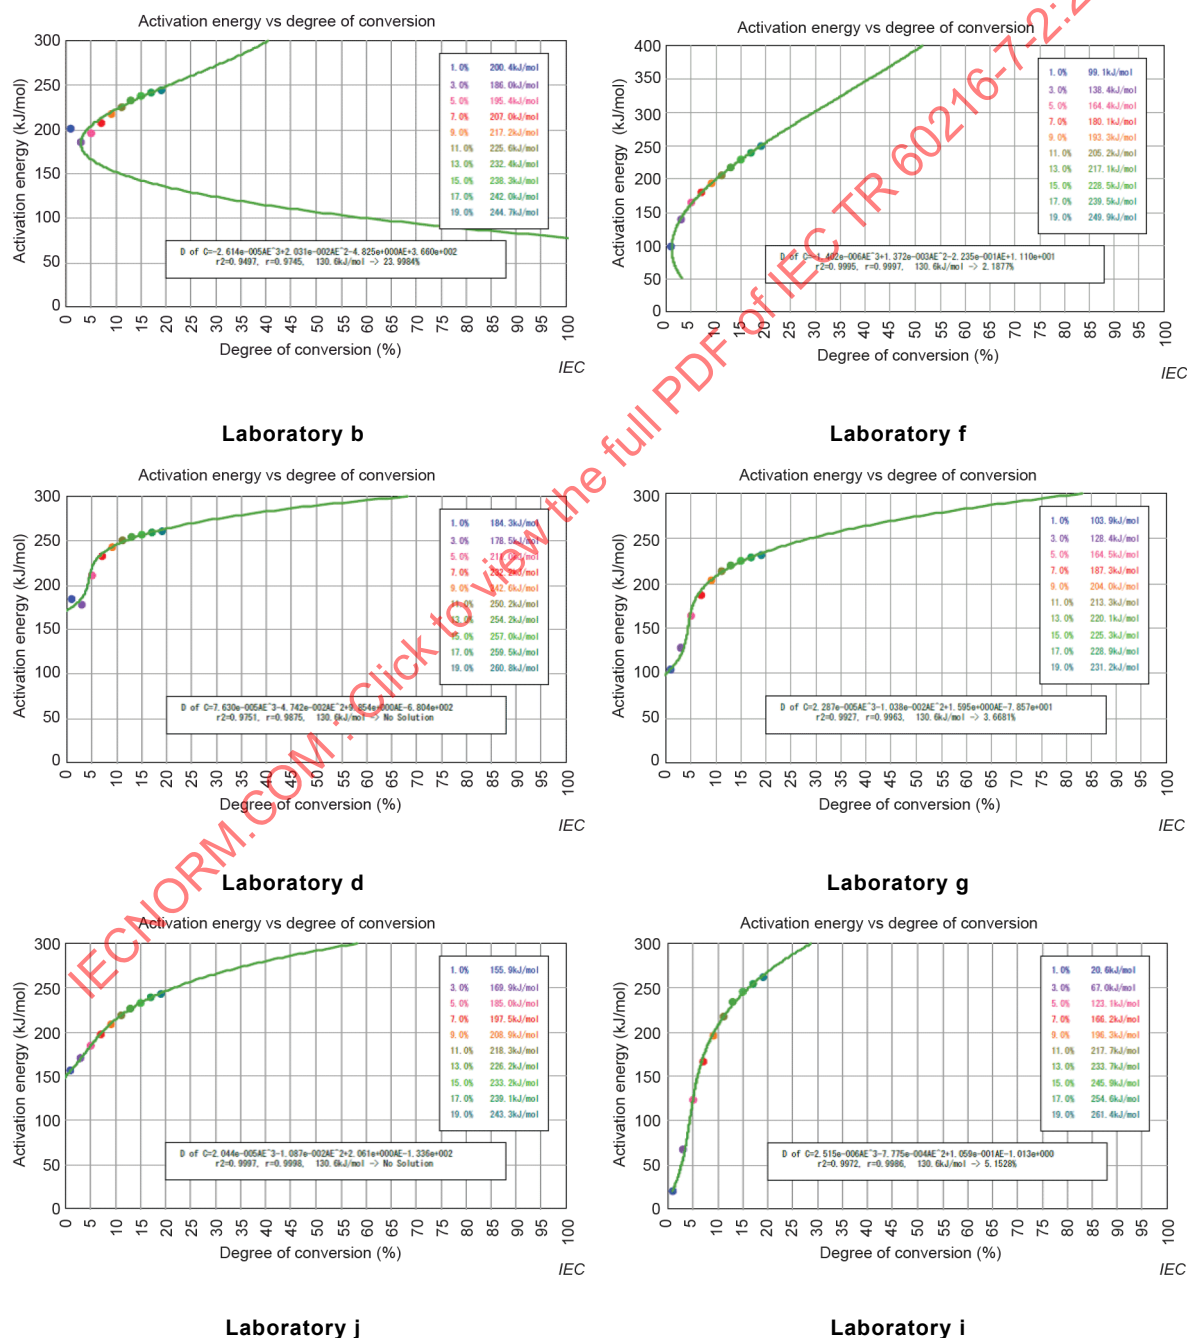


Figure 6 – Fitting curves of degree of conversion versus activation energy by TGA

## 9 Conclusion

This round robin test applied to one material category of liquid crystal polyester (LCP) and in which eleven laboratories from four countries participated, provided extremely useful findings to accelerate the evaluation of thermal endurance properties in the IEC 60216 series. These findings are as follows.

- By selecting a specific material category where one single reaction to heat is predominant, the two samples of LCP had very similar  $RTE_A$  or  $TI_A$  (based on IEC TS 60216-7-1) to the  $TI$  of the conventional heat ageing (based on the existing IEC 60216 series), within a small difference, except for one laboratory.
- $RTE_A$  determination by using the degree of conversion corresponding to the activation energy of the reference material based on past conventional heat ageing provided closer results to  $TI$ , whereas  $TI_A$  determination by using the fixed degree of conversion at 5 %, which is not dependent on the control material, provided more reproducible results to  $TI$ , even when higher temperatures were assigned in total. In addition,  $TI_A$  provided a solution to obtain tangible results when  $RTE_A$  was not determined by this method due to repeatability issues of TGA.
- It was found that TGA curves will not always be repeatable in the same material and at the same heating rates with the same test conditions, depending on the apparatus condition. Sufficient differences in temperatures detected at the same degree of conversion and provided by change in multiple heating rates gave more confidence in the analysis based on ISO 11358-2 [3] and IEC TS 60216-7-1. Confirmation of TGA curves per heating rate are therefore suggested with a few populations of the TGA runs, to check the raw data variation for fine tuning of the repeatable results.
- Identical mass of test sample ( $\pm 1$  %), dry air for purge gas into the TGA furnace ( $H_2O$  content less than a few ppm) and cancellation of the base line drift of the TGA curves can be further considered as potential factors which can affect the determination of  $RTE_A$  and  $TI_A$ .
- A good criterion to foresee the robustness of the testing procedure and thus the accuracy of  $TI_A$  and  $RTE_A$  is to repeat at least one test and check that the variance compared to the first run of TGA is small, for example, less than 10 % of the degree of conversion at a certain temperature or activation energy.
- While the difference with  $TI$  and  $E_a$  from heat ageing was not very significant between the two LCP materials given by one laboratory, the difference of  $RTI_A$  or  $TI_A$  between laboratories was significant in some instances (which possibly led to differences in excess of 20 °C between laboratories).

Additional round robin studies using polybutylene terephthalate are provided in Annex A.

## Annex A (informative)

### Additional round robin studies with polybutylene terephthalate

#### A.1 Objectives

The additional study preselected a generic polymer type of polybutylene terephthalate (PBT) materials having a lower TI than LCP, to validate the procedure of IEC TS 60216-7-1 and enhance data consistency based on the findings of necessary improvements in the round robin using LCP as follows:

- compensation of equipment baseline drift for TGA measurement;
- water content of purge air or nitrogen gas less than 0,001 % by mass;
- mass and temperature calibrations in accordance with ISO 11358-1; and
- heavier samples amount and smaller tolerance of 10 mg  $\pm$  0,1 mg.

#### A.2 Test specimens

Two powdered materials of unfilled PBT (PBT) and 30 % glass fibre reinforced PBT (PBT-GF30) were tested. The samples were powdered by cryogenic grinder with 0,5 mm mesh and then the homogeneous samples were delivered to 10 laboratories (A, B, C, D, E, F, G, H, I and J). The TI and HIC of the two materials in accordance with the conventional heat ageing are shown in Table A.1.

**Table A.1 – Heat ageing properties of the PBT test specimens by the conventional procedure in accordance with IEC 60216-5 [4]**

| Temperature in ovens | Time to end-point at 50 % retention of initial dielectric strength |          | Time to end-point at 50 % retention of initial tensile strength |          | Time to end-point at 50 % retention of initial impact strength |          |
|----------------------|--------------------------------------------------------------------|----------|-----------------------------------------------------------------|----------|----------------------------------------------------------------|----------|
|                      | h                                                                  |          | h                                                               |          | h                                                              |          |
| °C                   | PBT                                                                | PBT-GF30 | PBT                                                             | PBT-GF30 | PBT                                                            | PBT-GF30 |
| 180                  | 686                                                                | 850      |                                                                 | 881      |                                                                |          |
| 170                  | 1 433                                                              | 194      |                                                                 | 2 431    |                                                                |          |
| 160                  | 3 043                                                              | 4 190    |                                                                 | 4 516    |                                                                |          |
| 150                  | 6 113                                                              | 7 877    | 418                                                             | 7 362    |                                                                | 2 032    |
| 140                  |                                                                    |          | 3 506                                                           |          | 458                                                            |          |
| 130                  |                                                                    |          |                                                                 |          |                                                                |          |
| 120                  |                                                                    |          |                                                                 |          |                                                                |          |
| TI (°C)              | 116,6                                                              | 118,6    | 209,7                                                           | 111,0    | 140,9                                                          | 78,7     |
| $E_a$ (kJ/mol)       | 135,7                                                              | 139,4    | 125,7                                                           | 138,7    | 104,8                                                          | 111,2    |

#### A.3 Test apparatus

The same apparatus as used for TGA (see 5.1) was used for the evaluations. In addition to the conditions specified in 5.1, all the laboratories for this additional study did compensation of the equipment baseline drift. For the purge gas (see 5.2), all the laboratories selected dry air (water content less than 0,001 % by mass).

## A.4 Test procedures

For pre-conditioning (see 6.2), this study used  $10 \text{ mg} \pm 0,1 \text{ mg}$  of the test sample which was initially measured in each laboratory and mounted on the empty pan in the furnace opened. Then the furnace was closed and pre-conditioned in equilibrium at  $50 \text{ }^{\circ}\text{C}$  for 5 min until heating tests were started at  $50 \text{ }^{\circ}\text{C}$ . Other procedures after stating the TGA measurement followed the round robin with LCPs (see 6.3, 6.4 and 6.5).

## A.5 Test results

Degrees of conversion at the activation energy identical to those from conventional heat ageing (see 7.2) are shown in Table A.2.

NOTE The two studies using reported LCP materials and PBT materials specified in this Annex A were analysed by different software, even though both followed the same analytical methodology in accordance with IEC TS 60216-7-1. Software algorithms are minor but it is possible they will not provide identical values depending on significant figures of raw data values.

It was observed that both sample PBT and sample PBT-GF30 had a higher degree of conversion under TGA (around 5 % to 20 % mass loss) correlating to thermal degradation of the dielectric strength under a heating oven in terms of the identical activation energies.

**Table A.2 – Degrees of conversion at the activation energy identical to that from conventional heat ageing**

| Laboratory                | Degree of conversion identical to activation energy of the conventional heating, sample PBT | Degree of version identical to activation energy to the conventional heating, sample PBT-GF30 |
|---------------------------|---------------------------------------------------------------------------------------------|-----------------------------------------------------------------------------------------------|
| A                         | 0,0506                                                                                      | 0,2831                                                                                        |
| B                         | 0,0817                                                                                      | 0,1816                                                                                        |
| C                         | 0,0648                                                                                      | 0,3360                                                                                        |
| D                         | 0,0525                                                                                      | 0,1927                                                                                        |
| E                         | 0,0505                                                                                      | 0,3030                                                                                        |
| F                         | 0,0783                                                                                      | 0,0057                                                                                        |
| G                         | 0,1961                                                                                      | 0,2262                                                                                        |
| H                         | 0,2720                                                                                      | 0,4496                                                                                        |
| I                         | 0,0506                                                                                      | 0,0763                                                                                        |
| J                         | 0,0517                                                                                      | 0,3559                                                                                        |
| <b>Average</b>            | <b>0,0949</b>                                                                               | <b>0,2410</b>                                                                                 |
| <b>Standard deviation</b> | <b>0,0764</b>                                                                               | <b>0,1333</b>                                                                                 |

$\text{HIC}_A$  of the PBT materials determined by Method A and Method B according to IEC TS 60216-7-1 (see 7.3) are shown in Table A.3, Table A.4, Table A.5 for dielectric strength, tensile strength, and impact strength, respectively.

**Table A.3 – HIC<sub>A</sub> determined by Method A and Method B for dielectric strength**

| Laboratory                | Method A                       |                                     | Method B                       |                                     |
|---------------------------|--------------------------------|-------------------------------------|--------------------------------|-------------------------------------|
|                           | HIC <sub>A</sub> of sample PBT | HIC <sub>A</sub> of sample PBT-GF30 | HIC <sub>A</sub> of sample PBT | HIC <sub>A</sub> of sample PBT-GF30 |
| A                         | 6,2                            | 12,0                                | 8,0                            | 12,3                                |
| B                         | 7,4                            | 10,6                                | 9,4                            | 11,5                                |
| C                         | 6,1                            | 12,5                                | 9,1                            | 12,3                                |
| D                         | 5,9                            | 11,4                                | 7,6                            | 11,4                                |
| E                         | 6,1                            | 12,1                                | 8,1                            | 12,3                                |
| F                         | N/A                            | 7,0                                 | 9,6                            | 7,4                                 |
| G                         | 8,0                            | 8,9                                 | 10,9                           | 12,5                                |
| H                         | 7,4                            | 10,3                                | 13,6                           | 15,4                                |
| I                         | 7,4                            | 9,7                                 | 8,4                            | 9,9                                 |
| J                         | 6,4                            | 12,5                                | 8,5                            | 12,6                                |
| <b>Average</b>            | <b>6,8</b>                     | <b>10,7</b>                         | <b>9,3</b>                     | <b>11,8</b>                         |
| <b>Standard deviation</b> | <b>0,8</b>                     | <b>1,8</b>                          | <b>1,8</b>                     | <b>2,1</b>                          |

NOTE N/A means that in the cubic approximation of activation energy versus the degree of conversion equation did not provide a solution.

**Table A.4 – HIC<sub>A</sub> determined by Method A and Method B for tensile strength**

| Laboratory                | Method A                       |                                     | Method B                       |                                     |
|---------------------------|--------------------------------|-------------------------------------|--------------------------------|-------------------------------------|
|                           | HIC <sub>A</sub> of sample PBT | HIC <sub>A</sub> of sample PBT-GF30 | HIC <sub>A</sub> of sample PBT | HIC <sub>A</sub> of sample PBT-GF30 |
| A                         | 5,7                            | N/A                                 | 7,4                            | 11,3                                |
| B                         | 6,9                            | N/A                                 | 8,8                            | 10,7                                |
| C                         | 5,7                            | N/A                                 | 8,4                            | 11,4                                |
| D                         | 5,3                            | N/A                                 | 7,0                            | 10,5                                |
| E                         | 5,7                            | N/A                                 | 7,5                            | 11,4                                |
| F                         | N/A                            | N/A                                 | 9,0                            | 6,8                                 |
| G                         | 7,8                            | N/A                                 | 10,3                           | 11,5                                |
| H                         | 7,0                            | N/A                                 | 13,1                           | 14,3                                |
| I                         | 7,1                            | N/A                                 | 7,8                            | 9,1                                 |
| J                         | 5,9                            | N/A                                 | 7,9                            | 11,7                                |
| <b>Average</b>            | <b>6,3</b>                     | <b>N/A</b>                          | <b>8,7</b>                     | <b>10,9</b>                         |
| <b>Standard deviation</b> | <b>0,9</b>                     | <b>N/A</b>                          | <b>1,8</b>                     | <b>1,9</b>                          |

NOTE N/A means that in the cubic approximation of activation energy versus the degree of conversion equation did not provide a solution.

**Table A.5 –  $HIC_A$  determined by Method A and Method B for impact strength**

| Laboratory                | Method A              |                            | Method B              |                            |
|---------------------------|-----------------------|----------------------------|-----------------------|----------------------------|
|                           | $HIC_A$ of sample PBT | $HIC_A$ of sample PBT-GF30 | $HIC_A$ of sample PBT | $HIC_A$ of sample PBT-GF30 |
| A                         | 5,4                   | 12,0                       | 6,6                   | 11,3                       |
| B                         | 8,0                   | 7,0                        | 7,8                   | 10,7                       |
| C                         | 5,5                   | 11,6                       | 7,5                   | 11,4                       |
| D                         | 6,0                   | 10,6                       | 6,3                   | 10,5                       |
| E                         | 5,5                   | 11,7                       | 6,7                   | 11,4                       |
| F                         | N/A                   | 5,8                        | 8,0                   | 6,8                        |
| G                         | 8,4                   | 6,6                        | 9,0                   | 11,5                       |
| H                         | 7,3                   | 7,7                        | 11,3                  | 14,3                       |
| I                         | 8,6                   | 7,5                        | 7,0                   | 9,1                        |
| J                         | 5,6                   | 11,1                       | 7,0                   | 11,7                       |
| <b>Average</b>            | <b>6,7</b>            | <b>9,2</b>                 | <b>7,7</b>            | <b>10,9</b>                |
| <b>Standard deviation</b> | <b>1,4</b>            | <b>2,4</b>                 | <b>1,5</b>            | <b>1,9</b>                 |

NOTE N/A means that in the cubic approximation of activation energy versus the degree of conversion equation did not provide a solution.

$RTE_A$  determined by Method A and  $TI_A$  by Method B (see 7.4) are shown in Table A.6, Table A.7 and Table A.8 for dielectric strength, tensile strength, and impact strength, respectively.

**Table A.6 –  $RTE_A$  determined by Method A and  $TI_A$  by Method B for dielectric strength**

| Laboratory                | Method A              |                            | Method B             |                           |
|---------------------------|-----------------------|----------------------------|----------------------|---------------------------|
|                           | $RTE_A$ of sample PBT | $RTE_A$ of sample PBT-GF30 | $TI_A$ of sample PBT | $TI_A$ of sample PBT-GF30 |
| A                         | 144,9                 | 125,0                      | 137,2                | 124,0                     |
| B                         | 140,0                 | 131,0                      | 130,6                | 127,0                     |
| C                         | 145,3                 | 123,0                      | 132,3                | 123,9                     |
| D                         | 146,4                 | 127,7                      | 138,9                | 127,5                     |
| E                         | 145,3                 | 124,5                      | 136,5                | 123,6                     |
| F                         | N/A                   | 145,2                      | 129,8                | 143,7                     |
| G                         | 137,3                 | 137,6                      | 123,7                | 123,1                     |
| H                         | 139,7                 | 132,0                      | 110,3                | 109,9                     |
| I                         | 139,9                 | 134,7                      | 135,3                | 133,9                     |
| J                         | 144,1                 | 123,0                      | 134,9                | 122,5                     |
| <b>Average</b>            | <b>142,5</b>          | <b>130,4</b>               | <b>130,9</b>         | <b>125,9</b>              |
| <b>Standard deviation</b> | <b>3,3</b>            | <b>7,2</b>                 | <b>8,5</b>           | <b>8,6</b>                |

NOTE N/A means that in the cubic approximation of activation energy versus the degree of conversion equation did not provide a solution.

**Table A.7 –  $RTE_A$  determined by Method A and  $TI_A$  by Method B for tensile strength**

| Laboratory                | Method A              |                            | Method B             |                           |
|---------------------------|-----------------------|----------------------------|----------------------|---------------------------|
|                           | $RTE_A$ of sample PBT | $RTE_A$ of sample PBT-GF30 | $TI_A$ of sample PBT | $TI_A$ of sample PBT-GF30 |
| A                         | 125,2                 | N/A                        | 120,6                | 128,0                     |
| B                         | 121,9                 | N/A                        | 116,6                | 130,8                     |
| C                         | 125,2                 | N/A                        | 117,6                | 127,9                     |
| D                         | 126,2                 | N/A                        | 121,6                | 131,3                     |
| E                         | 125,2                 | N/A                        | 120,2                | 127,6                     |
| F                         | N/A                   | N/A                        | 116,1                | 146,1                     |
| G                         | 119,5                 | N/A                        | 112,3                | 127,2                     |
| H                         | 121,6                 | N/A                        | 103,8                | 115,0                     |
| I                         | 121,3                 | N/A                        | 119,5                | 137,1                     |
| J                         | 124,6                 | N/A                        | 119,2                | 126,6                     |
| <b>Average</b>            | <b>123,4</b>          | <b>N/A</b>                 | <b>116,7</b>         | <b>129,7</b>              |
| <b>Standard deviation</b> | <b>2,4</b>            | <b>N/A</b>                 | <b>5,3</b>           | <b>8,0</b>                |

NOTE N/A means that in the cubic approximation of activation energy versus the degree of conversion equation did not provide a solution.

**Table A.8 –  $RTE_A$  determined by Method A and  $TI_A$  by Method B for impact strength**

| Laboratory                | Method A              |                            | Method B             |                           |
|---------------------------|-----------------------|----------------------------|----------------------|---------------------------|
|                           | $RTE_A$ of sample PBT | $RTE_A$ of sample PBT-GF30 | $TI_A$ of sample PBT | $TI_A$ of sample PBT-GF30 |
| A                         | 106,0                 | 105,8                      | 100,3                | 108,6                     |
| B                         | 93,4                  | 125,3                      | 94,3                 | 111,3                     |
| C                         | 105,8                 | 107,5                      | 95,9                 | 108,5                     |
| D                         | 103,4                 | 111,4                      | 101,9                | 111,8                     |
| E                         | 105,9                 | 107,0                      | 99,7                 | 108,2                     |
| F                         | N/A                   | 129,9                      | 93,6                 | 126,4                     |
| G                         | 91,3                  | 126,8                      | 88,1                 | 107,8                     |
| H                         | 97,0                  | 122,8                      | 75,9                 | 95,8                      |
| I                         | 90,3                  | 123,4                      | 98,6                 | 117,5                     |
| J                         | 105,1                 | 109,4                      | 98,3                 | 107,2                     |
| <b>Average</b>            | <b>99,8</b>           | <b>116,9</b>               | <b>94,7</b>          | <b>110,3</b>              |
| <b>Standard deviation</b> | <b>6,7</b>            | <b>9,5</b>                 | <b>7,7</b>           | <b>7,8</b>                |

NOTE N/A means that in the cubic approximation of activation energy versus the degree of conversion equation did not provide a solution.

Differences between  $RTE_A$  or  $TI_A$  and  $TI$ , which is a numerical value remaining after  $TI$  is deducted from  $RTE_A$  or  $TI_A$  (see 7.5), are shown in Table A.9, Table A.10, and Table A.11 for dielectric strength, tensile strength, and impact strength, respectively.