
Resilient floor coverings — Determination of seam strength

Revêtements de sol résilients — Détermination de la résistance de la soudure

STANDARDSISO.COM : Click to view the full PDF of ISO 16906:2015



STANDARDSISO.COM : Click to view the full PDF of ISO 16906:2015



COPYRIGHT PROTECTED DOCUMENT

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

	Page
Foreword	iv
1 Scope	1
2 Terms and definitions	1
3 Principle	1
4 Apparatus	1
5 Sampling and preparation of test pieces	2
5.1 Sampling	2
5.2 Preparation of test pieces	2
6 Conditioning	2
7 Procedure	2
8 Calculation an expression of results	3
9 Test report	3

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 219, *Floor coverings*.

Resilient floor coverings — Determination of seam strength

1 Scope

This International Standard specifies a method for determining the strength of the seams of resilient floor coverings when welded in accordance with the manufacturer's instructions.

2 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

2.1

seam strength

maximum tensile force recorded, for a defined width, when a floor covering is tested under a constant rate of extension

2.2

constant-rate-of-extension (CRE) testing machine

tensile testing machine provided with one clamp which is stationary and another clamp which moves with a constant speed throughout the test, the entire testing system being virtually free from deflection

3 Principle

An increasing tensile force is applied until the seam breaks (see [Figure 1](#); the arrows indicate the direction of the applied tensile forces).




Figure 1 — Principle of test

4 Apparatus

A tensile testing machine, which allows a speed of separation of (100 ± 5) mm/min, and a force recording device shall be used.

5 Sampling and preparation of test pieces

5.1 Sampling


Take a representative sample from the available material.

5.2 Preparation of test pieces

Take two pieces of a sheet floor covering with minimum length of 1 m and minimum width of 300 mm and weld them together in accordance with the manufacturer's instructions. The weld shall be done on the long side of the sample. For tiles, weld two tiles together in accordance with the manufacturer's instructions.

Cut five test pieces with minimum length of 150 mm and width of $(50 \pm 0,5)$ mm at equal distances across the sample, the distance between the outer edge of the sample and the nearest edge of the test piece being at least 100 mm, with the seam centrally located across each test piece (see Figure 2).

Dimensions in millimetres

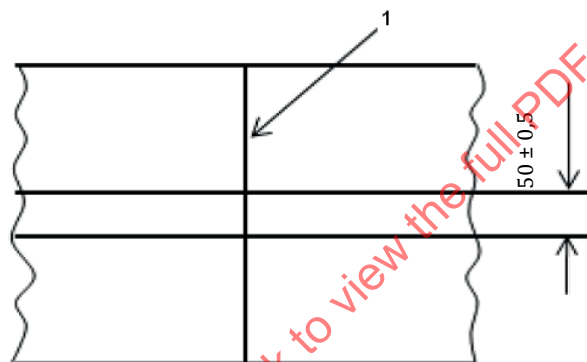

Key

1 seam

Figure 2 — Test piece layout

6 Conditioning

Condition the test pieces at a temperature of (23 ± 2) °C and relative humidity of (50 ± 5) % for a minimum of 24 h.

Maintain these conditions when carrying out the test.

7 Procedure

Place the test piece in the jaws (which are approximately 100 mm apart) of the tensile testing machine so that the seam is at an equal distance from the jaws and tension is applied evenly over the width. Set the machine and its recording device in operation such that the speed of separation is (100 ± 5) mm/min. Record the force at break or the maximum force exerted.

Repeat the test on the remaining test pieces to obtain five values.