

Fifth edition
2010-12-15

AMENDMENT 1
2013-04-01

**Plastics — Determination of flexural
properties**

AMENDMENT 1

Plastiques — Détermination des propriétés en flexion
AMENDEMENT 1



Reference number
ISO 178:2010/Amd.1:2013(E)

© ISO 2013

STANDARDSISO.COM : Click to view the full PDF of ISO 178:2010/Amd 1:2013



COPYRIGHT PROTECTED DOCUMENT

© ISO 2013

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

Amendment 1 to ISO 178:2010 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 2, *Mechanical properties*.

STANDARDSISO.COM : Click to view the full PDF of ISO 178:2010/Amd.1:2013

STANDARDSISO.COM : Click to view the full PDF of ISO 178:2010/Amd 1:2013

Plastics — Determination of flexural properties

AMENDMENT 1

Page iv, Foreword

At the end of the Foreword, add the following paragraph:

The fifth edition specifies measuring tips with an end radius of 50 mm. While this is useful to avoid alignment errors when dimensions on perfectly flat specimens are measured, it has disadvantages with injection-moulded specimens, which constitute the majority of specimens tested according to ISO 178. Injection-moulded specimens are never perfectly rectangular and, especially if made of semi-crystalline materials, also exhibit sink marks. Measuring tips with rounded ends tend to determine the minimum thickness, leading to artificially high values of stress and flexural modulus. Furthermore, the specified tips with round ends are not readily available and in the same instant rendered commonly used flat-ended tips obsolete, causing disagreement in audit processes. This amendment rectifies this error and introduces a specification for measuring the dimensions of the test specimens that allows different instruments to be used, provided they measure not the extreme (maximum or minimum) dimensions, but rather an average value.

Page 7, 5.5.1

Replace the two subclauses (5.5.1.1 and 5.5.1.2) with the following:

Use micrometers with an accuracy of $\pm 0,01$ mm.


Use measuring tips that allow the determination of the thickness centrally within the measuring range and the width at half height, as indicated in Figure 5.

Different geometry of the contact faces of the measuring tips, i.e. spherical, circular, rectangular or sharp edges are acceptable. Spherical tip faces shall have a radius of ≥ 50 mm. Flat tips are recommended. The face diameter of circular measuring tips shall be between 1,5 mm and 6,4 mm. Rectangular faces of measuring tips shall have a long side of 4 mm to 6,4 mm in length.

It is recommended to use a configuration that allows the determination of the width and the thickness with the same instrument.

Page 11, 8.1

Replace Figure 5 with the following.

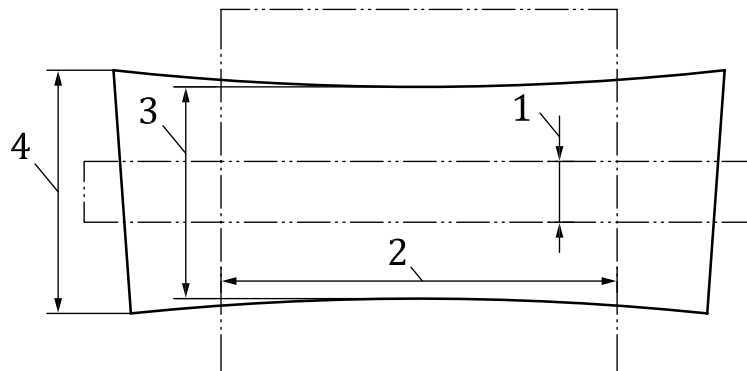

Key

- 1 measuring range for width determination $\pm 0,5$ mm
- 2 measuring range for thickness determination $\pm 3,25$ mm
- 3 minimum thickness $h_{\min}$
- 4 maximum thickness $h_{\max}$

Pages 10 to 11, 8.1

Replace with the following:

8.1 Measure the width and the thickness of the test specimen within the measurement ranges indicated in Figure 5, to the nearest 0,1 mm for the width and to the nearest 0,01 mm for the thickness. Calculate the mean values of the thickness, h , and the width, b , for the set of test specimens.

Avoid measuring the thickness at the edge of the specimen and directly in the centre (see Note 1). With rectangular or sharp tip faces the long side of the tip shall be parallel to the width direction when measuring thickness, and parallel to the length direction when measuring width.

NOTE 1 This excludes the maximum and minimum thickness, which for injection-moulded test specimens usually is found at the edge and in the centre, respectively. Injection-moulded test specimens prepared according ISO 294-1, generally have thickness differences due to sink marks of $\Delta h = h_{\max} - h_{\min} \leq 0,1$ mm (see Figure 5).

Discard any specimen(s) with a thickness exceeding the tolerance of ± 2 % of the mean value and replace it with another specimen chosen at random.

NOTE 2 For the purposes of this International Standard, the test specimen dimensions used for calculating flexural properties are measured at room temperature only. For the measurement of properties at other temperatures, therefore, the effects of thermal expansion are not taken into account.