
**Optics and photonics — Optical
materials and components — The
powder test method for the water
resistance of optical glass**

*Optique et photonique — Matériaux et composants optiques —
Méthode d'essai sur poudre pour déterminer la résistance à l'eau des
verres optiques*

STANDARDSISO.COM : Click to view the full PDF of ISO 21575:2018



STANDARDSISO.COM : Click to view the full PDF of ISO 21575:2018



COPYRIGHT PROTECTED DOCUMENT

© ISO 2018

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principles	1
5 Reagents	1
5.1 Water	1
5.2 Alcohol	1
6 Apparatus	2
6.1 Sieve	2
6.2 Basket for corrosion test	2
6.3 Apparatus for corrosion test	2
6.4 Heating bath	3
7 Preparation of the specimen of the glass to be tested	3
8 Procedure	3
9 Classification and designation	4
10 Test report	4

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 172, *Optics and photonics*, Subcommittee SC 3, *Optical materials and components*.

Introduction

There are two commonly used methods for test of the chemical resistance of optical glass: The powder method and the surface method. The powder method has simpler procedures for the sample preparation since it does not require a homogeneously polished surface.

STANDARDSISO.COM : Click to view the full PDF of ISO 21575:2018

STANDARDSISO.COM : Click to view the full PDF of ISO 21575:2018

Optics and photonics — Optical materials and components — The powder test method for the water resistance of optical glass

1 Scope

This document specifies the general procedures of the powder test method for the water resistance of optical glass.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3310-1, *Test sieves — Technical requirements and testing — Part 1: Test sieves of metal wire cloth*

ISO 3696, *Water for analytical laboratory use — Specification and test methods*

ISO 4797, *Laboratory glassware — Boiling flasks with conical ground joints*

ISO 4799, *Laboratory glassware — Condensers*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

4 Principles

The glass is ground into particles of diameter within the range of between 425 µm to 600 µm. A powder sample equivalent to the specific gravity in grams is placed in a platinum basket. The basket is placed in a flask of silica glass and boiled for 60 min. The degree of water resistance is determined by measuring the weight loss (in percent), and is denoted by a class number ranging from 1 to 6, as given in [Table 1](#).

5 Reagents

5.1 Water

The purity of the water used shall comply with the grade 2 requirements specified in ISO 3696.

5.2 Alcohol

Ethanol, methanol and 2-propanol can be used, but water-containing alcohol cannot be used.


6 Apparatus

6.1 Sieve

The sieve shall refer to the test sieve specified in ISO 3310-1.

6.2 Basket for corrosion test

The mesh basket for the corrosion test shall be fabricated with a specific opening size between 230 μm and 260 μm using platinum wire with a diameter of about 76 μm . A drawing of the apparatus including dimensions is shown in [Figure 1](#).

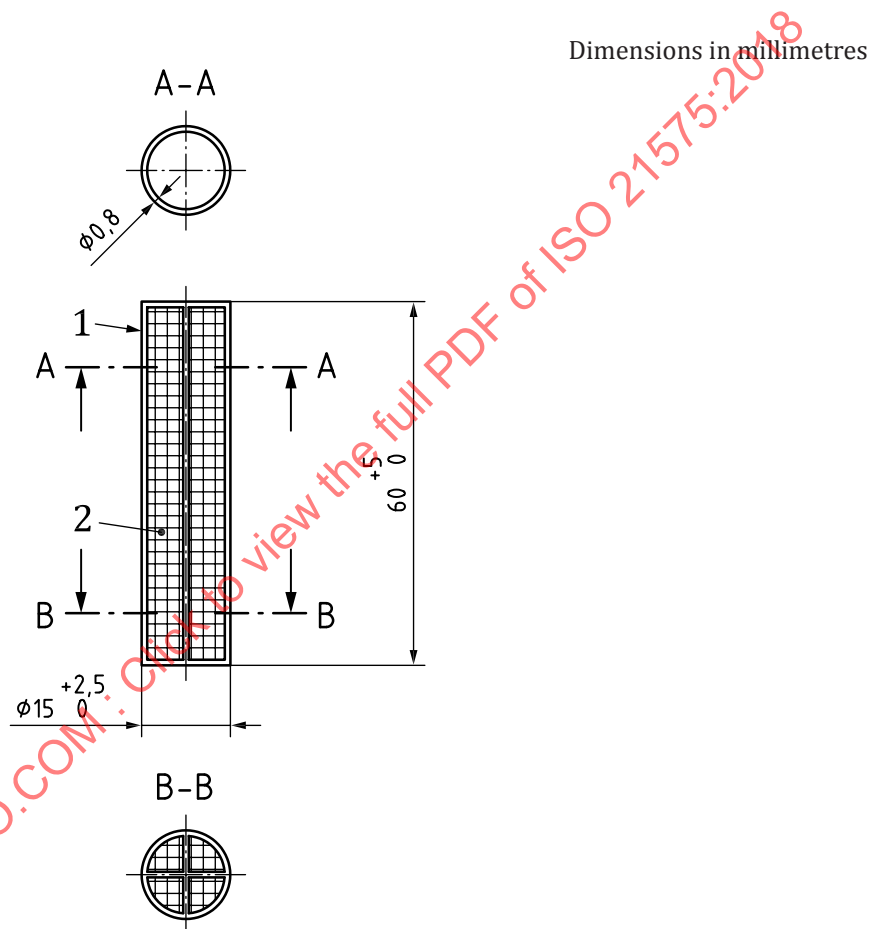

Key

- 1 platinum frame
- 2 platinum test sieve
- A-A cross-section view
- B-B cross-section view

Figure 1 — Basket

6.3 Apparatus for corrosion test

The configuration and dimensions of the apparatus are shown in [Figure 2](#). However, the dimensions of [Figure 2](#) are merely an example, the shape shall conform to ISO 4797 and ISO 4799. The dimension and shape may be different, as long as the nominal capacity of a spherical-shaped flask is 100 ml. The apparatus shall employ a flask fitted to a condenser made of either fused silica glass or fused borosilicate glass as specified in ISO 4797 and ISO 4799.

Dimensions in millimetres

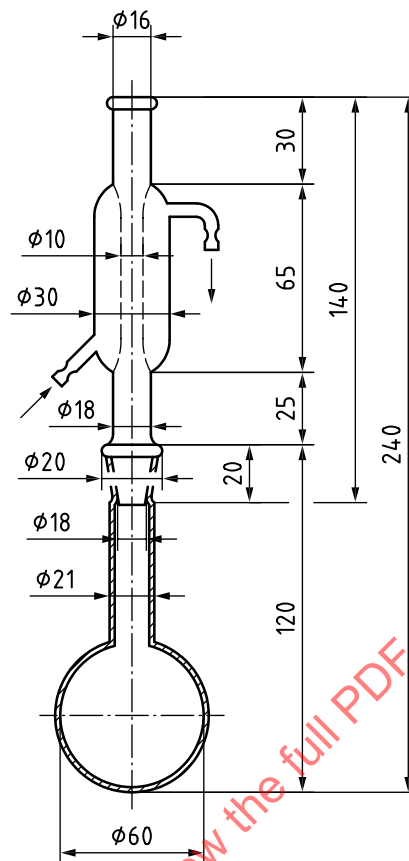


Figure 2 — Apparatus for corrosion

6.4 Heating bath

The apparatus shall employ a water bath in which the spherical part of the flask is completely immersed in hot water and shall be held at temperatures over 98 °C measured at 20 mm ± 10 mm location from the bottom of the flask.

7 Preparation of the specimen of the glass to be tested

Prepare the specimen as follows:

- Crush the glass and pass through a screen with a 710 µm sieve and sieve the selected particles again with a 600 µm sieve. Then reselect the glass particles with a 425 µm test sieve to collect particles of sizes between 425 µm and 600 µm.
- Place the powdered glass weighing about three times its specific gravity in grams into a 50 ml beaker. To remove dust powder from the particles, pour 15 ml of alcohol for decantation.
- After repeating operation b) five times, dry the specimen at the temperature between 120 °C and 130 °C in an oven for one hour and then store it in a desiccator with silica gel.

8 Procedure

Use the following procedure:

- Place a specimen weighing as much as its specific gravity in grams in the basket. Shake the basket gently and then place it in a weighing bottle with a lid and carefully weigh it.