

---

---

**Plastics — Methods of exposure to  
laboratory light sources —**

**Part 2:  
Xenon-arc lamps**

**AMENDMENT 1: Classification of daylight  
filters**

*Plastiques — Méthodes d'exposition à des sources lumineuses de  
laboratoire —*

*Partie 2: Lampes à arc au xénon*

*AMENDEMENT 1: Classification des filtres de la lumière du jour*





**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 6, *Ageing, chemical and environmental resistance*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 249, *Plastics*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

A list of all parts in the ISO 4892 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

STANDARDSISO.COM : Click to view the full PDF of ISO 4892-2:2013/Amd 1:2021

# Plastics — Methods of exposure to laboratory light sources —

## Part 2: Xenon-arc lamps

### AMENDMENT 1: Classification of daylight filters

#### 4.1.2

Add a new paragraph as follows:

Annex C differentiates between two different types of daylight filters: Type I and Type II. Both types fall under the relative spectral irradiance requirements of xenon-arc lamps with daylight filters given in Table 1.

#### *Annex C*

Add the following new Annex C:

## **Annex C** (informative)

### **Classification of daylight filters**

#### **C.1 Motivation**

The relative spectral irradiance requirements for xenon-arc lamps with daylight filters allow a broad range of different optical filter systems with different UV cut-on wavelengths. However, most of the available filters can be grouped in two main spectral specifications, both fulfilling the requirements of Method A. By giving additional information on the type of the used daylight filter, a much better reproducibility and comparability of results can be achieved. If the information on the type of filter is available, it is strongly recommended to add this information in the test report.

When performing Method A, any optical filters may be used that fulfil the requirements in Table 1. This is true even if the filters do not fulfil the Type I or Type II specifications (see Table C.1), or if such information is not available.

**NOTE** Reproducible results are more likely achieved, if setups (instrument and optical system) with Type I filter systems are compared with other Type I setups, and Type II setups are only compared with other Type II setups.

#### **C.2 Type I and Type II specifications**

The spectral irradiance of xenon-arc lamps with daylight filters according to Table 1 is redefined in 20 nm increments and split into two types. In Table C.1, the original values are referred to as general daylight. Type I defines optical filter systems with a higher UV cut-on compared to Type II. Figure C.1 shows examples of Type I and Type II filter systems in the spectral range from 280 nm to 400 nm together with a reference spectrum according to ISO/TR 17801. Type I and Type II optical systems cover the full range of the spectral irradiance requirements in Table 1.

**NOTE 1** The UV cut-on wavelength of Type I filters is closer to the cut-on of the natural global solar radiation. If Type II filters are used, faster material degradation is typically observed.

**NOTE 2** ISO/TR 17801 contains a recalculated reference spectrum based on CIE No. 85:1989, Table 4. The spectrum is in increments of a half nanometer in the UV region, and in increments of one nanometer for longer wavelengths.

**Table C.1 — Relative spectral irradiance of xenon-arc lamps with daylight filters (method A)<sup>a</sup>**

| Spectral pass-band wavelength<br>$\lambda$<br>nm | General <sup>b</sup> |       | Type I <sup>c</sup> |       | Type II <sup>d</sup> |       | CIE No. 85:1989,<br>Table 4 <sup>e</sup><br>% |
|--------------------------------------------------|----------------------|-------|---------------------|-------|----------------------|-------|-----------------------------------------------|
|                                                  | Min %                | Max % | Min %               | Max % | Min %                | Max % |                                               |
| $\lambda < 300$                                  | 2,60                 | 8,05  | 0,00                | 0,20  | 0,20                 | 1,05  | 5,40                                          |
| $300 \leq \lambda \leq 320$                      |                      |       | 2,60                | 6,00  | 3,50                 | 7,00  |                                               |
| $320 < \lambda \leq 340$                         | 28,2                 | 39,8  | 10,0                | 17,0  | 10,0                 | 17,0  | 38,2                                          |
| $340 < \lambda \leq 360$                         |                      |       | 18,3                | 23,2  | 18,3                 | 23,2  |                                               |
| $360 < \lambda \leq 380$                         | 54,2                 | 67,5  | 25,0                | 30,5  | 25,0                 | 30,5  | 56,4                                          |
| $380 < \lambda \leq 400$                         |                      |       | 29,2                | 37,0  | 29,2                 | 37,0  |                                               |


<sup>a</sup> This table gives the irradiance in the given passband, expressed as a percentage of the total irradiance between 290 nm and 400 nm. To determine whether a specific filter or set of filters for a xenon-arc lamp meets the requirements of this Table, the spectral irradiance must be measured from 250 nm to 400 nm. The total irradiance in each wavelength passband is then summed and divided by the total irradiance from 290 nm to 400 nm.

<sup>b</sup> Values of the spectral passband of xenon-arc lamps with daylight filters according to Table 1.

<sup>c</sup> Daylight filter systems as described in ASTM D7869 fall under the definition of Type I Daylight filters.

<sup>d</sup> Daylight filter systems as described in SAE J2527 fall under the definition of Type II Daylight filters.

<sup>e</sup> Details of the solar reference spectrum can be found in Table 1.

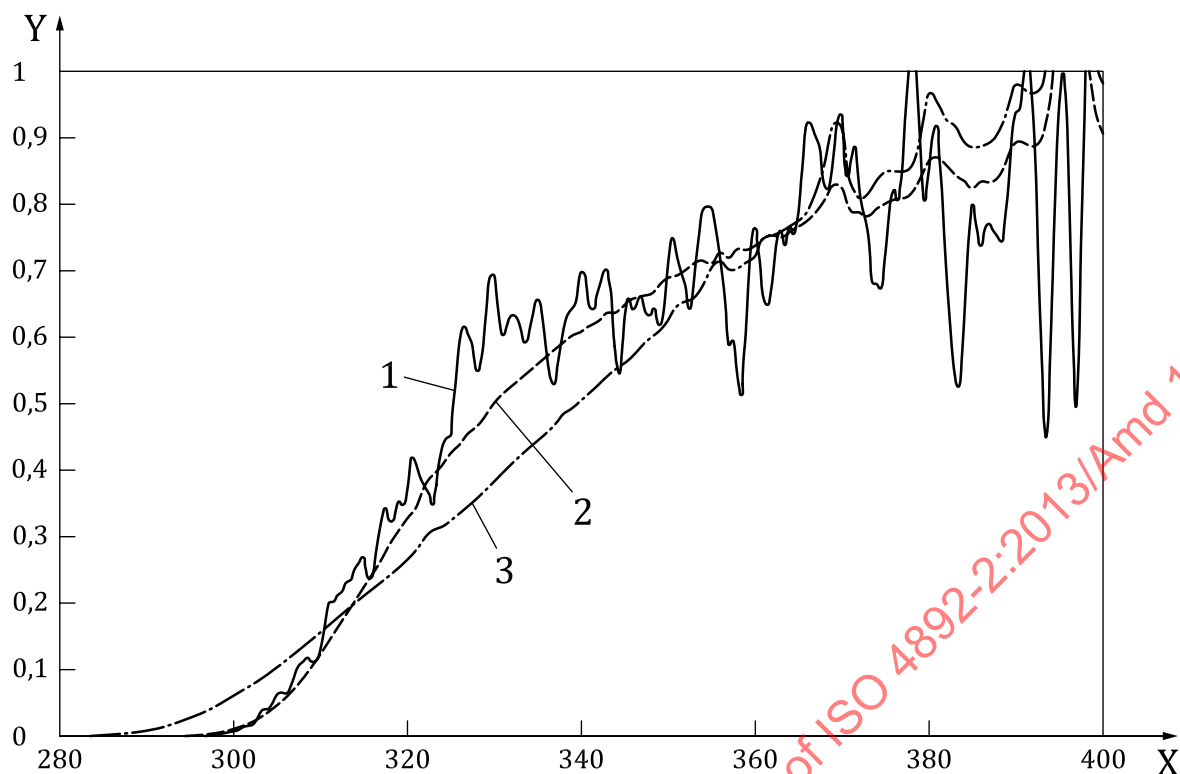

#### Key

X wavelength  $\lambda$  [nm]

Y spectral irradiance [W/(m<sup>2</sup> nm)]

1 ISO/TR 17801 (CIE 85:1989, Table 4)

2 Type I

3 Type II

NOTE The spectral irradiance distribution is normalized to 60 W/m<sup>2</sup> in the passband from 300 nm to 400 nm.

**Figure C.1 — Representative spectral irradiance distribution of xenon-arc lamps with Type I and Type II daylight filters and the reference solar spectrum according to ISO/TR 17801**

#### Bibliography

Add the following references:

[6] ISO/TR 17801, *Plastics — Standard table for reference global solar spectral irradiance at sea level - Horizontal, relative air mass 1*

[7] ASTM D7869, *Standard Practice for Xenon Arc Exposure Test with Enhanced Light and Water Exposure for Transportation Coatings*

[8] SAE J2527, *Performance Based Standard for Accelerated Exposure of Automotive Exterior Materials Using a Controlled Irradiance Xenon-Arc Apparatus*