
**Welding — Fusion-welded joints in
steel, nickel, titanium and their alloys
(beam welding excluded) — Quality
levels for imperfections**

*Soudage — Assemblages en acier, nickel, titane et leurs alliages
soudés par fusion (soudage par faisceau exclu) — Niveaux de qualité
par rapport aux défauts*





COPYRIGHT PROTECTED DOCUMENT

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents		Page
Foreword		iv
Introduction		v
1	Scope	1
2	Normative references	1
3	Terms and definitions	2
4	Symbols	3
5	Assessment of imperfections	4
Annex A (informative) Examples of determination of percentage (%) porosity		21
Annex B (informative) Additional criteria for welds in steel subject to fatigue		23
Bibliography		26

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 10, *Quality management in the field of welding*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 121, *Welding and allied processes*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This fourth edition cancels and replaces the third edition (ISO 5817:2014), which has been technically revised.

The main changes are as follows:

- editorial updates;
- actual throat thickness a_A , used in [Table 1](#), nos 1.3, 1.4, 1.16 and 3.2;
- figures for [Table 1](#), nos 1.4, 1.5, 1.6, 1.11, 1.14, 1.16, 1.19, 2.12, 2.13 and 4.1 changed or added;
- [Table 1](#), no. 4.1: exclusion of several imperfections and change of acceptance criteria;
- Former Annex B deleted.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html. Official interpretations of ISO/TC 44 documents, where they exist, are available from this page: <https://committee.iso.org/sites/tc44/home/interpretation.html>.

Introduction

This document is intended to be used as a reference in the drafting of application codes and/or other application standards. It contains a simplified selection of fusion weld imperfections based on the designations given in ISO 6520-1.

Some of the imperfections described in ISO 6520-1 have been used directly and some have been grouped together. The basic numerical referencing system from ISO 6520-1 has been used.

The purpose of this document is to specify dimensions of typical imperfections which might be expected in normal fabrication. It may be used within a quality system for the production of welded joints. It provides three sets of dimensional values from which a selection can be made for a particular application. The quality level necessary in each case should be specified by the application standard or the responsible designer in conjunction with the manufacturer, user and/or other parties concerned. The quality level shall be prescribed before the start of production, preferably at the enquiry or order stage. For special purposes, additional details may be prescribed. If the welds will be subsequently coated with a protective coating, lining or paint, the welds might require more thorough post weld treatment or surface finishing to achieve the requirements in ISO 8501-3.

The quality levels given in this document provide basic reference data and are not specifically related to any particular application. They refer to types of welded joint in fabrication and not to the complete product or component itself. It is possible, therefore, that different quality levels are applied to individual welded joints in the same product or component.

The main part of the document takes no account for fitness or design for purpose. [Annex B](#) gives a possibility to address design for purpose for fatigue applications.

It would normally be expected that for a particular welded joint the dimensional limits for imperfections can all be covered by specifying one quality level. In some cases, it can be necessary to specify different quality levels for different imperfections in the same welded joint. The choice of quality level for any application should take account of design considerations, subsequent processing (e.g. surfacing), mode of stressing (e.g. static, dynamic), service conditions (e.g. temperature, environment) and consequences of failure. Economic factors are also important and should include not only the cost of welding but also of inspection, testing and repair.

Although this document includes types of imperfection relevant to the fusion welding processes listed in [Clause 1](#), only those which are applicable to the process and application in question need to be considered.

Imperfections are quoted in terms of their actual dimensions, and their detection and evaluation can require the use of one or more methods of non-destructive testing. The detection and sizing of imperfections is dependent on the testing methods and the extent of testing specified in the application standard or contract.

This document does not address the methods used for the detection of imperfections. However, ISO 17635 contains a correlation between the quality level and acceptance level for different NDT methods.

This document is directly applicable to visual testing of welds and does not include details of recommended methods of detection or sizing by non-destructive means. It should be considered that there are difficulties in using these limits to establish appropriate criteria applicable to non-destructive testing methods, such as ultrasonic testing (UT), radiographic testing (RT), eddy current testing (ET), penetrant testing (PT) and magnetic particle testing (MT) and that these will possibly need to be supplemented by requirements for inspection, examining and testing.

The values given for imperfections are for welds produced using normal welding practice. Requirements for smaller (more stringent) values as stated in quality level B may include additional manufacturing processes, e.g. grinding, TIG dressing.

[Annex B](#) gives additional requirements for welds subject to fatigue.

For Standards Development only: No reproduction and circulation
WG on Gas Cylinders
STANDARDSISO.COM · Click to view the full PDF of ISO 5817 WG:2023

Welding — Fusion-welded joints in steel, nickel, titanium and their alloys (beam welding excluded) — Quality levels for imperfections

1 Scope

This document specifies quality levels of imperfections in fusion-welded joints (except for beam welding) in all types of steel, nickel, titanium and their alloys. It applies to material thickness $\geq 0,5$ mm. It covers fully penetrated butt welds and all fillet welds. Its principles can also be applied to partial-penetration butt welds.

Quality levels for beam-welded joints in steel are presented in ISO 13919-1.

Three quality levels are given in order to permit application to a wide range of welded fabrication. They are designated by symbols B, C and D. Quality level B corresponds to the highest requirement on the finished weld.

Several types of loads are considered, e.g. static load, thermal load, corrosion load, pressure load. Additional guidance on fatigue loads is given in [Annex B](#).

The quality levels refer to production and good workmanship.

This document is applicable to:

- a) non-alloy and alloy steels;
- b) nickel and nickel alloys;
- c) titanium and titanium alloys;
- d) manual, mechanized and automatic welding;
- e) all welding positions;
- f) all types of welds, e.g. butt welds, fillet welds and branch connections;
- g) the following welding processes and their sub-processes, as defined in ISO 4063:
 - 11 metal arc welding without gas protection;
 - 12 submerged arc welding;
 - 13 gas-shielded metal arc welding;
 - 14 gas-shielded arc welding with non-consumable tungsten electrode;
 - 15 plasma arc welding;
 - 31 oxyfuel gas welding (for steel only).

Metallurgical aspects, such as grain size and hardness, are not covered by this document.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

3 Terms and definitions

For the purposes of this document, the terms and definitions given in the ISO 25901 series and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1 quality level

description of the quality of a weld on the basis of type, size and amount of selected imperfections

3.2 short imperfection

<welds 100 mm long or longer> imperfection whose total length is not greater than 25 mm in the 100 mm of the weld which contains the greatest number of imperfections

3.3 short imperfection

< welds less than 100 mm long> imperfection whose total length is not greater than 25 % of the length of the weld


3.4 systematic imperfection

imperfection that is repeatedly distributed in the weld over the weld length to be tested, the size of a single imperfection being within the specified limits

3.5 projected area

area where imperfections distributed along the volume of the weld under consideration are imaged two-dimensionally

Note 1 to entry: In contrast to the cross-sectional area, the occurrence of imperfections is dependent on the weld thickness when exposed radiographically (see [Figure 1](#)).

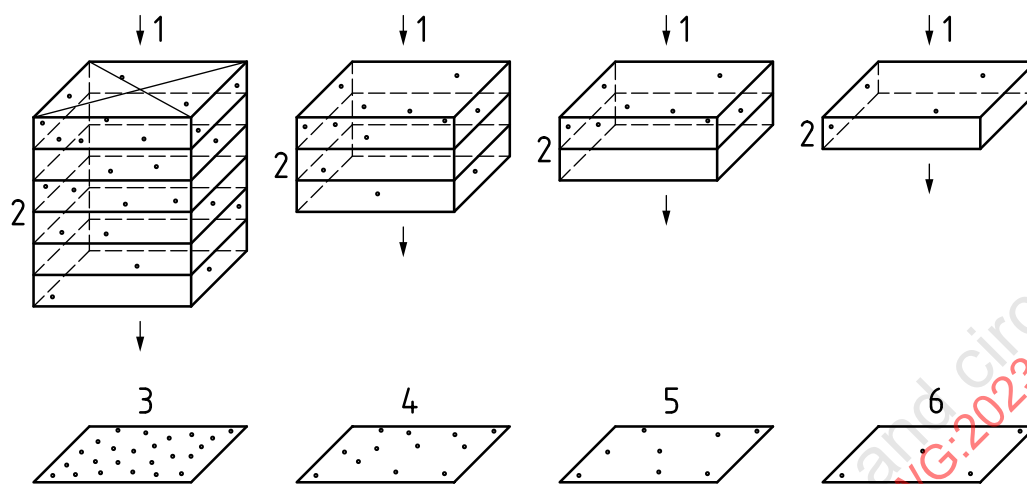**Key**

- | | | | | | |
|---|----------------------------|---|---------------------|---|-------------------|
| 1 | direction of rays | 3 | sixfold thickness | 5 | twofold thickness |
| 2 | four pores per volume unit | 4 | threefold thickness | 6 | onefold thickness |

Figure 1 — Radiographic films of specimens with identical occurrence of pores per volume unit

3.6**cross-sectional area**

area to be considered after fracture or sectioning

3.7**smooth transition**

even surface with no irregularities or sharpness at the transition between the weld bead and the parent material and/or the adjacent welding bead(s)

3.8**fatigue class****FAT_x**

classification reference to S-N curve

Note 1 to entry: x is the stress range in MPa at $2 \cdot 10^6$ cycles.

Note 2 to entry: Fatigue properties are described by S-N curves (stress-number of cycle-curves).

Note 3 to entry: See [Annex B](#).

4 Symbols

- | | |
|----------------------|---|
| <i>a</i> | nominal throat thickness of the fillet weld (see also ISO 2553) |
| <i>a_A</i> | actual throat thickness (throat thickness of the finalized weld) (see ISO/TR 25901-1) |
| <i>A</i> | area surrounding the gas pores |
| <i>b</i> | width of weld reinforcement |
| <i>d</i> | diameter of gas pore |
| <i>d_A</i> | diameter of area surrounding the gas pores |
| <i>h</i> | height or width of imperfection |

i	penetration in fillet welds
l	length of imperfection in longitudinal direction of the weld
l_p	length of projected or cross-sectional area
r	radius of weld toe
s	nominal butt weld thickness
t	wall or plate thickness (nominal size)
w_p	width of the weld or width or height of the cross-sectional area
z	leg length of a fillet weld (see also ISO 2553)
α	angle of weld toe
β	angle of angular misalignment

5 Assessment of imperfections

Limits for imperfections in accordance with ISO 6520-1 are given in [Table 1](#).

If, for the detection of imperfections, macro-examination is used, only those imperfections shall be considered which can be detected with a maximum of tenfold magnification. Excluded from this are micro lack of fusion (see [Table 1](#), 1.5) and microcracks (see [Table 1](#), 2.2).

Systematic imperfections are only permitted in quality level D, provided the other requirements of [Table 1](#) are fulfilled.

A welded joint should usually be assessed separately for each individual type of imperfection (see [Table 1](#), 1.1 to 3.2).

Different types of imperfection occurring at any cross-section of the joint need special consideration (see multiple imperfections in [Table 1](#), 4.1).

The limits for multiple imperfections (see [Table 1](#)) are only applicable for cases where the requirements for a single imperfection are not exceeded.

Any two adjacent imperfections separated by a distance smaller than the major dimension of the smaller imperfection shall be considered as a single imperfection.

Table 1 — Limits for imperfections

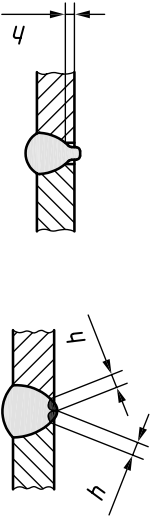
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels			
					D	C	B	B
1 Surface imperfections								
1.1.1	100	Crack		≥ 0,5	Not permitted	Not permitted	Not permitted	Not permitted
1.1.2	104	Crater crack		≥ 0,5	Not permitted	Not permitted	Not permitted	Not permitted
1.1.3	2017	Surface pore	On the weld face or the weld root Maximum dimension of a single pore	0,5 to 3	Butt welds $d \leq 0,3 s$ fillet welds $d \leq 0,3 a_A$	Not permitted	Not permitted	Not permitted
				> 3	Butt welds $d \leq 0,3 s$, but max. 3 mm fillet welds $d \leq 0,3 a_A$, but max. 3 mm	butt welds $d \leq 0,2 s$, but max. 2 mm fillet welds $d \leq 0,2 a_A$, but max. 2 mm	Not permitted	Not permitted
1.1.4	2025	End crater pipe	— butt welds — fillet welds	0,5 to 3	Butt welds $h \leq 0,2 s$ $d \leq 0,3 s$ fillet welds $h \leq 0,2 a_A$, $d \leq 0,3 a_A$	Not permitted	Not permitted	Not permitted
				> 3	Butt welds $h \leq 0,2 s$, but max. 2 mm $d \leq 0,3 s$, but max. 3 mm fillet welds $h \leq 0,2 a_A$, but max. 2 mm $d \leq 0,3 a_A$, but max. 3 mm	Butt welds $h \leq 0,1 s$, but max. 1 mm $d \leq 0,2 s$, but max. 2 mm fillet welds $h \leq 0,1 a_A$, but max. 1 mm $d \leq 0,2 a_A$, but max. 2 mm	Not permitted	Not permitted
1.1.5	401	Lack of fusion (incomplete fusion)		≥ 0,5	Not permitted	Not permitted	Not permitted	Not permitted
	4014	Micro lack of fusion	Only detectable by micro examination ($\geq 50 \times$)	≥ 0,5	Permitted	Permitted	Permitted	Not permitted

Table 1 (continued)

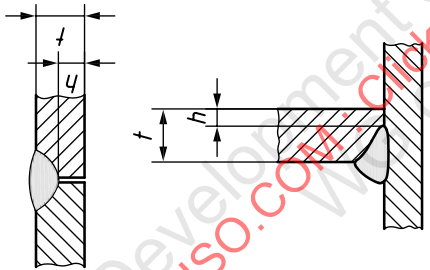
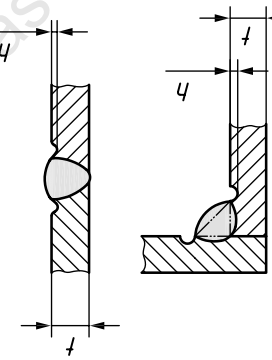
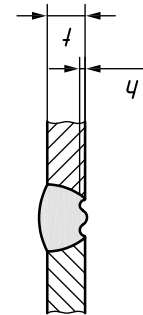
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
1.6	4021	Incomplete root penetration	Only for single side butt welds (full penetration) 	$\geq 0,5$	Short imperfections: $h \leq 0,2 t$ but max. 2 mm	Not permitted	Not permitted
1.7	5011 5012	Continuous undercut	Smooth transition is required. This is not regarded as a systematic imperfection. 	0,5 to 3	Short imperfections: $h \leq 0,2 t$	Short imperfections: $h \leq 0,1 t$	Not permitted
		Intermittent undercut (short imperfection)		> 3	$h \leq 0,2 t$, but max. 1 mm	$h \leq 0,1 t$, but max. 0,5 mm	$h \leq 0,05 t$, but max. 0,5 mm
1.8	5013	Shrinkage grooves	Smooth transition is required. 	0,5 to 3	Short imperfections: $h \leq 0,1 t$, but max. 0,2 mm	Short imperfections: $h \leq 0,1 t$	Not permitted
				> 3	Short imperfections: $h \leq 0,2 t$, but max. 2 mm	Short imperfections: $h \leq 0,1 t$, but max. 1 mm	Short imperfections: $h \leq 0,05 t$, but max. 0,5 mm

Table 1 (continued)



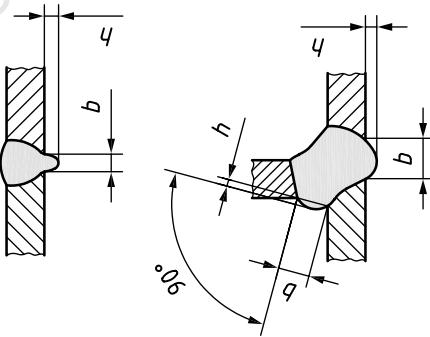
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
1.9	502	Excess weld metal (butt weld)	Smooth transition is required between the capping run(s) and the plate surface and/or the adjacent welding bead(s) 	≥ 0,5	$h \leq 0,25 b + 1 \text{ mm}$, but max. 10 mm	$h \leq 0,15 b + 1 \text{ mm}$, but max. 7 mm	$h \leq 0,1 b + 1 \text{ mm}$, but max. 5 mm
1.10	503	Excessive convexity (fillet weld)	Smooth transition is required between the cap of the weld and the plate surface and/or the adjacent welding bead(s) 	≥ 0,5	$h \leq 0,25 b + 1 \text{ mm}$, but max. 5 mm	$h \leq 0,15 b + 1 \text{ mm}$, but max. 4 mm	$h \leq 0,1 b + 1 \text{ mm}$, but max. 3 mm
1.11	504	Excessive penetration		0,5 to 3 > 3	$h \leq 0,6 b + 1 \text{ mm}$ $h \leq 1,0 b + 1 \text{ mm}$, but max. 5 mm	$h \leq 0,3 b + 1 \text{ mm}$ $h \leq 0,45 b + 1 \text{ mm}$, but max. 4 mm	$h \leq 0,1 b + 1 \text{ mm}$ $h \leq 0,2 b + 1 \text{ mm}$, but max. 3 mm

Table 1 (continued)




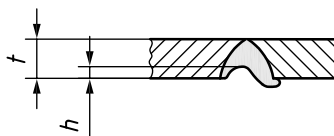
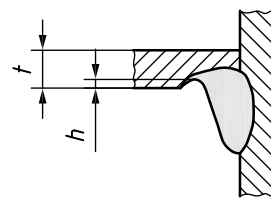
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
1.12	505	Incorrect weld toe	— butt welds  Not applicable for the root — fillet welds  $\alpha_1 \geq \alpha$ and $\alpha_2 \geq \alpha$ 	$\geq 0,5$ $\geq 0,5$ $\geq 0,5$	$\alpha \geq 90^\circ$ $\alpha \geq 100^\circ$ $h \leq 0,2 b$	$\alpha \geq 110^\circ$ $\alpha \geq 110^\circ$ Not permitted	$\alpha \geq 150^\circ$ $\alpha \geq 110^\circ$ Not permitted
1.13	506	Overlap		$\geq 0,5$			Not permitted
1.14	509	Sagging	Smooth transition is required  	0,5 to 3 > 3	Short imperfections: $h \leq 0,25 t$ Short imperfections: $h \leq 0,25 t$, but max. 2 mm	Short imperfections: $h \leq 0,1 t$ Short imperfections: $h \leq 0,1 t$, but max. 1 mm	Not permitted Short imperfections: $h \leq 0,05 t$, but max. 0,5 mm

Table 1 (continued)


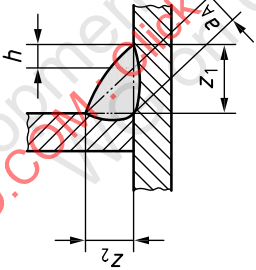
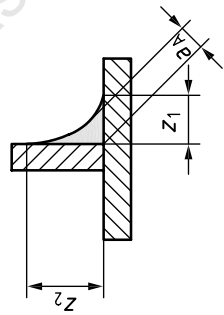
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
	511	Incompletely filled groove					
1.15	510	Burn through	—	≥ 0,5	Not permitted	Not permitted	Not permitted
1.16	512	Excessive asymmetry of fillet weld (excessive unequal leg length)	In cases where an asymmetric fillet weld has not been prescribed.   $h = z_1 - z_2$	≥ 0,5	Not permitted $h \leq 0,2 a_A + 2 \text{ mm}$	Not permitted $h \leq 0,15 a_A + 2 \text{ mm}$	Not permitted $h \leq 0,15 a_A + 1,5 \text{ mm}$

Table 1 (continued)

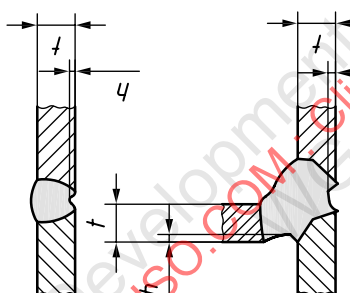

No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
1.17	515	Root concavity	Smooth transition is required. 	0,5 to 3	$h \leq 0,1 t + 0,2 \text{ mm}$	Short imperfections: $h \leq 0,1 t$	Not permitted
				> 3	Short imperfections: $h \leq 0,2 t$, but max. 2 mm	Short imperfections: $h \leq 0,1 t$, but max. 1 mm	Short imperfections: $h \leq 0,05 t$, but max. 0,5 mm
1.18	516	Root porosity	Spongy formation at the root of a weld due to bubbling of the weld metal at the moment of solidification (e.g. lack of gas backing)	$\geq 0,5$	Acceptance depends on application, e.g. material, corrosion protection	Not permitted	Not permitted
1.19	517	Poor restart		$\geq 0,5$	Permitted The limit depends on the type of imperfection which occurred due to the restart	Not permitted	Not permitted

Table 1 (continued)

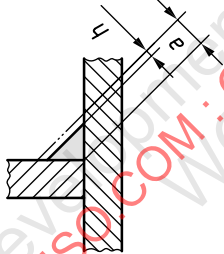
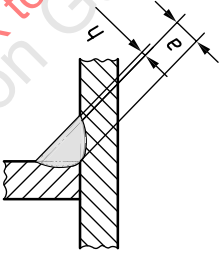
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
1.20	5213	Insufficient throat thickness	Not applicable to processes with proof of greater depth of penetration 	0,5 to 3 > 3	Short imperfections: $h \leq 0,1 a + 0,2$ mm Short imperfections: $h \leq 0,1 a + 0,2$ mm but max. 2 mm	Short imperfections: $h \leq 0,2$ mm Short imperfections: $h \leq 0,1 a + 0,3$ mm, but max. 1 mm	Not permitted Not permitted
1.21	5214	Excessive throat thickness	The actual throat thickness of the fillet weld is too large. 	$\geq 0,5$	Permitted	$h \leq 0,2 a + 1$ mm, but max. 4 mm	$h \leq 0,15 a + 1$ mm, but max. 3 mm
1.22	601	Stray arc	—	$\geq 0,5$	Permitted, if the properties of the parent metal are not affected	Not permitted	Not permitted
1.23	602	Spatter	—	$\geq 0,5$	Acceptance depends on application, e.g. material, corrosion protection	Acceptance depends on application, e.g. material, corrosion protection	Acceptance depends on application, e.g. material, corrosion protection
1.24	610	Temper colours (visible oxide film)	—	$\geq 0,5$	Acceptance depends on application, e.g. material, corrosion protection	Acceptance depends on application, e.g. material, corrosion protection	Acceptance depends on application, e.g. material, corrosion protection
2 Internal imperfections							
2.1	100	Crack	All types of cracks except microcracks and crater cracks	$\geq 0,5$	Not permitted	Not permitted	Not permitted

Table 1 (continued)

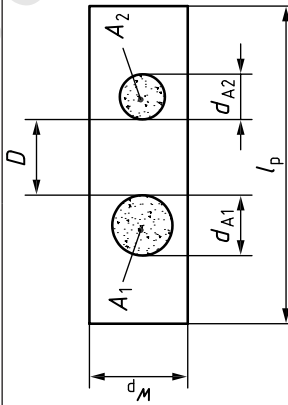
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
2.2	1001	Microcrack	A crack usually only visible under the microscope ($\geq 50\times$)	$\geq 0,5$	Permitted	Acceptance depends on type of parent metal with particular reference to crack sensitivity	Acceptance depends on type of parent metal with particular reference to crack sensitivity
2.3	2011 2012	Gas pore Uniformly distributed porosity	The following conditions and limits for imperfections shall be fulfilled. See also Annex A for information. a1) Maximum dimension of the area of the imperfections (inclusive of systematic imperfection) related to the projected area. The porosity in the project area depends on the numbers of layers (volume of the weld). a2) Maximum dimension of the cross-sectional area of the imperfections (inclusive of systematic imperfection) related to the fracture area (only applicable to test pieces: production test, welder or procedure qualification tests) b) Maximum dimension for a single pore for — butt welds — fillet welds	$\geq 0,5$	For single layer: $\leq 2,5\%$ For multi-layer: $\leq 5\%$ $\leq 2,5\%$	For single layer: $\leq 1,5\%$ For multi-layer: $\leq 3\%$ $\leq 1,5\%$	For single layer: $\leq 1\%$ For multi-layer: $\leq 2\%$ $\leq 1\%$
				$\geq 0,5$	$d \leq 0,4 s$, but max. 5 mm $d \leq 0,4 a_A$, but max. 5 mm	$d \leq 0,3 s$, but max. 4 mm $d \leq 0,3 a_A$, but max. 4 mm	$d \leq 0,2 s$, but max. 3 mm $d \leq 0,2 a_A$, but max. 3 mm
				$\geq 0,5$	$d_A \leq 25$ mm or $d_{A, \max} \leq w_p$	$d_A \leq 20$ mm or $d_{A, \max} \leq w_p$	$d_A \leq 15$ mm or $d_{A, \max} \leq w_p/2$
2.4	2013	Clustered (localized) porosity		$\geq 0,5$			

Table 1 (continued)

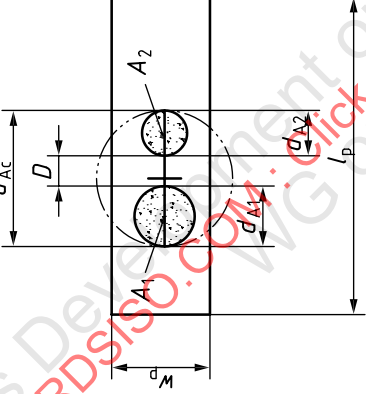
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
			 Reference length for l_p is 100 mm. The total gas pore area within the cluster is represented by a circle of diameter d_A surrounding all the gas pores. The requirement for a single gas pore shall be met by all the gas pores within this circle. A permitted porous area shall be local. The possibility of the pore cluster masking other imperfections shall be taken into consideration. If D is less than d_{A1} or d_{A2}, whichever is smaller, then the total gas pore area is represented by a circle of diameter d_{AC}, where $d_{AC} = d_{A1} + d_{A2} + D$. Systematic cluster porosity is not permitted. d_A corresponds to d_{A1}, d_{A2} or d_{AC}, whichever is applicable.				
2.5	2014	Linear porosity	— butt welds	$\geq 0,5$	$h \leq 0,4 s$, but max. 4 mm $l \leq s$, but max. 75 mm	$h \leq 0,3 s$, but max. 3 mm $l \leq s$, but max. 50 mm	$h \leq 0,2 s$, but max. 2 mm $l \leq s$, but max. 25 mm
			— fillet welds	$\geq 0,5$	$h \leq 0,4 a$, but max. 4 mm $l \leq a$, but max. 75 mm	$h \leq 0,3 a$, but max. 3 mm $l \leq a$, but max. 50 mm	$h \leq 0,2 a$, but max. 2 mm $l \leq a$, but max. 25 mm

Table 1 (continued)

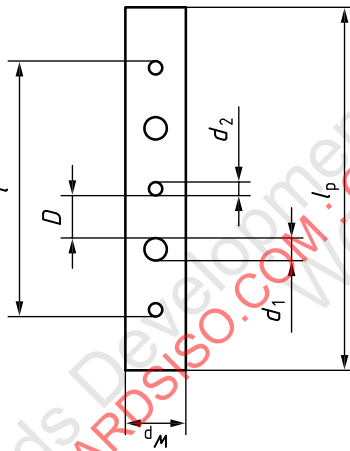
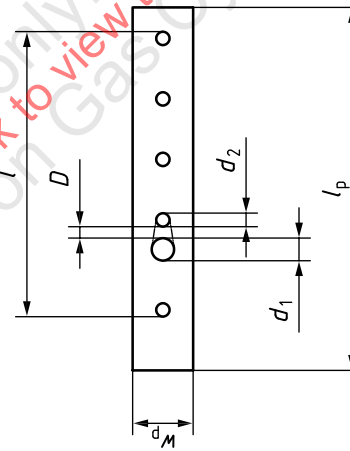
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
			Case 1 ($D > d_2$)  Case 2 ($D < d_2$)  Reference length for l_p is 100 mm. For case 1: $d_1 = h$ For case 2: $d_1 + d_2 + D = h$				

Table 1 (continued)

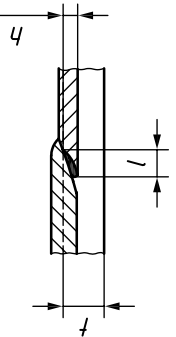
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels			
					D	C	B	B
2.6	2015 2016	Elongated cavity Worm hole	— butt welds	≥ 0,5	$h \leq 0,4 s$, but max. 4 mm	$h \leq 0,3 s$, but max. 3 mm	$h \leq 0,2 s$, but max. 2 mm	
					$l \leq s$, but max. 75 mm	$l \leq s$, but max. 50 mm	$l \leq s$, but max. 25 mm	
2.7	202	Shrinkage cavity	— fillet welds	≥ 0,5	$h \leq 0,4 a$, but max. 4 mm	$h \leq 0,3 a$, but max. 3 mm	$h \leq 0,2 a$, but max. 2 mm	
					$l \leq a$, but max. 75 mm	$l \leq a$, but max. 50 mm	$l \leq a$, but max. 25 mm	
2.8	2024	Crater pipe	 The larger value of h or l will be measured	0,5 to 3 > 3	Short imperfections permitted, but not breaking of the surfaces:	Not permitted	Not permitted	Not permitted
					butt welds: $h \leq 0,4 s$, but max. 4 mm fillet welds: $h \leq 0,4 a$, but max. 4 mm	Not permitted	Not permitted	Not permitted
2.9	300 301 302 303	Solid inclusion Slag inclusion Flux inclusion Oxide inclusion	— butt welds — fillet welds	≥ 0,5	$h \leq 0,4 s$, but max. 4 mm	$h \leq 0,3 s$, but max. 3 mm	$h \leq 0,2 s$, but max. 2 mm	
					$l \leq s$, but max. 75 mm	$l \leq s$, but max. 50 mm	$l \leq s$, but max. 25 mm	

Table 1 (continued)





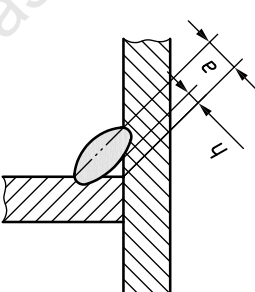
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
2.10	304	Metallic inclusion other than copper	— 	≥ 0,5	$h \leq 0,4 s$, but max. 4 mm	$h \leq 0,3 s$, but max. 3 mm	$h \leq 0,2 s$, but max. 2 mm
		— fillet welds		≥ 0,5	$h \leq 0,4 a$, but max. 4 mm	$h \leq 0,3 a$, but max. 3 mm	$h \leq 0,2 a$, but max. 2 mm
2.11	3042	Copper inclusion	—	≥ 0,5	Not permitted	Not permitted	Not permitted
2.12	401	Lack of fusion (incomplete fusion)		≥ 0,5	Short imperfections permitted:	Not permitted	Not permitted
	4011	Lack of side-wall fusion			butt welds: $h \leq 0,4 s$, but max. 4 mm		
4012		Lack of inter-run fusion			fillet welds: $h \leq 0,4 a$ but max. 4 mm		
4013		Lack of root fusion					
2.13	4021	Incomplete root penetration	 T-joint (fillet weld)	> 0,5	Short imperfections: $h \leq 0,2 a$, but max. 2 mm	Not permitted	Not permitted

Table 1 (continued)

No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
402		Lack of penetration	T-joint (partial penetration) Butt joint (partial penetration)	$\geq 0,5$	Short imperfections: $h \leq 0,2 s$ or $h \leq 0,2 i$, but max. 2 mm	Short imperfections: $h \leq 0,1 s$ or $h \leq 0,1 i$, but max. 1,5 mm	Not permitted
			Butt joint (full penetration) T-joint (full penetration)	$\geq 0,5$	Short imperfections: $h \leq 0,2 t$, but max. 2 mm	Not permitted	Not permitted

Table 1 (continued)

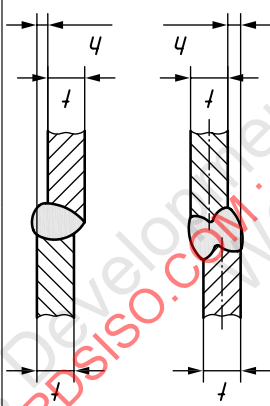
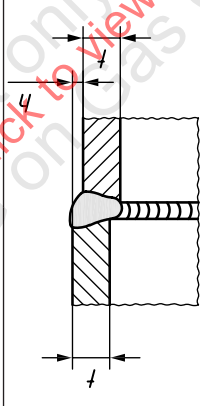
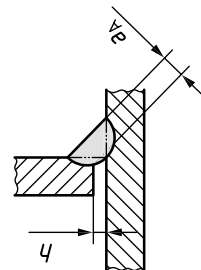
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
3 Imperfections in joint geometry							
3.1	507	Linear misalign- ment	The limits relate to deviations from the correct position. Unless otherwise specified, the correct position is that when the centrelines coincide (see also Clause 1). <i>t</i> refers to the smaller thickness.				
	5071	Linear misalign- ment between plates		0,5 to 3 > 3	$h \leq 0,25 t + 0,2 \text{ mm}$ $h \leq 0,25 t$ but max. 5 mm	$h \leq 0,15 t + 0,2 \text{ mm}$ $h \leq 0,15 t$, but max. 4 mm	$h \leq 0,1 t + 0,2 \text{ mm}$ $h \leq 0,1 t$, but max. 3 mm
	5072	Linear misalign- ment between tubes	This applies for longitudinal welds in plates and hollow sections 	$\geq 0,5$	$h \leq 0,5 t$, but max. 4 mm	$h \leq 0,5 t$, but max. 3 mm	$h \leq 0,5 t$, but max. 2 mm
3.2	617	Incorrect root gap for fillet welds	This applies for circumferential welds in tubes and hollow sections Gap between the parts to be joined. Gaps exceeding the appropriate limit may, in certain cases, be compensated for by a corresponding increase in the throat thickness. 	0,5 to 3 > 3	$h \leq 0,1 a_A + 0,5 \text{ mm}$ $h \leq 0,3 a_A + 1 \text{ mm}$, but max. 4 mm	$h \leq 0,1 a_A + 0,3 \text{ mm}$ $h \leq 0,2 a_A + 0,5 \text{ mm}$, but max. 3 mm	$h \leq 0,1 a_A + 0,2 \text{ mm}$ $h \leq 0,1 a_A + 0,5 \text{ mm}$, but max. 2 mm

Table 1 (continued)

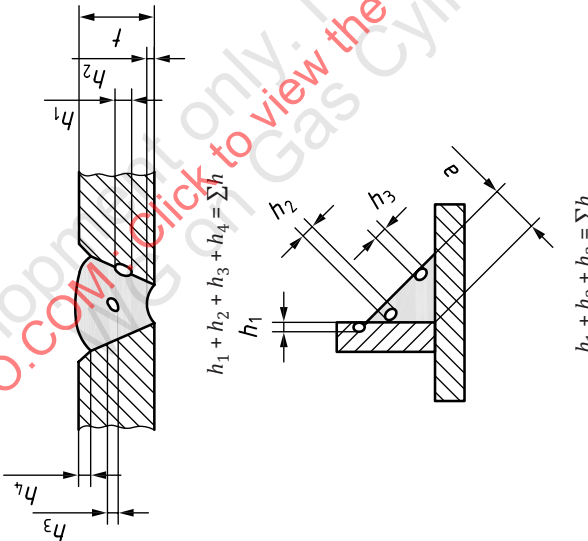
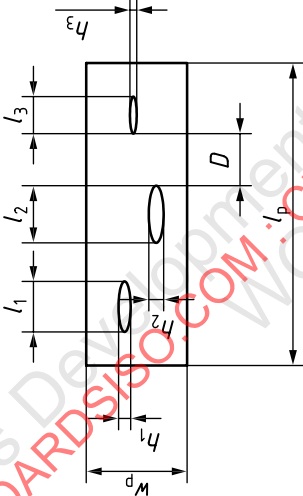
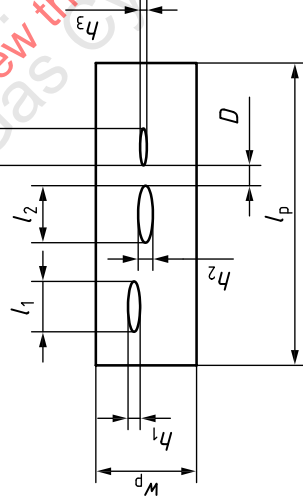
No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
4 Multiple imperfections							
4.1	None	Multiple imperfections in any cross-section which reduce the cross-section	502 Excess weld metal 503 Excessive convexity 504 Excessive penetration, 505 Incorrect weld toe, 506 Overlap, 512 Excessive asymmetry of fillet weld (excessive unequal leg length) and 5214 Excessive throat thickness are excluded 	0,5 to 3 > 3	Not permitted Maximum total height of imperfections: $\Sigma h \leq 0,4 t$ or $\leq 0,4 a$	Not permitted Maximum total height of imperfections: $\Sigma h \leq 0,3 t$ or $\leq 0,3 a$	Not permitted Maximum total height of imperfections: $\Sigma h \leq 0,2 t$ or $\leq 0,2 a$

Table 1 (continued)

No.	Reference to ISO 6520-1	Imperfection designation	Remarks	t mm	Limits for imperfections for quality levels		
					D	C	B
4.2	None	Projected or cross-sectional area in longitudinal direction	Case 1 ($D > l_3$)  $h_1 \times l_1 + h_2 \times l_2 + h_3 \times l_3 = \Sigma h \times l$ Case 2 ($D < l_3$)  $h_1 \times l_1 + h_2 \times l_2 + \left(\frac{h_2 + h_3}{2} \right) \times D + h_3 \times l_3 = \Sigma h \times l$ The sum of the areas $\Sigma h \times l$ shall be calculated as a percentage to the evaluation area $l_p \times w_p$ (case 1). If D is smaller than the shorter length of one of the neighbouring imperfections, the full connection of the two imperfections shall be applied to the sum of imperfections (case 2). See also Annex A for information.	$\geq 0,5$	$\Sigma h \times l \leq 16 \%$	$\Sigma h \times l \leq 8 \%$	$\Sigma h \times l \leq 4 \%$

Annex A

(informative)

Examples of determination of percentage (%) porosity

Figures A.1 to A.9 give a presentation of different percentage porosities. This should assist the assessment of porosity on projected areas (radiographs) or cross-sectional areas.

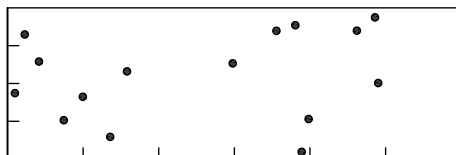


Figure A.1 — 1 surface per cent, 15 pores, $d = 1$ mm



Figure A.2 — 1,5 surface per cent, 23 pores, $d = 1$ mm

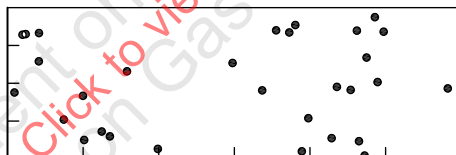


Figure A.3 — 2 surface per cent, 30 pores, $d = 1$ mm

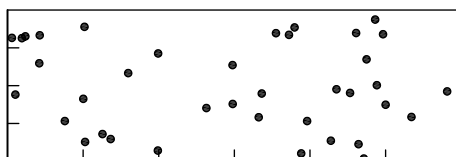


Figure A.4 — 2,5 surface per cent, 38 pores, $d = 1$ mm

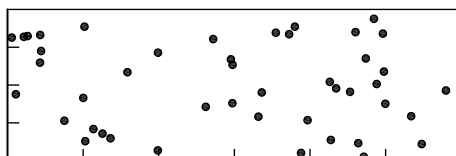


Figure A.5 — 3 surface per cent, 45 pores, $d = 1$ mm