

---

---

**Textile fabrics — Burning behaviour —  
Determination of ease of ignition of  
vertically oriented specimens**

*Textiles — Comportement au feu — Détermination de la facilité  
d'allumage d'éprouvettes orientées verticalement*

STANDARDSISO.COM : Click to view the full PDF of ISO 6940:2004



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 6940:2004

© ISO 2004

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Contents

|                                                                                       | Page      |
|---------------------------------------------------------------------------------------|-----------|
| <b>1 Scope .....</b>                                                                  | <b>1</b>  |
| <b>2 Normative references .....</b>                                                   | <b>1</b>  |
| <b>3 Terms and definitions .....</b>                                                  | <b>1</b>  |
| <b>4 Principle .....</b>                                                              | <b>2</b>  |
| <b>5 Apparatus .....</b>                                                              | <b>2</b>  |
| <b>6 Cautionary measures .....</b>                                                    | <b>3</b>  |
| <b>7 Sampling .....</b>                                                               | <b>3</b>  |
| <b>8 Conditioning and testing atmosphere .....</b>                                    | <b>5</b>  |
| <b>9 Setting up the apparatus .....</b>                                               | <b>7</b>  |
| <b>10 Test procedure .....</b>                                                        | <b>10</b> |
| <b>11 Calculation of the mean ignition time .....</b>                                 | <b>11</b> |
| <b>12 Precision .....</b>                                                             | <b>11</b> |
| <b>13 Test report .....</b>                                                           | <b>11</b> |
| <b>Annex A (normative) Description and construction of the burner .....</b>           | <b>12</b> |
| <b>Annex B (informative) Calculation of mean ignition time — worked example .....</b> | <b>13</b> |
| <b>Annex C (informative) Experimental techniques .....</b>                            | <b>14</b> |

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 6940 was prepared by Technical Committee ISO/TC 38, *Textiles*, Subcommittee SC 19, *Burning behaviour of textiles and textile products*.

This second edition cancels and replaces the first edition (ISO 6940:1984), which has been technically revised. It also incorporates the Amendment ISO 6940:1984/Amd.1:1993.

STANDARDSISO.COM : Click to view the full PDF of ISO 6940:2004

## Introduction

This method is one of two closely related methods of test for the inflammability of textile fabrics. It determines the ease of ignition, as defined in ISO 4880; the other method measures flame spread time (see ISO 6941).

STANDARDSISO.COM : Click to view the full PDF of ISO 6940:2004

[STANDARDSISO.COM](https://standardsiso.com) : Click to view the full PDF of ISO 6940:2004

# Textile fabrics — Burning behaviour — Determination of ease of ignition of vertically oriented specimens

## 1 Scope

This International Standard specifies a method for the measurement of ease of ignition of vertically oriented textile fabrics and industrial products in the form of single or multi-component fabrics (coated, quilted, multilayered, sandwich constructions, and similar combinations), when subjected to a small, defined flame.

This method assesses the properties of textile fabrics in response to flame contact under controlled conditions. Results may not apply to situations where there is restricted air supply or exposure to large sources of intense heat.

The influence of seams on the behaviour of fabrics can be determined by this method, the seam being positioned within the test specimen so as to be subjected to the test flame. Whenever practicable, trimmings should be tested as part of the fabric assembly on which they are, or will be, used.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4880, *Burning behaviour of textiles and textile products — Vocabulary*

ISO 6941, *Textile fabrics — Burning behaviour — Measurement of flame spread properties of vertically oriented specimens*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

### 3.1

#### **flame application time**

time for which the ignition flame is applied to the test specimen

### 3.2

#### **afterflame time**

#### **duration of flame**

length of time for which a material continues to flame under specified test conditions, after the ignition source has been removed

NOTE Afterflame time is measured to the nearest second and afterflame times of less than 1,0 s should be recorded as zero.

### 3.3

#### **ignition**

initiation of combustion

### 3.4

#### **sustained combustion**

flaming of the specimen which gives an afterflame time of 5 s or more or which reaches the top or vertical edges in less than 5 s

### 3.5

#### **minimum ignition time**

minimum time of exposure of a material to an ignition source to obtain sustained combustion under specified test conditions

## 4 Principle

A defined flame from a specified burner is applied to the surface or bottom edge of textile specimens which are vertically oriented.

The mean ignition time is determined as the weighted mean of the measured flame application times to obtain ignition of the specimens.

## 5 Apparatus

**5.1 Mounting frame**, constructed to a design capable of holding the gas burner (5.2, see Figure 1) and the test specimen holder (5.3, see Figure 2) in the specified relative orientation (see Figure 3).

**5.2 Gas burner**, as described in Annex A, capable of being moved from a standby position, where the tip of the burner is at least 75 mm from the test specimen, to either the horizontal or inclined operating position (see Figure 3).

**5.3 Specimen holder**, consisting of a rectangular metal frame having a specimen support pin at each corner of a rectangle of length 190 mm by width 70 mm (see Figure 2). The pins for supporting the specimen have a maximum diameter of 2 mm and a length of at least 26 mm.

NOTE Longer pins may be needed for mounting thick or multilayer specimens.

For the purpose of locating the specimen in a plane at least 20 mm away from the frame (see 9.1.1 and 9.2.1), a spacer stub of 2 mm diameter and a length of at least 20 mm shall be positioned adjacent to each of the four pins.

**5.4 Template**, flat and rigid, made of a suitable material and a size corresponding to the size of the specimen (200 mm × 80 mm). Holes approximately 4 mm in diameter are drilled in each corner of the template and positioned so that the distances between the centres of the holes correspond to the distances between the pins on the specimen holder (see Figure 2). The holes should be located equidistant about the vertical centreline of the template.

**5.5 Gas**, commercial grade propane or butane or butane/propane mixtures.

NOTE Commercial grade propane is preferred but other gases may be used.

### 5.6 Timing devices

**5.6.1** A timing device to control and measure the flame application time, which can be set at 1 s and adjusted at 1 s intervals to an accuracy of 0,2 s or better.

**5.6.2** Three timing devices reading to 0,2 s or better are required to measure the afterflame time. This device is started, preferably automatically, at the instant of test flame termination or removal, and is stopped manually.

## 6 Cautionary measures

### 6.1 Construction of testing equipment

Some products of combustion are corrosive. The equipment shall be constructed of material that will not be adversely affected by the fumes.

### 6.2 Location of test apparatus

The volume of air surrounding the test location shall not have any influence on testing. Where an open-fronted cabinet is used for the test, provision shall be made to allow the specimen to be mounted at least 300 mm from any wall.

### 6.3 Health and safety of test operators

Burning of materials may produce smoke and toxic gases that can affect the health of operators. Between tests, the atmosphere of the testing location, which shall be of adequate dimensions to avoid endangering the health of operators, shall be cleared of smoke and fumes by an extractor fan or other means of ventilation (see 6.2).

NOTE Smoke and fume emission may be subject to national regulations concerning atmospheric pollution control.

## 7 Sampling

### 7.1 Number of specimens

Mark out a set of twelve test specimens, using the template (5.4), to allow for at least five instances of ignition and five instances of non-ignition to occur.

Specimens should normally be tested with the length direction vertical and the outer face towards the igniting flame. If the test material is non-homogeneous and preliminary testing indicates dissimilar inflammability characteristics, length and width specimens should be tested separately. For surface ignition, where the two surfaces of the sample are visually dissimilar and preliminary testing indicates dissimilar inflammability characteristics, each surface shall be tested and the results reported separately.

An iterative procedure is used and the exact number of specimens cannot be stated. A minimum of 10 specimens is needed for each orientation. An extra test specimen is required for the setting-up procedure (see 9.1 and 9.2).

### 7.2 Specimen holder pin location marks


Mark the position through which the pins on the specimen holder must pass by means of the holes in the template (5.4).

NOTE Where the fabric is of open construction (e.g., scrim, gauze), small pieces of adhesive tape may be affixed to the fabric at the pin sites and the position marked on the tape.


### 7.3 Test specimen size

Cut out specimens  $(200 \text{ mm} \pm 2 \text{ mm}) \times (80 \text{ mm} \pm 2 \text{ mm})$ .


Dimensions in millimetres

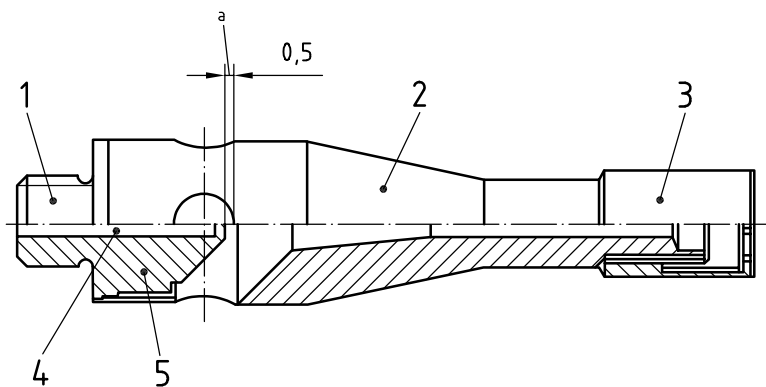

**a) Gas burner arrangement**

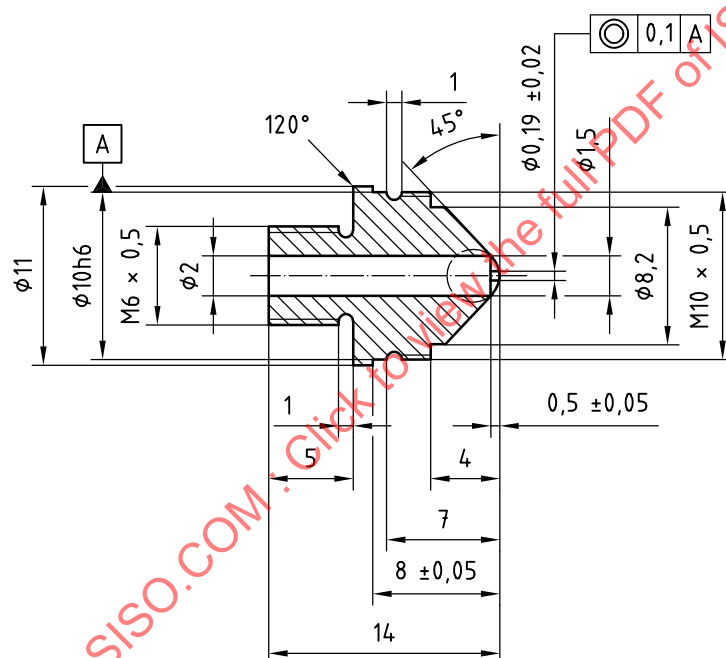

**b) Gas jet**

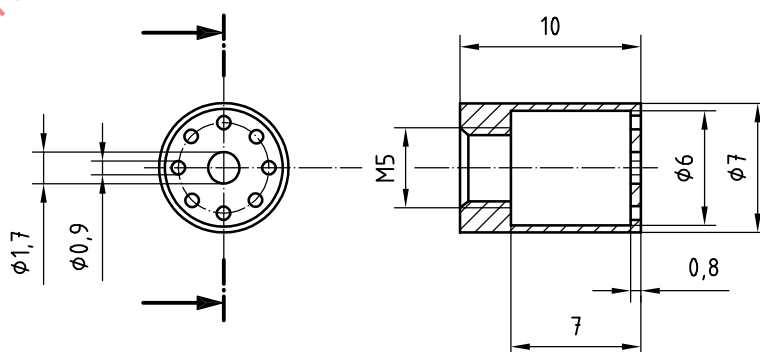


**c) Flame stabilizer**

**Figure 1 — Gas burner**

**d) Burner tube**

- 1 gas jet
  - 2 burner tube
  - 3 flame stabilizer
  - 4 choke tube
  - 5 notch
  - 6 gas mixing zone
  - 7 diffusion zone
  - 8 air chamber
  - 9 outlet
- a Fitted during assembly

Dimensions in millimetres

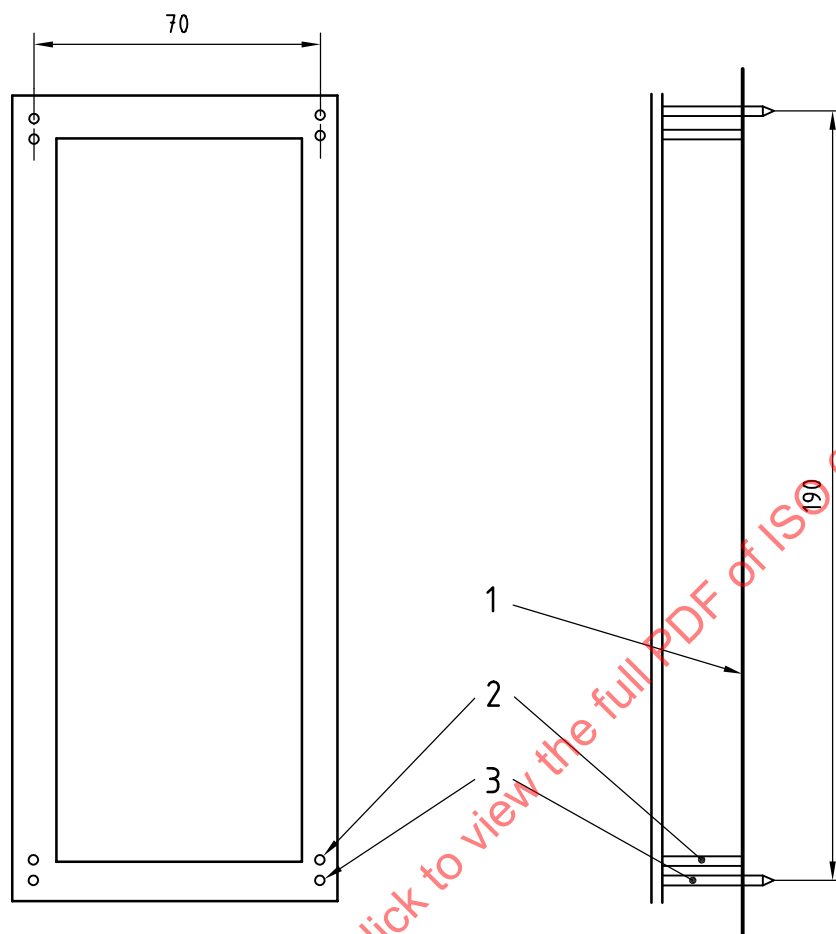

**Key**

- 1 test specimen
- 2 spacer stub
- 3 mounting pin

**Figure 2 — Test specimen holder**

## 8.2 Testing atmosphere

The tests should be performed in an atmosphere having a temperature between 10 °C and 30 °C, a relative humidity of between 15 % and 80 %, and air movement less than 0,2 m/s at the commencement of the test of each specimen. Air movement shall be measured at the flame application position and shall not be influenced by mechanical devices operating during the test.

NOTE Draught shields may be required to maintain stability of the test flame.

## 9 Setting up the apparatus

### 9.1 Procedure A (surface ignition)

#### 9.1.1 Mounting the specimen

Place the test specimen (see 7.1) on the pins of the test specimen holder, making certain that the pins pass through the points marked off from the template and that the back of the specimen is at least 20 mm away from the rectangular metal frame of the test specimen holder. Fit the test specimen holder to the mounting frame with the specimen vertical.

#### 9.1.2 Operating position of the burner

Position the burner perpendicular to the surface of the test specimen such that the axis of the burner is 20 mm above the line of the lower pins and is aligned with the vertical centreline of the face of the test specimen. Ensure that the tip of the burner stabilizer is  $17 \text{ mm} \pm 1 \text{ mm}$  from the surface of the test specimen [see Figure 3 a)].

#### 9.1.3 Flame adjustment — Horizontal reach

Set the burner in the vertical standby position. Light the burner and preheat it for at least 2 min. Move the burner into the horizontal standby position and adjust the horizontal reach of the flame to  $25 \text{ mm} \pm 2 \text{ mm}$ , measured as the distance from the tip of the burner stabilizer to the extreme end of the yellow part of the flame when viewed against a dark background [see Figure 3 d)].

The flame reach shall be checked before testing each set of six specimens.

NOTE If the apparatus does not have a horizontal standby position, it will be necessary to remove the test specimen before carrying out the flame adjustment.

#### 9.1.4 Flame position

Move the burner from the standby position to the horizontal operating position (see 9.1.2). Confirm that the flame impinges on the test specimen in the correct location [see Figure 3 a)].

### 9.2 Procedure B (bottom edge ignition)

#### 9.2.1 Mounting of the test specimen

Place the test specimen (see 7.1) on the pins of the test specimen holder, making certain that the pins pass through the points marked off from the template and that the back of the specimen is at least 20 mm away from the rectangular metal frame of the test specimen holder. Fit the test specimen holder to the mounting frame with the specimen vertical.

### 9.2.2 Operating position of the burner

Position the burner in front of, but below, the test specimen such that it lies in a plane through the vertical centreline of the test specimen and perpendicular to its surface with the longitudinal axis inclined upwards at  $30^\circ$  to the vertical bottom edge of the test specimen. Ensure that the distance between the tip of the burner stabilizer and the bottom edge of the test specimen is  $20 \text{ mm} \pm 1 \text{ mm}$  measured as shown in Figure 3 b).

NOTE It may not be possible to obtain consistent results with fabrics that exhibit drape or sag. Surface ignition may be more appropriate for such fabrics.

### 9.2.3 Flame adjustment — vertical flame height


Set the burner in the vertical standby position. Light the burner and preheat it for at least 2 min. Adjust the flame height to  $40 \text{ mm} \pm 2 \text{ mm}$ , measured as the distance from the tip of the burner stabilizer to the extreme end of the yellow part of the flame when viewed against a dark background [see Figure 3 c)].

The flame height shall be checked before testing each set of six specimens.

### 9.2.4 Flame position

Move the burner from the standby position to the inclined operating position (see 9.2.2). Check that the bottom edge of the test specimen bisects the flame [see Figure 3 b)].


Dimensions in millimetres

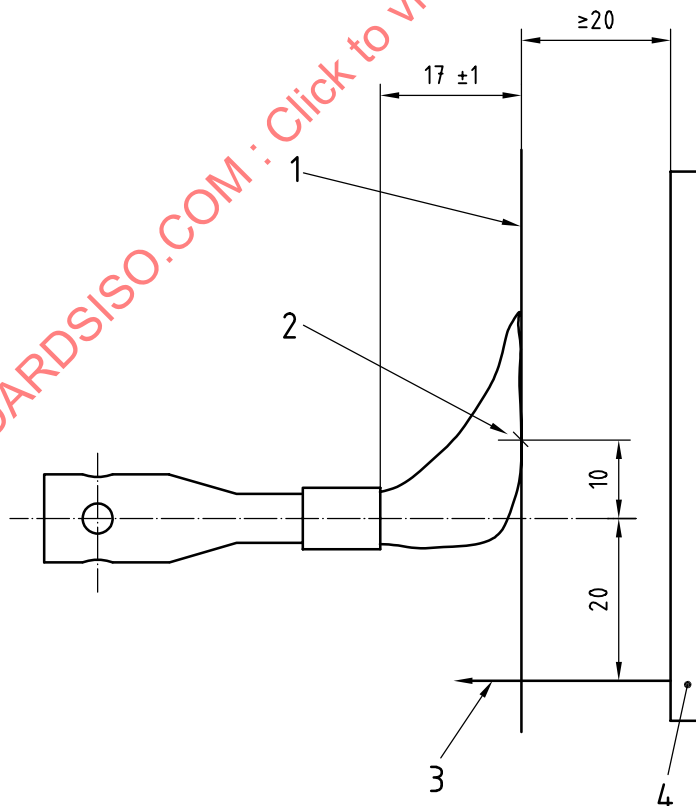

**a) Surface ignition**

### Figure 3 — Flame position and adjustment

Dimensions in millimetres

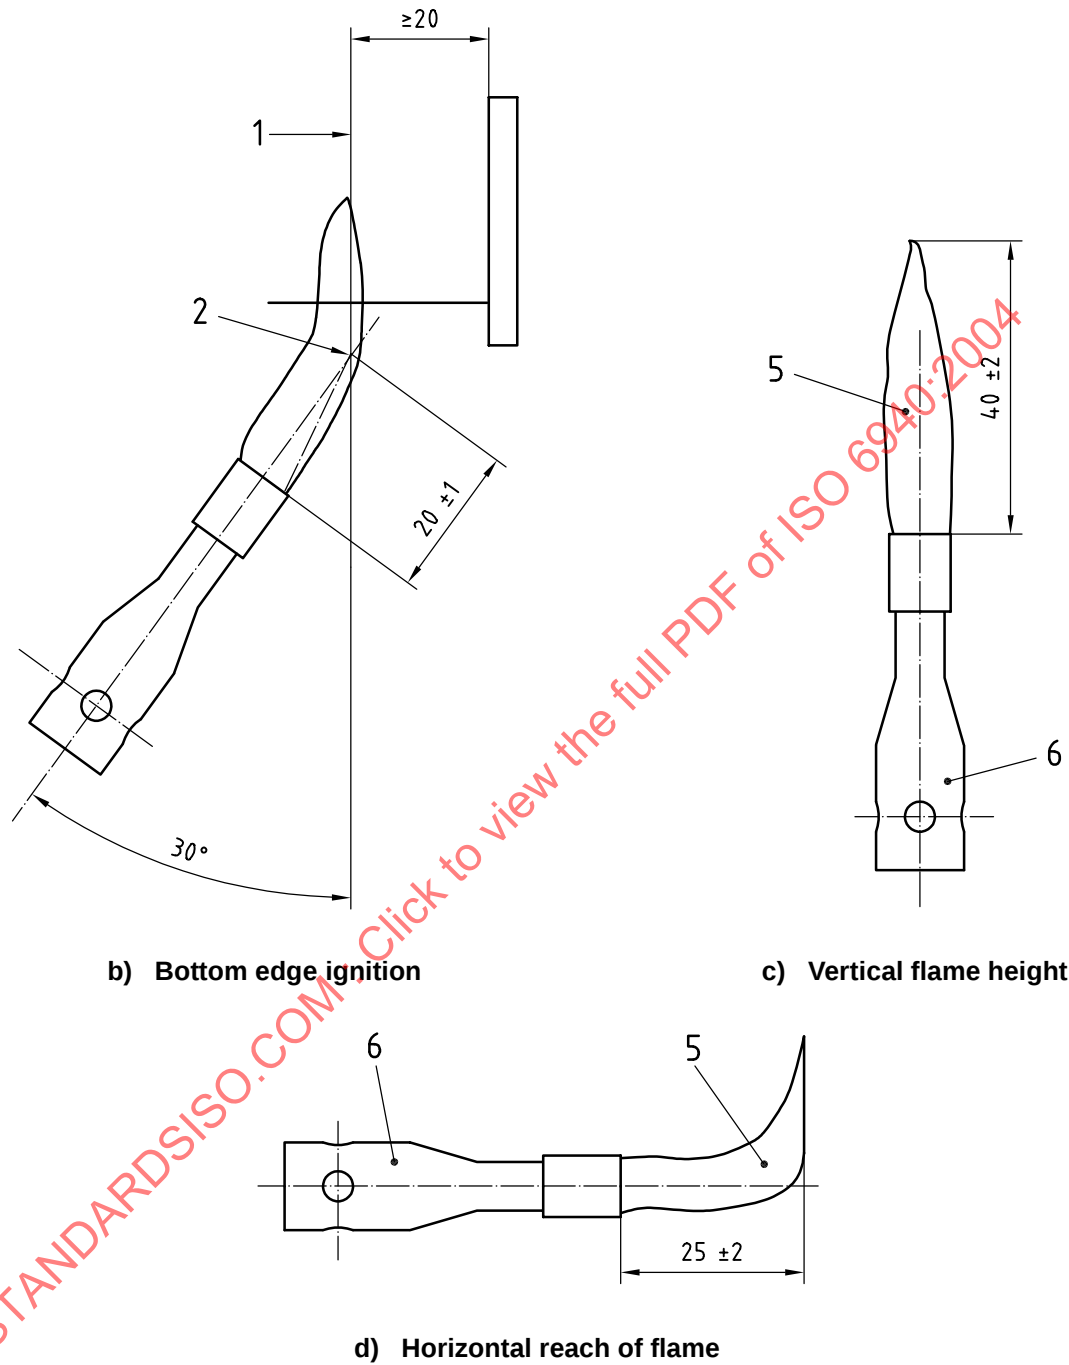

**Key**

- 1 fabric specimen
- 2 nominal flame ignition point
- 3 pin
- 4 mounting frame
- 5 flame
- 6 burner

**Figure 3 — Flame position and adjustment** (*continued*)

## 10 Test procedure

### 10.1 Surface ignition

**10.1.1** Set up the apparatus as described in 9.1.

**10.1.2** Position a fresh test specimen in the specimen holder (see 9.1.1). Record whether the length or the width direction is vertical and which surface of the test specimen is exposed towards the test flame.

**10.1.3** Apply the test flame for the flame application time that approximates to the shortest time to cause ignition.

NOTE Preliminary testing may be needed to determine this initial flame application time.

**10.1.4** Record the flame application time and whether ignition has occurred.

**10.1.5** Mount a fresh specimen in the same orientation in the specimen holder. If ignition has occurred with the previous specimen, apply the test flame for 1 s less; if ignition has not occurred with the previous specimen, apply the test flame for 1 s more. Record the flame application time and whether ignition has occurred.

If a specimen ignites with a 1 s flame application time, record non-ignition as "0" and retest with 1 s flame application time. If a specimen does not ignite with a 20 s flame application time, retest with a 20 s flame application time.

**10.1.6** Continue testing in accordance with 10.1.5 until there are at least five instances of ignition and five instances of non-ignition. In the case of ignition at 1 s flame application time, continue until there are at least five instances of ignition at 1 s. In the case of non-ignition at 20 s flame application time, continue until there are at least five instances of non-ignition at 20 s.

NOTE The maximum flame application time used is 20 s. Materials that do not ignite with this flame application time will not normally ignite with higher flame application times. If necessary, testing can be extended above 20 s and this fact reported in the test report (see Clause 13).

### 10.2 Bottom edge ignition

**10.2.1** Set up the apparatus as described in 9.2.

**10.2.2** Position a fresh test specimen in the specimen holder (see 9.2.1). Record whether the length or the width direction is vertical and which surface of the test specimen is exposed towards the test flame.

**10.2.3** Apply the test flame for a flame application time that approximates to the shortest time to cause ignition.

NOTE Preliminary testing may be needed to determine this initial flame application time.

**10.2.4** Record the flame application time and whether ignition has occurred.

**10.2.5** Mount a fresh specimen in the same orientation in the specimen holder. If ignition has occurred with the previous specimen, apply the test flame for 1 s less; if ignition has not occurred with the previous specimen, apply the test flame for 1 s more. Record the flame application time and whether ignition has occurred.

If a specimen ignites with a 1 s flame application time, record non-ignition as "0" and retest with 1 s flame application time. If a specimen does not ignite with a 20 s flame application time, retest with a 20 s flame application time.

**10.2.6** Continue testing in accordance with 10.2.5 until there are at least five instances of ignition and five instances of non-ignition. In the case of ignition at 1 s flame application time, continue until there are at least five instances of ignition at 1 s. In the case of non-ignition at 20 s flame application time, continue until there are at least five instances of non-ignition at 20 s.

NOTE The maximum flame application time used is 20 s. Materials that do not ignite with this flame application time will not normally ignite with higher flame application times. If necessary, testing can be extended above 20 s and this fact reported in the test report (see Clause 13).

## 11 Calculation of the mean ignition time

Calculate the mean of the recorded times for ignition or non-ignition, whichever has occurred least. If the data relate to non-ignition, add 0,5 s; if it relates to ignition, subtract 0,5 s. Round this result to the nearest second and report as the mean ignition time for the orientation tested. See Annex B for a worked example.

## 12 Precision

These methods are used to determine the mean ignition time, which is the minimum flame application time required to produce sustained combustion under the specified test conditions, calculated to the nearest second. The precision of the methods is largely dependent on the type of material to be tested.

These methods are designed for use on inflammable materials, which sustain combustion when ignited. With this type of material, these methods are accurate to the nearest second. However, because the mean ignition time represents the boundary between non-ignition and ignition, both types of behaviour may be observed when the flame is applied for exactly the mean ignition time. See worked example in Annex B.

The methods are not suitable for flame-retardant materials, which give only very limited combustion rather than sustained combustion. The limited combustion of these materials is difficult to detect by these methods and flame-retardant materials are consistently recorded as "not ignited by 20 s". The flame-retardant properties of these fabrics may be determined by other test methods.

Certain intermediate materials give extremely variable results. These materials give sustained combustion only under certain limited circumstances, i.e., sustained combustion is only achieved within a narrow range of flame application times. This inconsistent behaviour is a property of the material and not a feature of the test methods.

## 13 Test report

The test report shall include the following information:

- a) a statement that the test was carried out in accordance with this International Standard and details of any deviation from it;
- b) gas used;
- c) date of test;
- d) ambient conditions of temperature and relative humidity in the area in which the test was carried out (see 8.2);
- e) technique used to attach fabrics that cannot be supported on pins (see 7.2);
- f) identification of fabric tested including details of any pretreatment, e.g. a cleansing procedure;
- g) which surface was exposed towards the flame, which fabric direction was vertical, and whether surface or bottom ignition was used;
- h) a table giving the flame application time and the observation of ignition or non-ignition for each test specimen;
- i) the mean ignition time calculated in accordance with Clause 11 for each orientation tested;
- j) if the fabric did not ignite with a 20 s flame ignition time (or higher maximum flame ignition time: see Notes to 10.1.6 and to 10.2.6).