
International Standard



7056

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

Plastics laboratory ware — Beakers

Matériel de laboratoire en plastique — Bêchers

First edition — 1981-09-01

STANDARDSISO.COM : Click to view the full PDF of ISO 7056:1981

UDC 542.231.5 : 678.5/.8

Ref. No. ISO 7056-1981 (E)

Descriptors : glassware, laboratory glassware, beakers, construction, dimensions, graduations, tests, determination, conductivity, flexibility.

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards institutes (ISO member bodies). The work of developing International Standards is carried out through ISO technical committees. Every member body interested in a subject for which a technical committee has been set up has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council.

International Standard ISO 7056 was developed by Technical Committee ISO/TC 48, *Laboratory glassware and related apparatus*, and was circulated to the member bodies in May 1980.

It has been approved by the member bodies of the following countries :

Australia	Hungary	Romania
Brazil	Italy	South Africa, Rep. of
Czechoslovakia	Korea, Rep. of	Spain
Egypt, Arab Rep. of	Mexico	United Kingdom
France	Netherlands	USSR
Germany, F. R.	Poland	

The member body of the following country expressed disapproval of the document on technical grounds :

India

Plastics laboratory ware — Beakers

1 Scope and field of application

This International Standard specifies requirements for a series of squat-form plastics beakers for laboratory use. It is applicable to beakers having a tapered or a non-tapered form. The non-tapered form may, however, have a slight taper to facilitate mould release during manufacture.

2 Reference

IEC Publication 335-1, *Safety of household and similar electrical appliances/Part 1: General requirements*.

3 Sizes

The beakers covered by this International Standard have the following nominal capacities:

25 — 50 — 100 — 250 — 500 — 1 000 — 2 000 and 5 000 ml.

4 Graduation and figuring

Provided that the beaker is not opaque, it shall be graduated and figured on the outside as follows.

4.1 General

The graduation lines, figuring and inscriptions shall be clearly and durably marked.

4.2 Graduation lines

The graduation lines shall be of uniform thickness and shall lie in a plane perpendicular to the axis of the beaker. Each beaker shall bear figured graduation lines at intervals depending on the nominal capacity of the beaker, as defined in the table 1.

Table 1

Nominal capacity, ml	25	50	100	250	500	1 000	2 000	5 000
Figured intervals, ml	5	10	20	50	100	200	400	1 000

The highest graduation line shall indicate the nominal capacity of the beaker (see clause 5). The lowest graduation line shall indicate 20 % of the nominal capacity. Shorter, non-figured, intermediate graduation lines shall indicate intervals of 1, 2 or 5 ml, or decimal multiples thereof.

The figured graduated lines shall extend at least one-fifteenth of the way round the mean circumference of the beaker, but in any case shall be not less than 8 mm long.

The ends of the figured graduation lines shall lie on a line coplanar with the axis of the beaker; this line may be marked.

4.3 Figuring

The position of the figuring shall be such as to enable the value corresponding to each graduation line to be readily identified.

The figures indicating the nominal capacity of the beaker shall be adjacent to the top graduation line, shall be more prominent than the other figures, and shall be followed by the inscription "ml".

4.4 Tolerances

The errors in graduation shall not exceed $\pm 10\%$ of the indicated values.

5 Capacity

The brimful capacity of a beaker shall be not less than 1,3 times the nominal capacity of the beaker for sizes up to 500 ml, and not less than 1,2 times the nominal capacity for larger sizes.

6 Material

6.1 General

Beakers shall be rigidly constructed of generally non-brittle plastics material of suitable chemical and physical properties and shall be as free as possible from moulding defects and stress.

6.2 Resistance to extraction of ionic material by water at 60 °C

When tested by the method specified in annex A, the beaker shall give an aqueous extract free of suspended matter, and the difference between its conductivity and that of the original water used for the extraction shall not exceed the values given in table 2.

NOTE — The conductivity of water containing approximately 1 mg/l of sodium chloride is 200 $\mu\text{S}/\text{m}$.

Table 2

Nominal capacity ml	Difference in conductivity $\mu\text{S}/\text{m}$
25	1 000
50	800
100	700
250	500
500	400
1 000	300
2 000	250
5 000	150

7 Details of construction

7.1 Base

The base shall be such that the beaker stands vertically on a plane, horizontal surface without any tendency to spin or rock. The inside surface of the base shall be flat and free from moulding residues.

7.2 Brim

The diameter of the brim shall be not less than 10 % greater than the average external diameter of the body. The edge of the brim shall be finished in a plane parallel to that of the base. The inside surface of the beaker shall have a smooth contour.

7.3 Spout

The spout shall be so shaped that, when the beaker is filled to its nominal capacity with water, the water may be poured in a regular stream clear of the side of the beaker. The spout shall be at 90° to the radius drawn from the midpoint of the graduation lines and shall be on the left-hand side when the graduation lines face the user. The spout shall not extend above the plane of the brim of the beaker.

7.4 Shape

The ratio of overall height to maximum body diameter shall lie between 1,0 and 1,4.

If the sides of the beaker are not parallel, the body shall form a right frustum of a cone, the apex angle of which shall lie below the base of the beaker. This angle (defined as the angle included between the sides) may be the minimum required to en-

sure mould release in the manufacture of nominally non-tapered beakers, and shall not exceed 10° in the case of tapered beakers.

7.5 Radius at base

The internal radius at the junction between the base and the side of the beaker shall be not less than 3 mm.

7.6 Wall thickness

The wall thickness and brim design shall be such that, when the beaker is tested by the method specified in annex B, the outside diameter of the brim shall not decrease by more than 10 %.

The wall thickness shall be uniform, and the base thickness shall be not less than the wall thickness.

Substantial local irregularities shall be avoided.

7.7 Dimensions

Recommended nominal dimensions are given in table 3.

Table 3

Nominal capacity ml	Overall height, h mm	Average outside body diameter mm	Wall thickness mm min.
25	40	35	1,5
50	45	45	1,5
100	70	50	1,5
250	80	75	2
500	115	90	2
1 000	130	110	2
2 000	175	140	2
5 000	220	195	2,5

7.8 Surface finish

The inside and outside surfaces shall have a smooth contour.

8 Inscriptions

The following inscriptions shall be durably and legibly marked on all beakers :

- the words "approximate volumes", or a suitable abbreviation (on graduated beakers);
- the maker's and/or vendor's name or readily identifiable mark;
- the name of the material from which the beaker is made, for example "polypropylene" or the symbol "PP"¹⁾,

1) See ISO 1043, *Plastics — Symbols*.

and the manufacturer's recommended safe maximum temperature for short-term use (several hours) in contact with materials that do not attack the plastic; for example, for polypropylene : PP 135 °C max.

NOTE — The temperature in the example is merely intended to indicate an inscription and does not represent any particular grade of plastics material.

d) the pictogram shown in figure 1, or the words "no flame" (the former is preferred);

NOTE — The pictogram indicates that the beaker is not suitable for heating by flame or other heat sources (for example, on a hot plate) that raise the surface temperature above the manufacturer's recommended safe temperature for short-term use.

e) the number of the International Standard, or corresponding national standard.

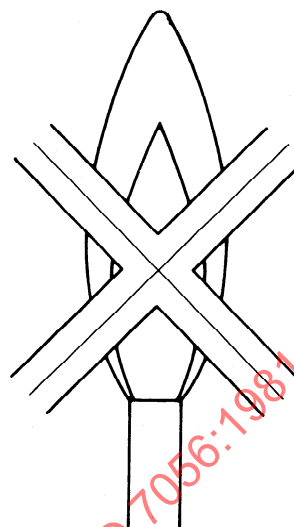


Figure 1 — Pictogram to be inscribed on the beaker

STANDARDSISO.COM : Click to view the full PDF of ISO 7056:1981

Annex A

Verification of resistance to extraction of ionic material by water at 60 °C

(Forms part of the Standard.)

A.1 Apparatus and materials

A.1.1 Watch glasses, made of borosilicate glass, and of sizes appropriate to the beakers under test.

A.1.2 Water bath, maintained at 60 ± 2 °C.

A.1.3 Conductivity meter, suitable for measurement of the electrical conductivity of water.

A.1.4 De-ionized water, having a conductivity of less than 200 µS/m.

The conductivity at 20 °C shall be determined before use.

A.1.5 Detergent solution.

A.2 Procedure

Thoroughly clean each beaker with hot water and the detergent solution (A.1.5), then rinse well with hot water followed by cold water and finally with liberal quantities of the de-ionized water (A.1.4).

Fill each beaker to its nominal capacity with the de-ionized water (A.1.4) and place in the water bath (A.1.2) maintained at 60 ± 2 °C to the depth of the water level in the beaker. Cover each beaker with a clean watch glass (A.1.1) and allow to stand for 3 h.

Remove each beaker from the water bath and allow the contents to cool to 20 °C. Measure the electrical conductivity of the water in each beaker by means of the conductivity meter (A.1.3), and record the difference in conductivity, in microsiemens per meter, of the water before and after the test.

STANDARDSISO.COM : Click to view the full text of ISO 7056-1981