
**Rubber, vulcanized — Determination of
creep in compression or shear**

*Caoutchouc vulcanisé — Détermination du fluage en compression ou
en cisaillement*

STANDARDSISO.COM : Click to view the full PDF of ISO 8013:2006



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 8013:2006

© ISO 2006

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword.....	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions.....	1
4 Apparatus	2
5 Test piece	7
6 Time-lapse between vulcanization and testing	8
7 Mechanical conditioning.....	9
8 Test temperature.....	9
9 Procedure	9
10 Calculation of results	10
11 Expression of results	13
12 Test report	13
Annex A (informative) Values of forces required for rubbers of different hardnesses	14

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 8013 was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 2, *Testing and analysis*.

This second edition cancels and replaces the first edition (ISO 8013:1988), which has been revised to update the normative references (ISO 471, ISO 3383, ISO 4648 and ISO 4661-1 have been replaced by ISO 23529 and ISO 1747 by ISO 1827).

Introduction

When a constant stress is applied to rubber, the deformation is not constant but increases gradually with time; this behaviour is called “creep”. Conversely, when rubber is subjected to a constant strain, a decrease in the stress in the material takes place; this behaviour is called “stress relaxation”.

The creep test is of particular interest where vulcanized rubbers are used to support a constant load, such as in bearings or mountings.

The processes responsible for creep may be physical or chemical in nature, and under all normal conditions both processes will occur simultaneously. However, at normal or low temperatures and/or short times, creep is dominated by physical processes, whilst at high temperatures and/or long times, chemical processes are dominant. In general, physical creep is found to be directly proportional to logarithmic time, and chemical creep to linear time; but great care must be taken in extrapolating time/creep curves in order to predict creep after periods considerably longer than those covered by the test, and in using tests at higher temperatures as accelerated tests to give information on creep at lower temperatures.

In addition to the need to specify the temperature- and time-intervals in a creep test, it is also necessary to specify the initial strain and the previous mechanical history of the test piece, since these may also influence the measured creep, particularly in rubbers containing filler.

STANDARDSISO.COM : Click to view the full PDF of ISO 8013:2006

Rubber, vulcanized — Determination of creep in compression or shear

WARNING — Persons using this International Standard should be familiar with normal laboratory practice. This standard does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any national regulatory conditions.

1 Scope

This International Standard specifies a method for the determination of creep in rubber continuously subjected to compressive or to shear forces. The standard cannot be used for intermittent deformation of rubber.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 815, *Rubber, vulcanized or thermoplastic — Determination of compression set at ambient, elevated or low temperatures*

ISO 1827, *Rubber, vulcanized or thermoplastic — Determination of modulus in shear or adhesion to rigid plates — Quadruple shear method*

ISO 4664-1, *Rubber, vulcanized or thermoplastic — Determination of dynamic properties — Part 1: General guidance*

ISO 23529, *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

creep increment

increase in strain which occurs in a specified time-interval under constant force and at constant temperature

NOTE It is expressed as the ratio of the increase in deformation over the time-interval to the initial, unstrained thickness.

3.2

creep index

relative increase in strain which occurs in a specified time-interval under constant force and at constant temperature

NOTE It is expressed as the ratio of the increase in the strain over the time-interval to the strain at the beginning of the interval.

3.3

compliance increment

ratio of the increase in strain which occurs in a specified time-interval under constant force and at constant temperature to the constant stress applied

4 Apparatus

4.1 Thickness-measuring device

Thickness measurements shall be made using a device complying with either ISO 23529 or the test apparatus described in 4.2. It shall be capable of measuring the test piece thickness to the nearest 0,1 mm. It shall have plates of diameter at least 30 mm. The dial gauge shall be fitted with a flat contact perpendicular to the plunger and parallel to the base plate and shall operate with a foot pressure of (22 ± 5) kPa.

4.2 Compression device for measurement in compression

The apparatus shall consist of two parallel, flat steel plates, between which the prepared test piece is compressed. In the case of unbonded test pieces, the plates shall be highly polished with a surface finished to not worse than 0,2 μm arithmetic mean deviation from the mean line of the profile. It is recommended that the operating surfaces of the plates be lubricated. The test pieces shall be free from mould lubricants and dusting powder. The plates shall be sufficiently rigid to withstand the force without bending and of sufficient size to ensure that the whole of the compressed test piece is within the area of the plates.

NOTE For most purposes, a silicone or fluorosilicone liquid having a kinematic viscosity of 0,01 m^2/s at standard temperature is a suitable lubricant.

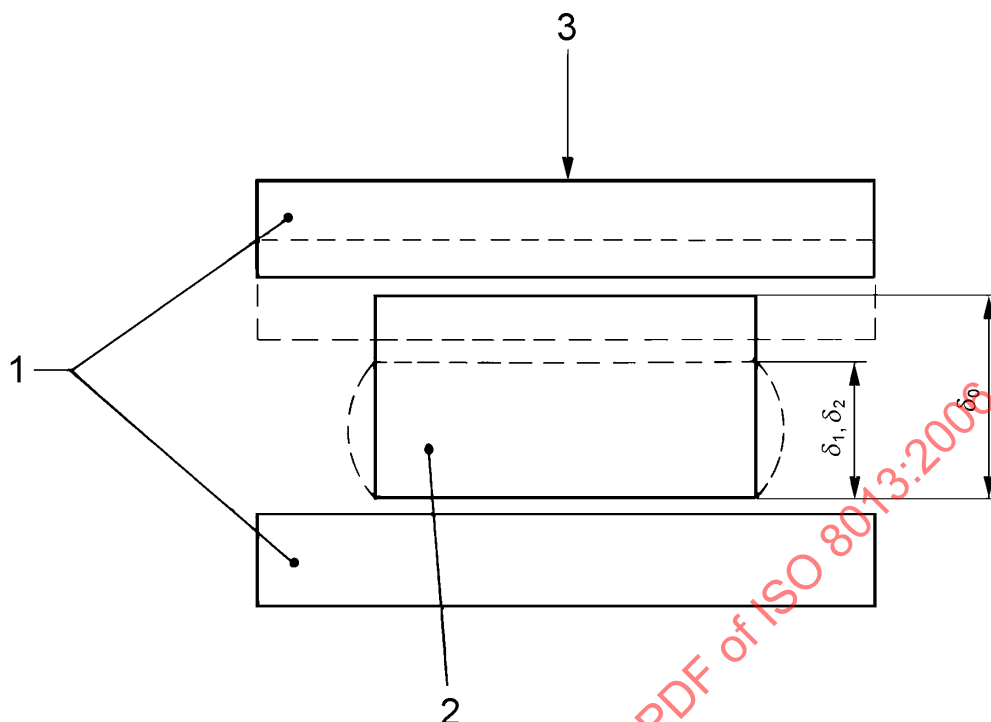
One of the plates shall be rigidly mounted so that it does not move in any direction under the action of the compressive force. The other plate shall be able to move in a friction-free manner in one direction only, i.e. in a direction coincident with the axis of the test piece (see Figure 1).

The apparatus shall be capable of applying the full force with negligible overshoot and maintaining it constant to within 0,1 %. The mechanism for applying the force shall be such that the line of action of the applied force remains coincident with the axis of the test piece as it creeps.

Suitable equipment shall be connected to the compression device so that the deformation of the test piece may be determined, to an accuracy of $\pm 0,1$ % of the initial test piece thickness, at different times after the force has been fully applied.

Many types of apparatus have been used, with mechanical, electronic or optical measurement of deformation. Figure 2 shows a typical example using a micrometer dial gauge for the determination of creep in compression. The measuring device shall not exert a pressure of more than 22 kPa on the test piece at the beginning.

The test piece and the flat plates of the compression device shall be inside a temperature-controlled chamber (see 4.4).

**Key**

- 1 steel plates
- 2 test piece
- 3 line of action of compressive force
- δ_0 initial thickness

Figure 1 — Test piece in compression**4.3 Shear device for measurements in shear**

The apparatus shall be capable of measuring the shear deflection in the test piece due to the application of a constant shear force.

The apparatus shall be capable of applying the full force with negligible overshoot and maintaining it constant to within 0,1 %.

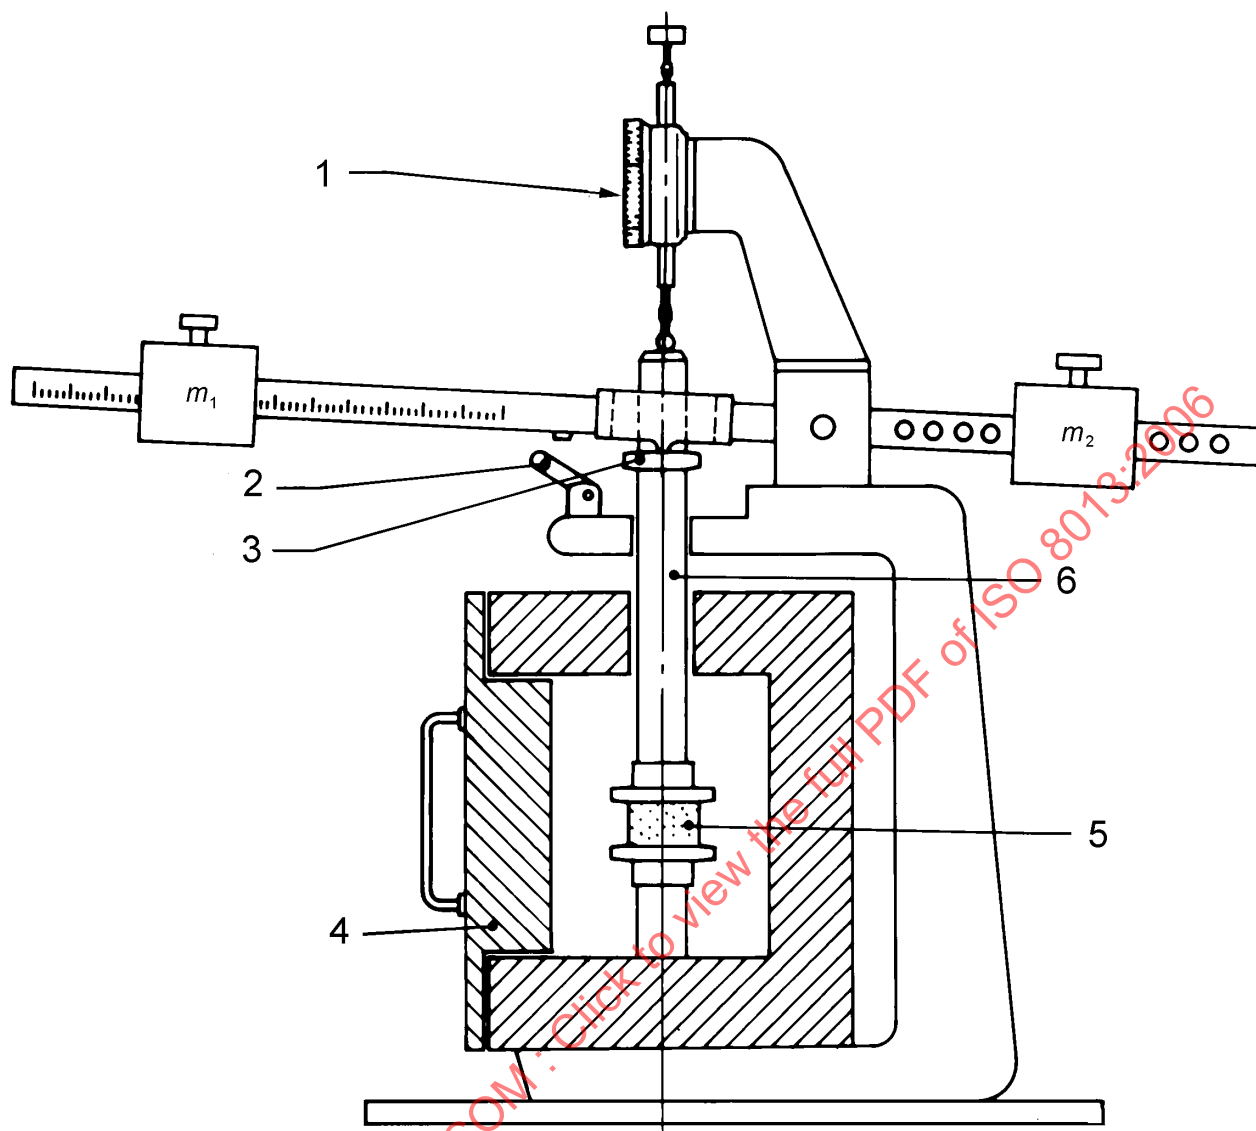
The force shall be applied either to the central metal plate, with the outer plates rigidly mounted, or to the outer metal plates with the central plate rigidly mounted. The line of action of the applied force shall be in the plane of the central plate, and pass through its centre in a direction perpendicular to the undeformed rubber test pieces. This line of action shall be maintained as the test piece creeps (see Figure 3).

The movement of the central plate relative to the outer plates shall be in a friction-free manner and only in the direction of the line of action of the applied force.

Suitable equipment shall be connected to the test piece so that relative movement of the central plate with respect to the outside plates can be determined with an accuracy of $\pm 0,01$ mm at different times after the force has been fully applied.

The test piece and the flat plates to which it is bonded shall inside a temperature-controlled chamber (see 4.4).

Figure 4 shows a typical shear test fixture.



Key

- | | |
|-----------------|----------------------------------|
| 1 dial gauge | 4 temperature-controlled chamber |
| 2 locking lever | 5 test piece |
| 3 setting ring | 6 ceramic bar |

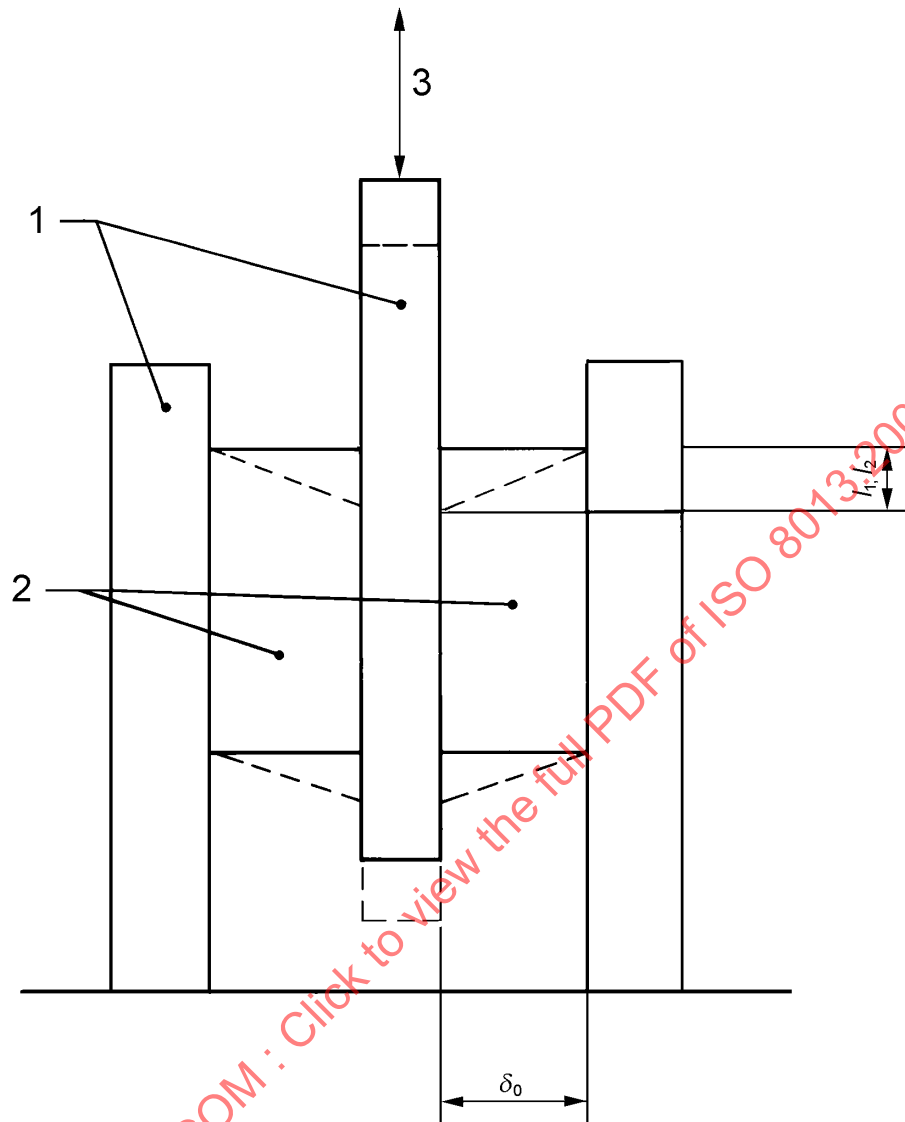
Figure 2 — Example of test arrangement for creep in compression with temperature-controlled chamber

4.4 Temperature-controlled chamber

A test chamber in accordance with ISO 23529, provided with temperature control to maintain the specified air temperature within the tolerances given in Clause 8, shall be used. Satisfactory circulation of the air shall be achieved by means of a fan. Care shall be taken to minimize change in temperature of the test piece by conduction through metal parts which are connected with the outside of the chamber or by direct radiation from heaters within the chamber.

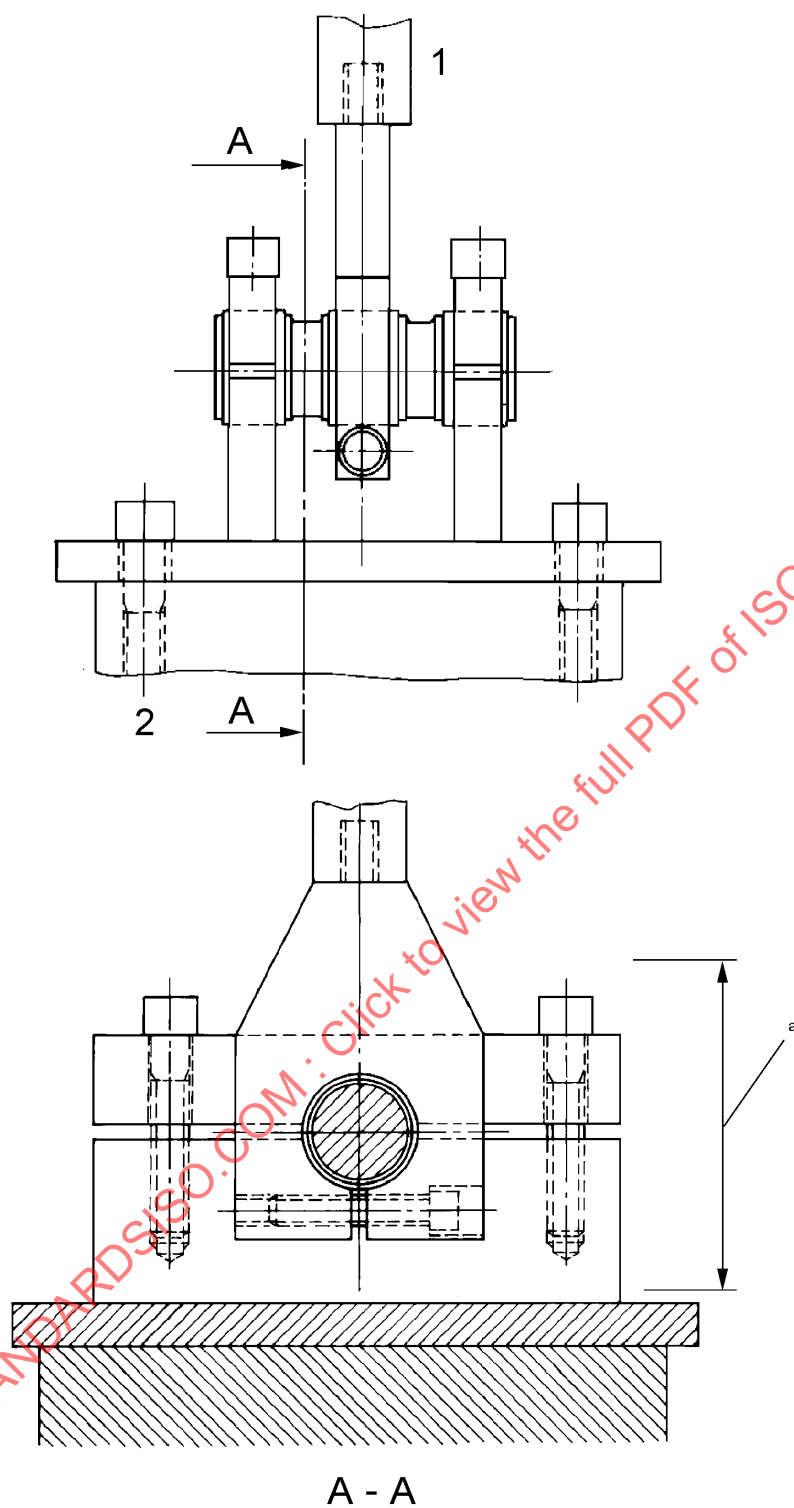
4.5 Timer

Use a timer reading in seconds and minutes.

**Key**

- 1 steel plates
- 2 bonded test pieces
- 3 line of action of shear force
- δ_0 initial thickness

Figure 3 — Test piece in shear



Key

- 1 actuator
- 2 load cell

^a Shall be in test chamber.

Figure 4 — Typical test fixture for double-bonded shear test piece

5 Test piece

5.1 Test piece for measurements in compression

5.1.1 The test piece shall be a cylindrical disc; two sizes may be used having the following dimensions:

- Type A shall have a diameter of $(29,0 \pm 0,5)$ mm and a thickness of $(12,5 \pm 0,5)$ mm.
- Type B shall have a diameter of $(13,0 \pm 0,5)$ mm and a thickness of $(6,3 \pm 0,3)$ mm.

NOTE These sizes correspond to type A and B test pieces in ISO 815.

5.1.2 The test pieces shall be prepared in accordance with ISO 23529 by either moulding or cutting. They shall be free from any fabric or other reinforcing support.

Cutting shall be carried out by means of a sharp rotating circular die or revolving knife, lubricated with soapy water and brought carefully into contact with the rubber. Alternatively, the die or knife may be kept stationary and the rubber rotated against it.

NOTE When cupping is a problem, the test piece shape can be improved by cutting the test piece in two stages: first cut an oversized test piece and then trim it to the exact dimensions with a second cutter.

If bonded test pieces are required, the plane surfaces of the rubber disc shall be bonded to rigid end pieces. Bonding to the end pieces shall be carried out either during moulding or subsequently, using a suitable adhesive that does not flow under the test conditions and avoiding the use of excessive amounts of adhesive. The thickness of the end pieces shall be determined prior to bonding.

NOTE 1 Different results will be obtained in compression with bonded and non-bonded test pieces.

NOTE 2 Since rigidity is required only in a radial direction, the end pieces may be of thin metal sheet, having a minimum thickness of 0,25 mm.

5.2 Test piece for measurements in shear

The double-shear test piece shall be of either circular or square cross-section and shall be bonded to rigid end plates and a rigid centre plate (see Figures 3 and 4).

To avoid significant bending, the diameter (or side in the case of square test pieces) shall be at least four times the thickness. This will ensure that the deformation is essentially simple shear of the calculated magnitude and that the apparent shear modulus differs by less than 3 % from the true value.

Because of the difficulties of ensuring uniform vulcanization in thick pieces, the thickness of the vulcanized pieces should not be more than 12 mm.

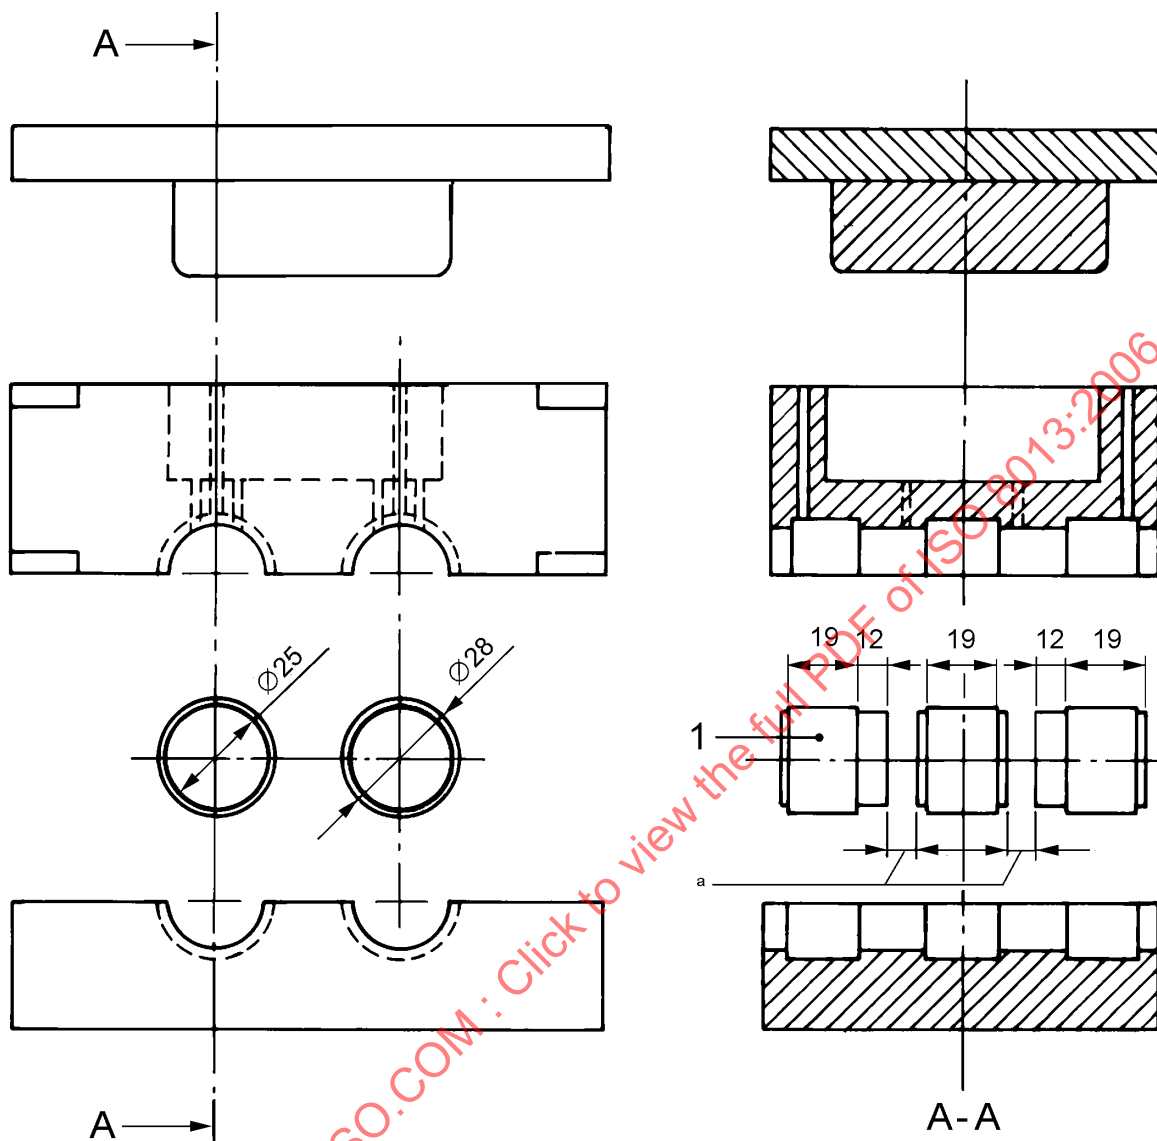
Preferably, the test pieces should have a circular cross-section of 25 mm diameter and a thickness of 6,3 mm. Alternatively, the double-shear test piece specified in ISO 4664-1 or ISO 1827 may be used.

The test pieces should preferably be prepared by moulding (see Figure 5) directly on to steel plates. The thickness of the steel plates used shall be determined prior to moulding or bonding.

5.3 Number

At least three test pieces shall be used.

Dimensions in millimetres

**Key**

1 metal parts

a Thickness of rubber block.

Figure 5 — Double-bonded shear mould**6 Time-lapse between vulcanization and testing**

For all test purposes, the minimum time between vulcanization and testing or mechanical conditioning shall be 16 h.

For non-product tests, the maximum time between vulcanization and testing shall be 4 weeks and, for evaluations intended to be comparable, the test, as far as possible, shall be carried out after the same time interval.

For product tests, whenever possible, the time between vulcanization and testing shall not exceed 3 months. In other cases, tests shall be made within 2 months of the date of receipt of the product.

Samples and test pieces shall be protected from light and excessive heat as completely as possible during the interval between vulcanization and testing.

7 Mechanical conditioning

It is known that results are affected by the strain history of the sample and that reproducibility of the results is improved by mechanical conditioning. It is therefore preferable that the following conditioning procedure be carried out, at standard temperature:

- a) strain the test piece by about $(25 \pm 2) \%$ at a rate of 25 mm/min in the same direction as in the test (see 4.2 or 4.3) and then return it to approximately zero deflection;
- b) repeat step a) to give a total of five deformations.

A minimum of not less than 16 h and maximum of not more than 48 h at standard laboratory temperature shall be allowed to elapse between mechanical conditioning and testing.

8 Test temperature

The temperature of test will be chosen for technical reasons, but it is recommended that one of the following be used, in accordance with ISO 23529, with the following tolerances:

Standard temperature, $(55 \pm 1) ^\circ\text{C}$, $(70 \pm 1) ^\circ\text{C}$, $(85 \pm 1) ^\circ\text{C}$, $(100 \pm 1) ^\circ\text{C}$, $(125 \pm 2) ^\circ\text{C}$, $(150 \pm 2) ^\circ\text{C}$, $(175 \pm 2) ^\circ\text{C}$, $(200 \pm 2) ^\circ\text{C}$, $(225 \pm 2) ^\circ\text{C}$, $(250 \pm 2) ^\circ\text{C}$.

Other temperatures, including sub-normal, may also be used.

9 Procedure

9.1 Testing

Bring the test device to the test temperature for an adequate time for all parts to reach thermal equilibrium.

Keep the test piece at the specified test temperature (see Clause 8) for a minimum of 30 min to reach equilibrium (see ISO 23529), then determine the initial cross-sectional area A_0 .

WARNING — Test staff should note that the test temperatures specified present potential burn hazards.

Measure the initial thickness δ_0 of the compression test piece at the selected test temperature with an apparatus meeting the requirements of 4.1 or 4.2

Measure the total sandwich thickness of the shear test piece at the selected test temperature and determine the thickness of rubber by subtracting the thickness of the end plates and central plate.

Mount the test piece in the test device. Take the initial reading of the measuring device, or alternatively set the indicator to zero, depending upon the type of device used.

Apply the force to the test piece such that the full force is reached in not more than 6 s (0,1 min) and without significant overshoot.

For tests in compression and shear, the force shall be chosen such that the initial strain is $(20 \pm 2) \%$.

NOTE 1 A trial run on a separate test piece may be necessary to determine the required force.

NOTE 2 Guidance on the values of forces required for rubbers of differing hardnesses is given in Annex A.

Measure the deformation of the test piece at different times after the application of the full force, this force being held constant throughout the total test time. The height δ_1 in compression or the deformation l_1 in shear shall be measured after $(10 \pm 0,2)$ min and the height δ_2 or deformation l_2 after the times recommended in 9.2.

9.2 Duration of test

It is recommended that the measurements of δ_2 and δ_1 be made on an approximately logarithmic time-scale, for example 100 min, 1 000 min and 10 000 min, or 1 day, 2 days, 4 days, 7 days, ... days.

10 Calculation of results

10.1 Creep increment

10.1.1 In compression

The creep increment in compression $\Delta\varepsilon$ is given by the equation

$$\begin{aligned}\Delta\varepsilon &= \varepsilon_2 - \varepsilon_1 \\ &= \frac{\delta_1 - \delta_2}{\delta_0}\end{aligned}$$

with

$$\begin{aligned}\varepsilon_1 &= \frac{\delta_0 - \delta_1}{\delta_0} \\ \varepsilon_2 &= \frac{\delta_0 - \delta_2}{\delta_0}\end{aligned}$$

where

- ε_1 is the compression strain of the compression test piece 10 min after application of the force;
- ε_2 is the compression strain of the compression test piece after the specified test duration;
- δ_0 is the initial thickness, in millimetres, of the test piece at the test temperature (see Figure 1);
- δ_1 is the thickness, in millimetres, of the compression test piece compressed under constant force 10 min after application of the force;
- δ_2 is the thickness, in millimetres, of the compression test piece after the specified test duration.

10.1.2 In shear

The creep increment in shear $\Delta\gamma$ is given by the equation

$$\begin{aligned}\Delta\gamma &= \gamma_2 - \gamma_1 \\ &= \frac{l_2 - l_1}{\delta_0}\end{aligned}$$

with

$$\gamma_1 = \frac{l_1}{\delta_0}$$

$$\gamma_2 = \frac{l_2}{\delta_0}$$

where

γ_1 is the shear strain of the double-shear test piece 10 min after application of the constant shear force;

γ_2 is the shear strain of the double-shear test piece after the specified test duration;

l_1 is the shear displacement, in millimetres, of the double-shear test piece under constant shear force 10 min after application of the force;

l_2 is the shear displacement, in millimetres, of the double-shear test piece after the specified test duration;

δ_0 has the same meaning as in 10.1.1.

10.2 Creep index

10.2.1 In compression

The creep index in compression $\frac{\Delta\varepsilon}{\varepsilon_1}$ is given by the equation

$$\frac{\Delta\varepsilon}{\varepsilon_1} = \frac{\delta_1 - \delta_2}{\delta_0 - \delta_1}$$

where $\Delta\varepsilon$, ε_1 , δ_0 , δ_1 and δ_2 have the same meanings as in 10.1.1.

10.2.2 In shear

The creep index in shear $\frac{\Delta\gamma}{\gamma_1}$ is given by the equation

$$\frac{\Delta\gamma}{\gamma_1} = \frac{l_2 - l_1}{l_1}$$

where $\Delta\gamma$, γ_1 , l_1 and l_2 have the same meanings as in 10.1.2.