

---

---

**Materials and articles in contact with  
foodstuffs — Cutlery and table  
holloware —**

**Part 5:  
Specification for sharpness and edge  
retention test of cutlery**

*Matériaux et objets en contact avec les denrées alimentaires —  
Coutellerie et orfèvrerie de table —*

*Partie 5: Spécification du tranchant et essai de conservation du  
tranchant*



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 8442-5:2004

© ISO 2004

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 8442-5 was prepared by the European Committee for Standardization (CEN) in collaboration with Technical Committee ISO/TC 186, *Cutlery and table and decorative metal hollow-ware*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Throughout the text of this document, read “...this European Standard...” to mean “...this International Standard...”.

ISO 8442 consists of the following parts, under the general title *Materials and articles in contact with foodstuffs — Cutlery and table holloware*:

- *Part 1: Requirements for cutlery for the preparation of food*
- *Part 2: Requirements for stainless steel and silver-plated cutlery*
- *Part 3: Requirements for silver-plated table and decorative holloware*
- *Part 4: Requirements for gold plated cutlery*
- *Part 5: Specification for sharpness and edge retention test of cutlery*
- *Part 6: Lightly silver-plated table holloware protected by lacquer*
- *Part 7: Requirements for table cutlery made of silver, other precious metals and their alloys*
- *Part 8: Requirements for silver table and decorative holloware*

## Contents

|                                                                 | page |
|-----------------------------------------------------------------|------|
| Foreword.....                                                   | v    |
| 1 Scope .....                                                   | 1    |
| 2 Terms and definitions .....                                   | 1    |
| 3 Testing .....                                                 | 2    |
| 4 Principle.....                                                | 3    |
| 5 Test medium.....                                              | 4    |
| 6 Apparatus .....                                               | 5    |
| 7 Test procedure .....                                          | 7    |
| 8 Expression of results .....                                   | 8    |
| Annex A (normative) Calibration of cutting test apparatus ..... | 10   |

STANDARDSISO.COM : Click to view the full PDF of ISO 8442-5:2004

## Foreword

This document (EN ISO 8442-5:2004) has been prepared by Technical Committee CEN/TC 194, "Utensils in contact with food", the secretariat of which is held by BSI, in collaboration with Technical Committee ISO/TC 186 "Cutlery and table and decorative metal hollow-ware".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2005, and conflicting national standards shall be withdrawn at the latest by June 2005.

Annex A is normative.

EN ISO 8442 consists of the following parts:

- Part 1: *Requirements for cutlery for the preparation of food*
- Part 2: *Requirements for stainless steel and silver-plated cutlery*
- Part 3: *Requirements for silver-plated table and decorative holloware*
- Part 4: *Requirements for gold-plated cutlery*
- Part 5: *Specification for sharpness and edge retention test of cutlery*
- Part 6: *Lightly silver-plated table holloware protected by laquer*
- Part 7: *Requirements for table cutlery made of silver, other precious metals and their alloys*
- Part 8: *Requirements for silver table and decorative holloware*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



## 1 Scope

This European Standard specifies the sharpness and edge retention of knives which are produced for professional and domestic use in the preparation of food of all kinds, specifically those knives intended for hand use.

Powered blade instruments of any kind are excluded.

Generally these types of knives are manufactured with blades of either plain edge design or with edges incorporating particular features to enhance or optimize aspects of cutting ability.

The following two types of knife blade are suitable for the cutting test:

Type A edges: Cutting edges which can be resharpened by the user and edges with a pitch greater than 1 mm;

Type B edges: Cutting edges which are not intended to be resharpened on a steel.

Whilst these knives are predominantly manufactured with blades made from various grades of heat treated steels, the testing of knives of any construction or blade material is not precluded providing that the test criteria are met.

The principle of the testing is to reproduce a cutting action, by forward and reverse strokes, against a pack of synthetic test medium under controlled parameters.

## 2 Terms and definitions

For the purposes of this European Standard, the following terms and definitions apply.

### 2.1

#### **cutlery**

utensils for the preparation and serving of food having a blade with a cutting edge

### 2.2

#### **centre line**

line which generally bisects the cross-section of the blade passing through the cutting edge and the back of the blade (see Figure 1)

EXAMPLE

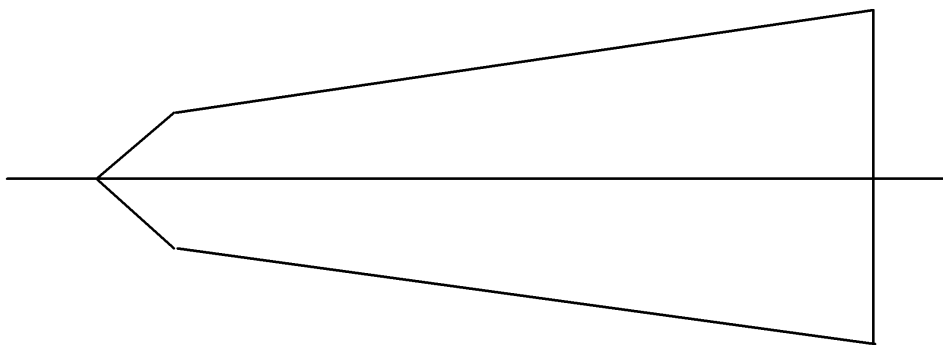


Figure 1 — Centreline

### 2.3

#### **initial cutting performance (ICP)**

cutting ability to be expected by the user from a knife when supplied “as new” from the factory or point of sale

### 2.4

#### **cutting edge retention (CER)**

ability of the knife blade’s edge to resist wear throughout its useful life

### 2.5

#### **total card cut (TCC)**

cumulative amount of card cut (measured in millimetres) by the test knife over the duration of a full test

### 2.6

#### **cutting cycle**

one forward plus one reverse stroke of the designated length of the blade against the medium

## 3 Testing

### 3.1 General


When tested in accordance with the test method of clause 7 each type of knife shall conform to 3.2 to 3.4.

This test shall be carried out before any other physical or mechanical test so that edge performances are assessed in the “as received” condition.

### 3.2 Test length

The portion of the cutting edge of the blade to be tested (see 3.3) shall be straight except for a maximum deviation (positive or negative, not both) of 1 mm.

In the case of type “B” edges the shape of the blade is considered to be the underlying profile on which the detail is superimposed (see Figure 2).

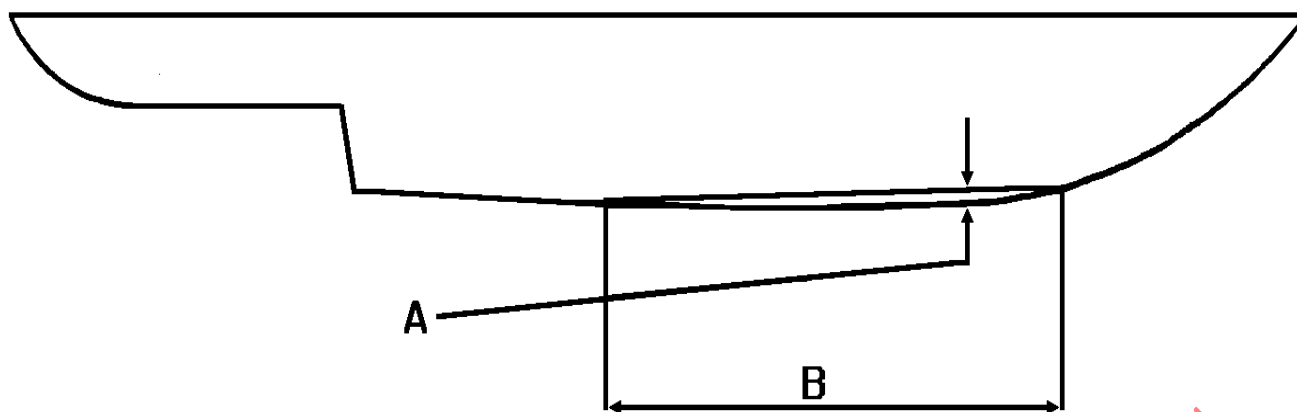

### Key

- A Max. deviation from straight (shown positive)
- B Stroke length

Figure 2 — Blade to be tested

### 3.3 Test conditions

The same test is applied to both types of knives but the duration for the purpose of establishing cutting edge retention is determined by the type of edge. Test parameters are given in Table 1.

Table 1 — Cutting test parameters

| Blade edge Type | Test load N | Stroke Length (mm) | Nominal cutting speed (mm/s) | Total no. Cutting cycles (F) |
|-----------------|-------------|--------------------|------------------------------|------------------------------|
| A               | 50          | 40                 | 50                           | 60                           |
| B               | 50          | 40                 | 50                           | 200                          |

### 3.4 Cutting performance

When tested in accordance with clause 7 the minimum initial cutting performance (ICP) and cutting edge retention (CER) shall conform to the performance levels specified in Table 2.

Table 2 — Performance levels

| Blade edge type | Minimum ICP mm | Minimum CER (TCC) mm |
|-----------------|----------------|----------------------|
| A               | 50             | 150                  |
| B               | 50             | 1 500                |

## 4 Principle

Performance of the blade in terms of distance cut through the medium on each cycle is measured throughout the duration of the test, which is designed to accelerate wear of the knife blade over a short period.

Blades shall cut an adequate amount of medium to complete the test and the two cutting performance indicators ICP and CER are calculated in accordance with clause 8 from the accumulated data.

## 5 Test medium

A specially developed chemical pulp is produced in the form of sheets of card containing a controlled amount of abrasive material i.e. quartz. This card shall be pure chemical soda pulp without any other chemical additive except for the addition of silica in the proportion of  $(5 \pm 0,5)$  % by weight.

The properties of the quartz shall conform to Tables 3 to 5.

The quartz shall have the percentage composition of chemical elements specified in Table 3.

**Table 3 — Composition of silica abrasive**

| Compound                       | Composition<br>% |
|--------------------------------|------------------|
| SiO <sub>2</sub>               | 99               |
| Fe                             | 0,013            |
| Al <sub>2</sub> O <sub>3</sub> | 0,22             |
| MgO                            | Nil              |
| Alkalines                      | Nil              |

The grain size distribution of quartz shall be as specified in Table 4.

**Table 4 — Grain size distribution of silica - C 400**

| Grain size<br>µm | Composition (in weight)<br>% |
|------------------|------------------------------|
| > 50             | 0,2                          |
| > 30             | 4,7                          |
| > 20             | 15                           |
| > 16             | 2                            |
| > 12             | 11                           |
| > 10             | 10                           |
| > 8              | 7                            |
| > 6              | 9                            |
| > 4              | 12                           |
| > 2              | 29                           |

To satisfy the test arrangement the card is cut into 10 mm wide strips (with the fibres of the card grain flowing across the strip) and compiled into a pack maximum 50 mm deep when clamped under pressure  $(130 \pm 2,5)$  N in a holder as shown in Figure 3.

The physical properties of each strip shall be as specified in Table 5.

**Table 5 — Physical properties**

| Thickness<br>mm | Weight<br>g/m <sup>2</sup> | Strip (pack) width<br>mm |
|-----------------|----------------------------|--------------------------|
| 0,31 ± 0,02     | 200 ± 10                   | 10,0 ± 0,1               |

Before use, the test medium shall be conditioned in a controlled atmosphere of  $(55 \pm 5)$  % relative humidity at  $(20 \pm 2)$  °C for a period of 24 h. The card shall be open to this atmosphere and used within 4 h of removal from it.

## 6 Apparatus

NOTE A suitable apparatus for performing the cutting test is shown in Figure 3 and comprises the elements of 6.1 to 6.6.

### 6.1 Card strip holder

A rigid holder with a 10 mm wide aperture to hold the strips of card (max. 50 mm deep). The holder shall provide sideways restraint against the cutting force of the knife and also a support bar above the card, which protrudes, from the holder to provide the reaction against the 50 N test load throughout the test. The card pack shall be clamped by a force of  $(130 \pm 2,5)$  N on the inboard side of the cutting line and any cut card shall be allowed to fall away freely (see also Figure 4).

### 6.2 Counterbalance arrangement

An arrangement of add-on or counterbalance weights, which in conjunction with the card and holder, vertical slide element and all its fittings shall result in a total vertical static load at the interface between card and blade of  $50_0^{+2}$  N (average over the working range) at the start of each new test.

### 6.3 Blade fixture

A fixture, which holds the blade and presents the cutting edge uppermost and provides support against the test load and also a means of easy levelling of the test lengths. The centre line through the section of the blade shall be vertical.

When held in the fixture, the blade edge shall be capable of cutting through the 50 mm of card cleanly without any undue frictional influences excepting that from the blade's sharpened bevel against the face of the uncut card. The blade edge shall be prevented from coming into contact with the metal support bar by means of an independent depth stop.

### 6.4 Transverse blade slide unit


A transverse frictionless slide unit, on which the blade fixture shall be mounted to reduce the influence of friction forces between the blade's sharpened bevel and face of the uncut card. This will allow movement of the blade away from the card holder during the cutting strokes, normal to the direction of the cutting strokes. At the beginning of the first stroke through each 50 mm block of card the point at which the blade starts its cut shall be  $(3 \pm 0,2)$  mm away from the edge of the card holder/clamp. The end of the card pack should be straight and aligned to an approximate angle of  $20^\circ$  to the vertical to allow an approximately equal length of card beyond the cutting point.

### 6.5 Longitudinal blade slide unit

A longitudinal frictionless slide table, which provides the motion to the blade in the direction of the cutting strokes. This shall have a drive system which is capable of producing a nominal 50 mm/s cutting speed, which is achieved by maintaining a more or less constant speed of 50 mm/s over at least 90 % of the specified stroke, with rapid acceleration and deceleration at the ends. This parameter will be verified over several non-cutting cycles and the result shall be  $(45 \pm 0,5)$  mm/s average speed. The stroke shall also be repeatable within  $(45 \pm 0,5)$  mm/s average and verified over several non-cutting cycles of the table.

### 6.6 Card cut amount transducer


A displacement transducer, capable of measuring the depth of cut through the pack of card on each cutting cycle, with a minimum resolution of 0,1 mm (i.e. 1/3 card thickness).

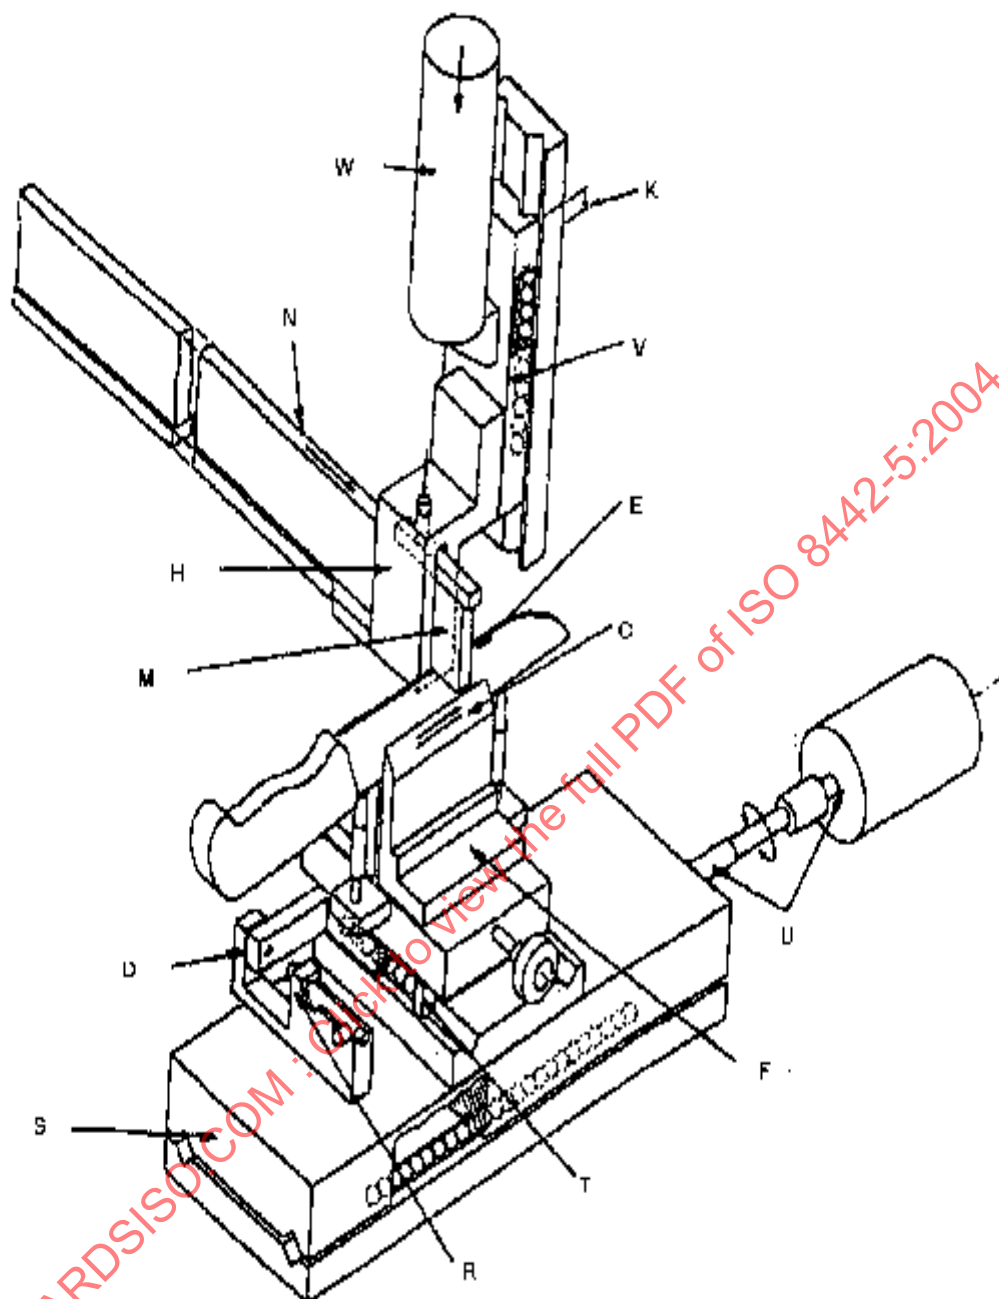

**Key**

|   |                                       |   |                                   |
|---|---------------------------------------|---|-----------------------------------|
| C | Cutting strokes                       | N | Medium feed forwards              |
| D | 1 <sup>st</sup> cut datum             | R | Retaining clamp                   |
| E | Test blade                            | S | Longitudinal slide                |
| F | Component fixture                     | T | Transverse slide                  |
| H | Medium holder                         | U | Motor & ballscrew drive mechanism |
| K | Depth of cut measured by slide travel | V | Vertical slide                    |
| M | Medium                                | W | Additional test weight            |

**Figure 3 — Schematic arrangement of suitable test apparatus**

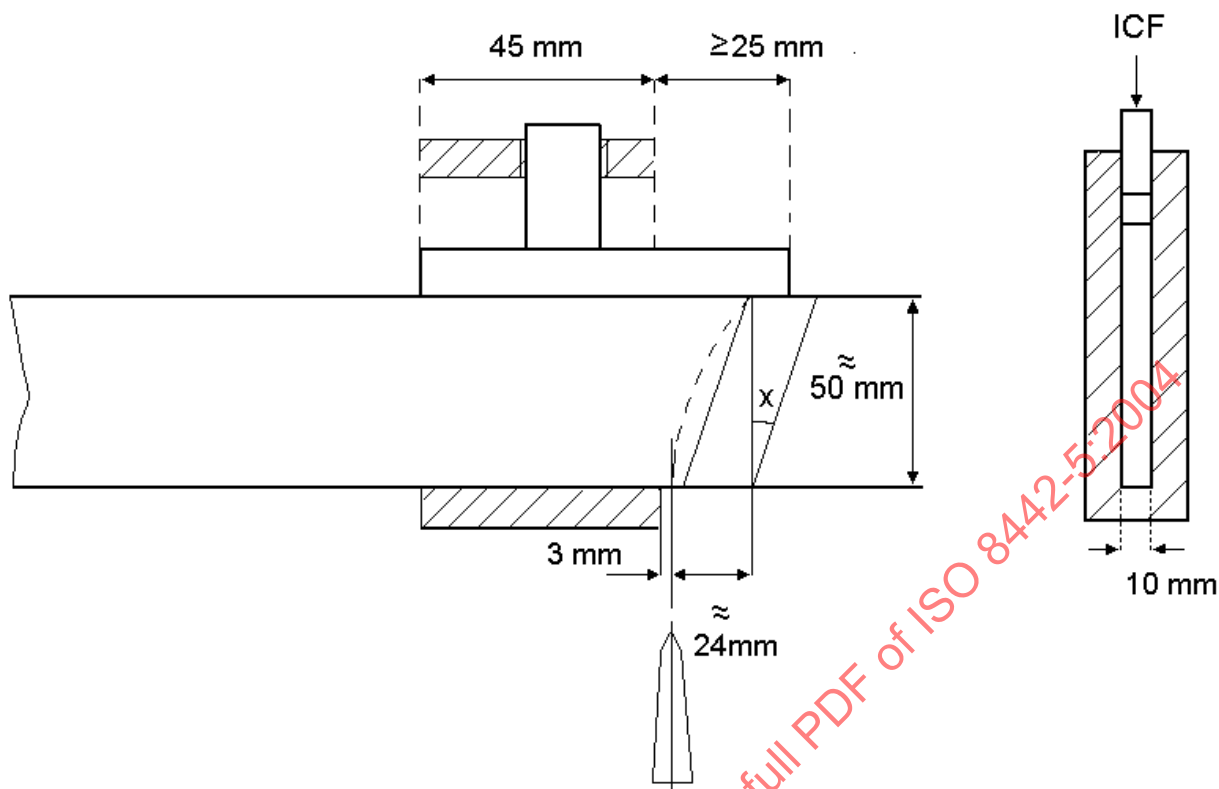

No test shall be performed within 25 mm of the start of the new pack.

#### Key

$x \approx 20^\circ$

ICF Independent clamping force ( $130 \pm 2,5$ ) N

Figure 4 — Arrangement of test medium clamp and blade presentation

## 7 Test procedure

Determine the portion of the blade (50 mm = 40 mm stroke + 10 mm test card width) which meets the straightness criterion ( $\pm 1$  mm deviation over the stroke length of 40 mm) and mark with a suitable marker. Mount the blade (edge uppermost) in the fixture and set the length to be tested level to within 0,5 mm at either end.

Load the apparatus with the test card and weights which combine to give the required 50 N test load (in the static condition) at the start of a new test.

Clamp the card in the holder with approximately 24 mm protruding and lower the assembly until the protruding medium rests on the edge of the blade and the position of contact is 3 mm from the clamped edge.

Release any retaining clamp on the transverse slide and move the blade in forwards and backwards cutting strokes of 40 mm with the test card contacting the cutting edge of the blade throughout the whole cycle. Measure the depth of cut through the card pack at the end of each cutting cycle. Do not allow the blade cutting edge to contact the metal support bar. When more card is required, lift the card pack off the blade and feed forwards the whole pack by approximately 3 mm. Return the transverse slide back to the starting position with respect to the card clamped edge and carry out more cutting strokes.

Record the depth of cut on each cutting cycle, repeating until the predetermined number of cycles is completed for that type of blade. Tabulate the results showing cumulative card cut as per the example in Table 6.

**Table 6 — Method of recording results (example)**

| Cycle no. (x) | Depth of card cut (mm) |                      |
|---------------|------------------------|----------------------|
|               | Per cycle $y_{(x)}$    | Cumulative $z_{(x)}$ |
| 1             | 34,8                   | 34,8                 |
| 2             | 26,5                   | 61,3                 |
| 3             | 23,6                   | 84,9                 |
| 4             | 21,1                   | 106,0                |
| 5             | 18,2                   | 124,2                |
| 6             | 17,7                   | 141,9                |
| 7             | 16,2                   | 158,1                |
| 8             | 14,6                   | 172,7                |
| 9             | 13,9                   | 186,6                |
| 10            | 11,1                   | 197,7                |
|               |                        |                      |
| f             | $y_{(f)}$              | $z_{(f)}$            |

$$z_{(x)} = z_{(x-1)} + y_{(x)}$$

where f Final cycle number

Type A blades: 60 cycles

Type B blades: 200 cycles

$z_{(f)}$  TCC - Total card cut over completed test

## 8 Expression of results

Whilst the plotting of the results graphically is not essential to the calculation of the performance indicators, a typical performance curve would be as shown in Figure 5 with the axes as follows:

X axis: Cutting cycles (up to the limiting number of cycles - 60 type A, 200 type B);


Y axis: Depth of card cut per cycle (mm).

The initial cutting performance ICP is determined by adding together the card cut (in mm) during the initial 3 cycles.

$$ICP = z_{(3)}$$

The cutting edge retention is determined by the total card cut during the complete test.

$$CER = TCC = z_{(f)}$$

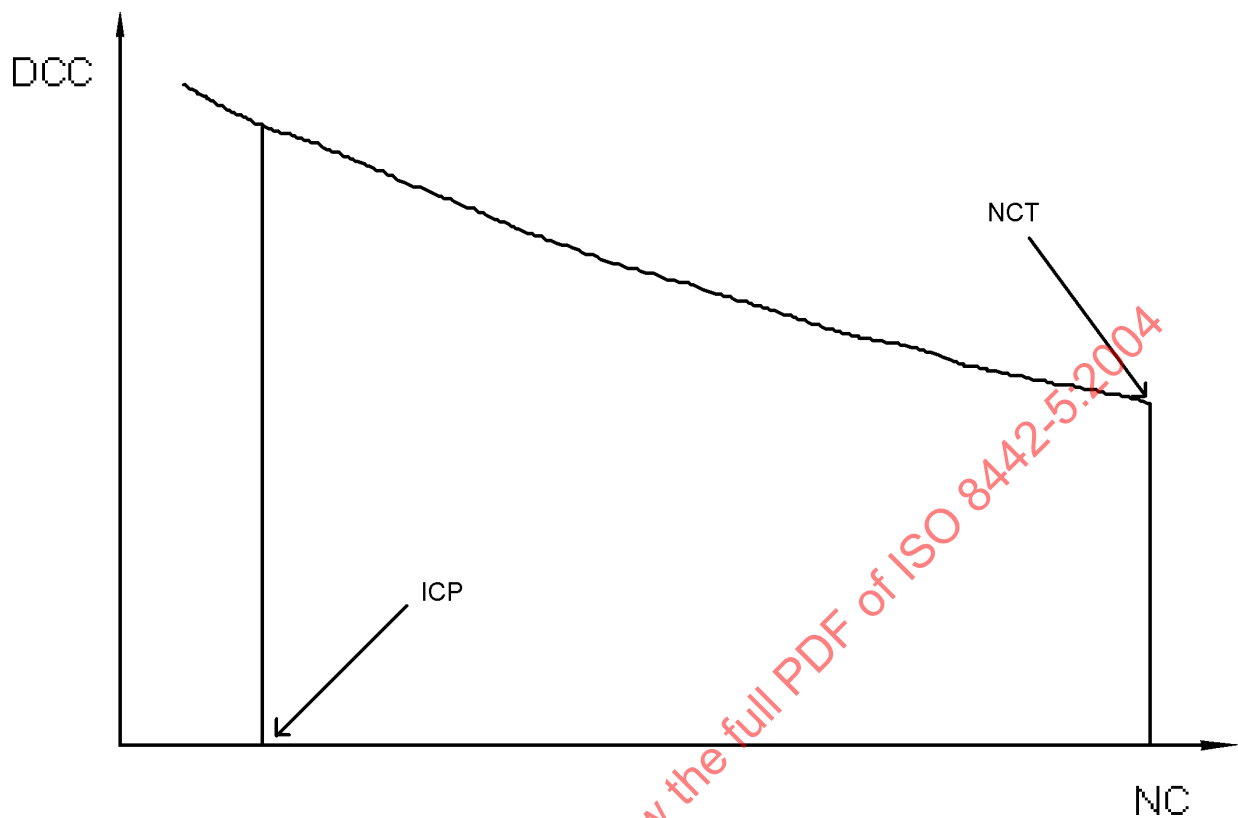**Key**

- DCC Depth of card cut per cycle (mm)  
 ICP Initial cutting performance—Cumulative depth of card cut after 3 cycles  
 NC Number of cycles  
 NCT Limiting number of cycles for test

**Figure 5 — Typical performance of a knife on test**

## **Annex A** (normative)

### **Calibration of cutting test apparatus**

#### **A.1 Principle**

In order to ensure the apparatus performs with accuracy and consistency two forms of calibration are required. Initially the physical parameters of force, distance and speed are calibrated. Once this has been completed the final adjustment of the machine is achieved by carrying out a cutting test with a standard blade. Any discrepancies with the known performance of this blade are then adjusted for.

#### **A.2 Physical calibration**

##### **A.2.1 General data**

The following parameters shall be calibrated to the given values:

a) cutting load (static)  $50^{+2}_0$  N

(the load with which the test card rests on the knife blade);

b) medium clamping force  $(130 \pm 2,5)$  N

(the force with which the card is compressed in its holding device);

c) blade traverse speed

1) nominal 50 mm/s;

2) measured average  $(45 \pm 0,5)$  mm/s over 10 strokes;

d) starting position of test blade in relation to card clamping device  $(3 \pm 0,15)$  mm.

Card cut measurement transducer accuracy  $\pm 0,2$  mm over 50 mm.

These parameters shall be calibrated in accordance with A.2.2 to A.2.7.

##### **A.2.2 Cutting load**

This is calibrated in a static condition at four positions of the vertical slide carrying the test medium. Measurement of the static load shall be carried out by placing a certified load cell in the area of the blade fixture and recording the static readings of the force applied. By the use of spacers it is possible to measure the load at intervals along the slide travel.

##### **A.2.3 Medium clamping force**

By fitting a suitably sized calibrated load cell into the test medium carriage unit the card clamping device shall be adjusted/calibrated to the force specified in A.2.1.