
Plastics — Determination of ignition temperature using a hot-air furnace

*Plastiques — Détermination de la température d'allumage au moyen
d'un four à air chaud*

STANDARDSISO.COM : Click to view the full PDF of ISO 871:2006



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 871:2006

© ISO 2006

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

	Page
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Apparatus	2
6 Location of thermocouples	3
7 Test specimens	3
8 Procedure	5
8.1 Flash-ignition temperature (FIT)	5
8.2 Spontaneous-ignition temperature (SIT)	6
9 Precision	6
10 Test report	6
Annex A (informative) Results obtained by interlaboratory trials	7

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 871 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 4, *Burning behaviour*.

This third edition cancels and replaces the second edition (ISO 871:1996), which has been technically revised.

STANDARDSISO.COM : Click to view the full PDF of ISO 871:2006

Plastics — Determination of ignition temperature using a hot-air furnace

1 Scope

1.1 This International Standard specifies a laboratory method for determining the flash-ignition temperature and spontaneous-ignition temperature of plastics using a hot-air furnace. It is one of a number of methods in use for evaluating the reaction of plastics to the effects of ignition sources.

1.2 This method does not give a direct measure of the combustibility or rate of burning of a material or any definition of the safe upper limit of temperature for the plastics in use, and it should not be used alone to describe or appraise the fire hazard or fire risk of materials, products or assemblies under actual fire conditions. However, results of this test may be used as elements of a fire hazard or fire risk assessment which takes into account all of the factors pertinent to an assessment of the fire hazard of a particular end use.

1.3 Tests made under conditions of this method can be of considerable value in comparing the relative ignition characteristics of different materials. Values obtained represent the lowest ambient air temperature that will cause ignition of the material under the conditions of this test. Test values are expected to rank materials according to ignition susceptibility under actual use conditions.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 13943, *Fire safety — Vocabulary*

IEC 60584-2:1982, *Thermocouples — Part 2: Tolerances*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply in addition to those given in ISO 13943.

3.1

flash-ignition temperature

FIT

minimum temperature at which, under specified test conditions, sufficient flammable gases are emitted to ignite momentarily on application of a pilot flame

3.2

spontaneous-ignition temperature

SIT

minimum temperature at which, under specified test conditions, ignition is obtained by heating in the absence of any additional ignition source

3.3

glowing combustion

combustion of a material in the solid phase without flame but with emission of light from the combustion zone

4 Principle

A specimen of the material is heated in a hot-air ignition furnace using various temperatures within the heated chamber, and the flash-ignition temperature is determined with a small pilot flame directed at the opening in the top of the furnace to ignite evolved gases.

The spontaneous-ignition temperature is determined in the same manner as the flash-ignition temperature, but without the pilot flame.

5 Apparatus

5.1 Hot-air ignition furnace, similar to that shown in Figure 1, consisting primarily of an electrical heating unit and a specimen holder.

5.2 Furnace tube, with an inside diameter of $100 \text{ mm} \pm 5 \text{ mm}$ and a length of $240 \text{ mm} \pm 20 \text{ mm}$, made of a ceramic that will withstand at least 750°C . The tube shall be positioned vertically so that it stands on the furnace floor above a plug for the removal of accumulated residue.

5.3 Inner ceramic tube, capable of withstanding at least 750°C , with an inside diameter of $75 \text{ mm} \pm 2 \text{ mm}$, a length of $240 \text{ mm} \pm 20 \text{ mm}$ and a thickness of approximately 3 mm, placed centrally inside the furnace tube and positioned $20 \text{ mm} \pm 2 \text{ mm}$ above the furnace floor on three small refractory spacer blocks. The top shall be covered by a disc of heat-resistant material with a $25 \text{ mm} \pm 2 \text{ mm}$ diameter opening in the centre which is used for observations and allows the passage of smoke and gases. The pilot flame shall be located immediately above the opening.

5.4 Outside air source, to supply clean air near the top of the annular space between the ceramic tubes through a copper tube at a steady and controllable rate. The air shall be heated and circulated in the space between the two tubes and enter the inner ceramic tube at the bottom. The air flow shall be metered by a rotameter or other suitable device.

5.5 Electrical heating unit, made of 50 turns of $1,3 \text{ mm} \pm 0,1 \text{ mm}$ nichrome wire or equivalent. The wires, contained within a mineral-fibre sleeve, shall be wound around the furnace tube and shall be embedded in heat-resistant cement.

5.6 Insulation, consisting of a layer of mineral-fibre wool approximately 60 mm thick, and covered by a sheet-iron jacket.

5.7 Pilot igniter, consisting of a copper tube of nominal inside diameter 2,0 mm attached to a supply of 94 % minimum purity propane and placed horizontally $5 \text{ mm} \pm 1 \text{ mm}$ above the top surface of the disc cover. The pilot flame shall be adjusted to $20 \text{ mm} \pm 2 \text{ mm}$ in length and centred above the opening in the disc cover.

5.8 Specimen support and holder, consisting of a metal specimen pan made of $0,7 \text{ mm} \pm 0,2 \text{ mm}$ thick stainless steel and measuring $40 \text{ mm} \pm 2 \text{ mm}$ in diameter by $15 \text{ mm} \pm 2 \text{ mm}$ in depth, having a rounded bottom and held in a ring of approximately 2 mm diameter stainless-steel welding rod. The ring shall be welded to a length of the same type of rod extending through the cover of the furnace, as shown in Figure 1. The bottom of the specimen pan shall be located $185 \text{ mm} \pm 2 \text{ mm}$ down from the lower edge of the pilot igniter.

5.9 Thermocouples, 0,5 mm in diameter, chromel-alumel (type K) or iron-constantan (type J), for temperature measurement, connected to a calibrated recording instrument with a tolerance not exceeding $\pm 2^\circ\text{C}$. The thermocouple tolerance shall be in accordance with IEC 60584-2:1982, Table A.1, class 2, or better.

5.10 Heating control, consisting of a suitable variable transformer or an automatic controller connected in series with the heating coils.

5.11 Timing device, having an accuracy of 1 s or better.

6 Location of thermocouples

6.1 Thermocouple TC₁ (see Figure 1) measures the temperature T_1 of the specimen. It is located as close as possible to the centre of the upper surface of the specimen when the specimen is in place within the furnace. The thermocouple wire is attached to the specimen support rod.

6.2 Thermocouple TC₂ gives some indication of the temperature T_2 of the air travelling past the specimen. It is located $10\text{ mm} \pm 2\text{ mm}$ below the centre of the specimen pan. The thermocouple wire is conveniently attached to the specimen support rod.

NOTE Thermocouple TC₂ may also be installed through a hole drilled in the centre of the inspection plug below the specimen pan.

6.3 Thermocouple TC₃ measures the temperature T_3 of the heating coil. It is located adjacent to the furnace heating coil and is used in preference to the inner-tube thermocouples because of its faster response.

7 Test specimens

7.1 Materials supplied in any form, including composites, may be used, but it is essential that the form is fully described in the test report.

NOTE 1 Specimens containing flame retardants and high levels of inorganic fillers may be difficult to evaluate.

NOTE 2 The same material tested in different forms may give different results.

7.2 For materials having a density greater than 100 kg/m^3 , a specimen mass of $3,0\text{ g} \pm 0,2\text{ g}$ shall be used. Materials may be tested in the form of pellets or powder, as normally supplied for moulding. For sheet materials, cut the sheet into squares of maximum size $(20\text{ mm} \pm 2\text{ mm}) \times (20\text{ mm} \pm 2\text{ mm})$ and stack these to a height which gives the required specimen mass. For film materials, roll up a strip $20\text{ mm} \pm 2\text{ mm}$ wide and of length sufficient to give the required specimen mass.

7.3 For cellular materials having a density less than 100 kg/m^3 , remove any outer skin and cut specimens in the form of a block measuring $(20\text{ mm} \pm 2\text{ mm}) \times (20\text{ mm} \pm 2\text{ mm}) \times (50\text{ mm} \pm 5\text{ mm})$.

NOTE If the specimen is bulky and light and easily affected by the air flow in the furnace so that it may fall out of the tray, the specimen may be bound by a thin wire.

7.4 Sufficient material is required for at least two determinations.

7.5 Condition the test specimens at $23\text{ }^\circ\text{C} \pm 2\text{ }^\circ\text{C}$ and $(50 \pm 5)\%$ relative humidity for not less than 40 h prior to test, in accordance with ISO 291.

Dimensions in millimetres

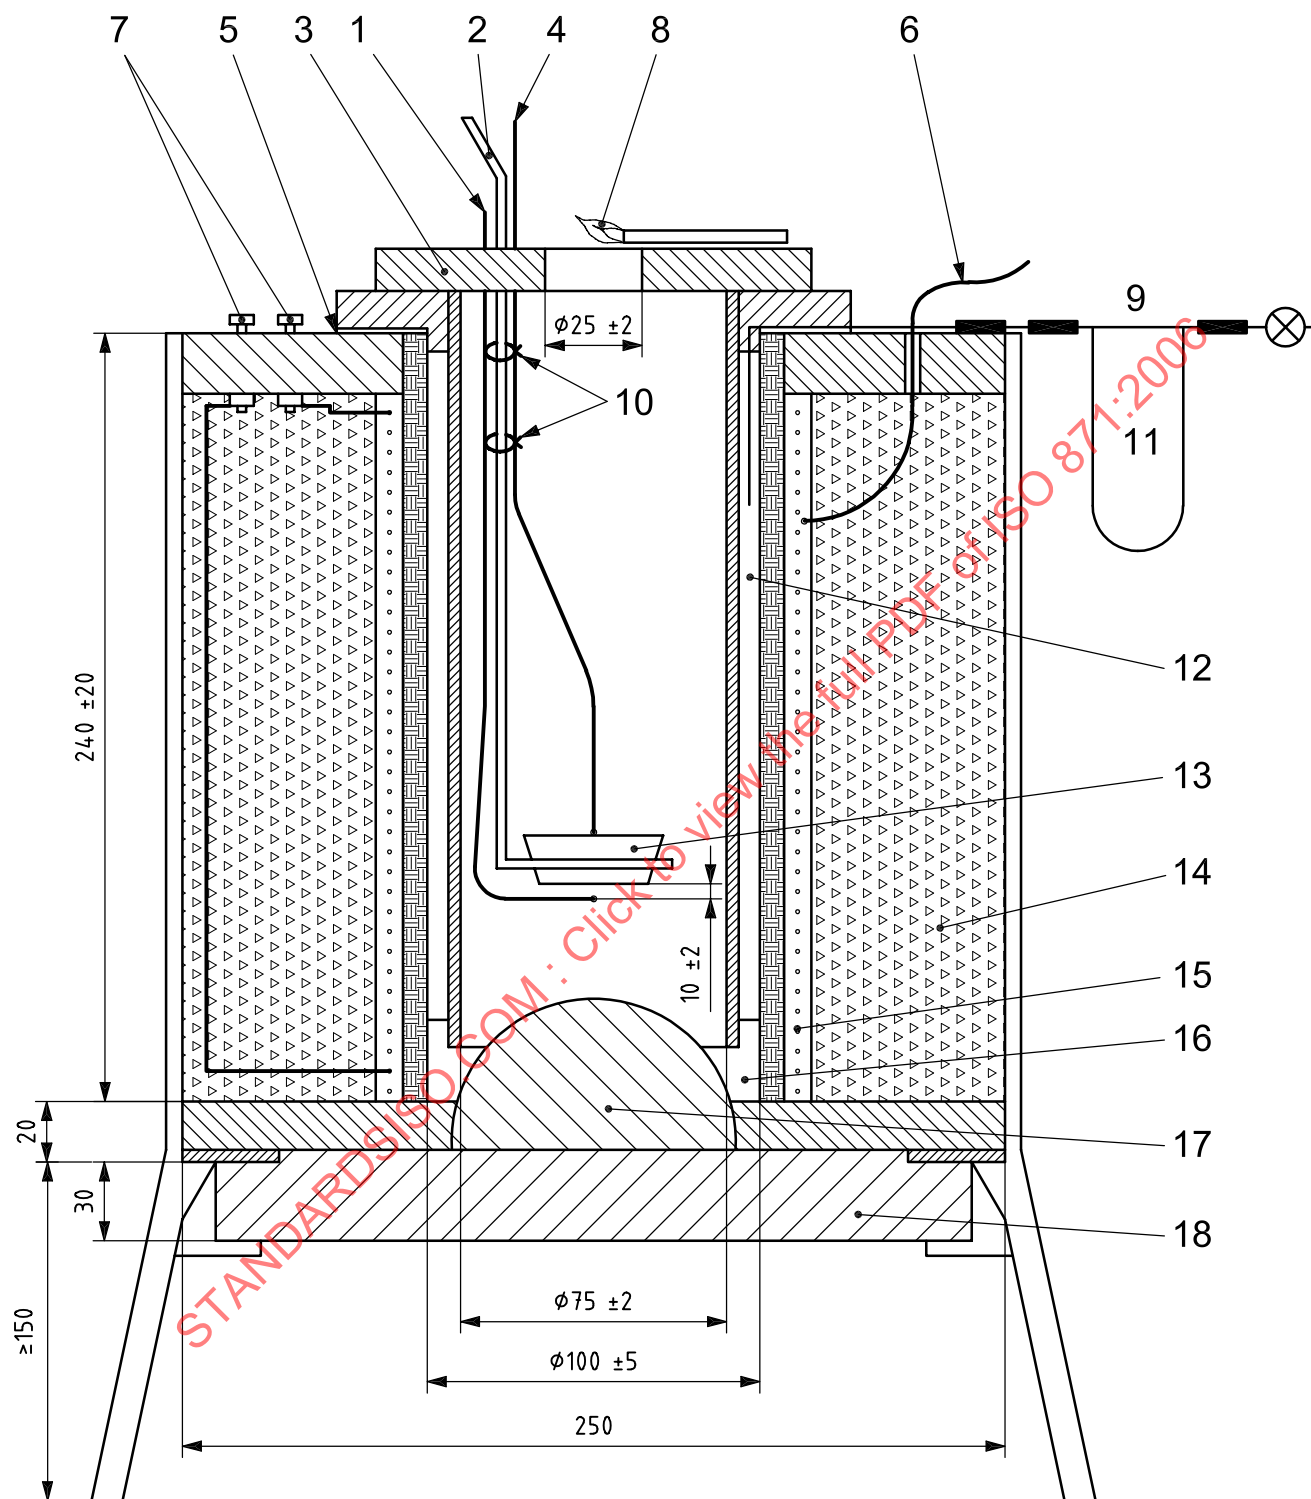


Figure 1 — Cross section of hot-air ignition furnace

Key

- 1 thermocouple TC₂
- 2 support rod
- 3 refractory disc cover
- 4 thermocouple TC₁
- 5 gasket
- 6 thermocouple TC₃
- 7 heater terminals
- 8 pilot flame
- 9 air supply
- 10 metal fasteners
- 11 air-flow meter (not part of furnace)
- 12 air flow tangential to cylinder
- 13 specimen pan
- 14 mineral fibre wool
- 15 50 turns of No. 16 nichrome wire in heat-resistant cement
- 16 three refractory blocks to space inner tube and support it
- 17 inspection plug (removable)
- 18 thermal insulation (removable)

Figure 1 — Cross section of hot-air ignition furnace (*continued*)**8 Procedure****8.1 Flash-ignition temperature (FIT)**

8.1.1 Set the air velocity to 25 mm/s by adjusting the actual air-flow rate q_v through the full section of the inner tube (5.3) at the furnace temperature to a value calculated in litres per minute from the following equation:

$$q_v = 6,62 \times \frac{293}{T}$$

where T is the temperature in K.

Ensure that the air-flow rate is maintained at $\pm 10\%$ of the calculated value.

8.1.2 Adjust the electric current supplied to the heating coil (5.5) by means of the variable transformer or automatic controller (5.10), by reference to temperature T_3 , until the air temperature T_2 remains constant at the desired initial test temperature.

NOTE A temperature of 400 °C is used when no prior knowledge of the probable flash-ignition temperature range is available. Other starting temperatures may be selected if information about the material indicates a better choice.

8.1.3 Raise the specimen holder (see 5.8) to the cover opening and place the pan with the specimen into the ring of the holder. Ensure that thermocouples TC₁ and TC₂ are in their correct position (see 6.1 and 6.2) and lower the pan into the furnace. Start the timer (5.11), ignite the pilot flame and watch for evidence of a flash or mild explosion of combustible gases which may be followed by burning of the specimen.

8.1.4 At the end of 10 min, lower or raise the temperature T_2 by 50 °C, depending on whether ignition has or has not occurred, and repeat the test with a fresh specimen.

8.1.5 When the range within which the flash-ignition temperature lies has been determined, begin tests 10 °C below the highest temperature within this range and continue by dropping the temperature in 10 °C steps until the temperature is reached at which there is no ignition during a 10 min period.