

SAE Executive Standards Committee Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be revised, reaffirmed, stabilized, or cancelled. SAE invites your written comments and suggestions.

REV.
B

AS5928™

FEDERAL SUPPLY CLASS
3110

RATIONALE

AS5928B IS BEING REVIEWED AS A PART OF SAE'S FIVE-YEAR REVIEW POLICY. UPDATED SURFACE FINISH REQUIREMENTS. UPDATED LUBRICATION STATEMENT.

NOTICE

THE COMPLETE REQUIREMENTS FOR PROCURING THE PRODUCT DESCRIBED HEREIN SHALL CONSIST OF THIS DOCUMENT AND THE LATEST ISSUE OF AS39901.


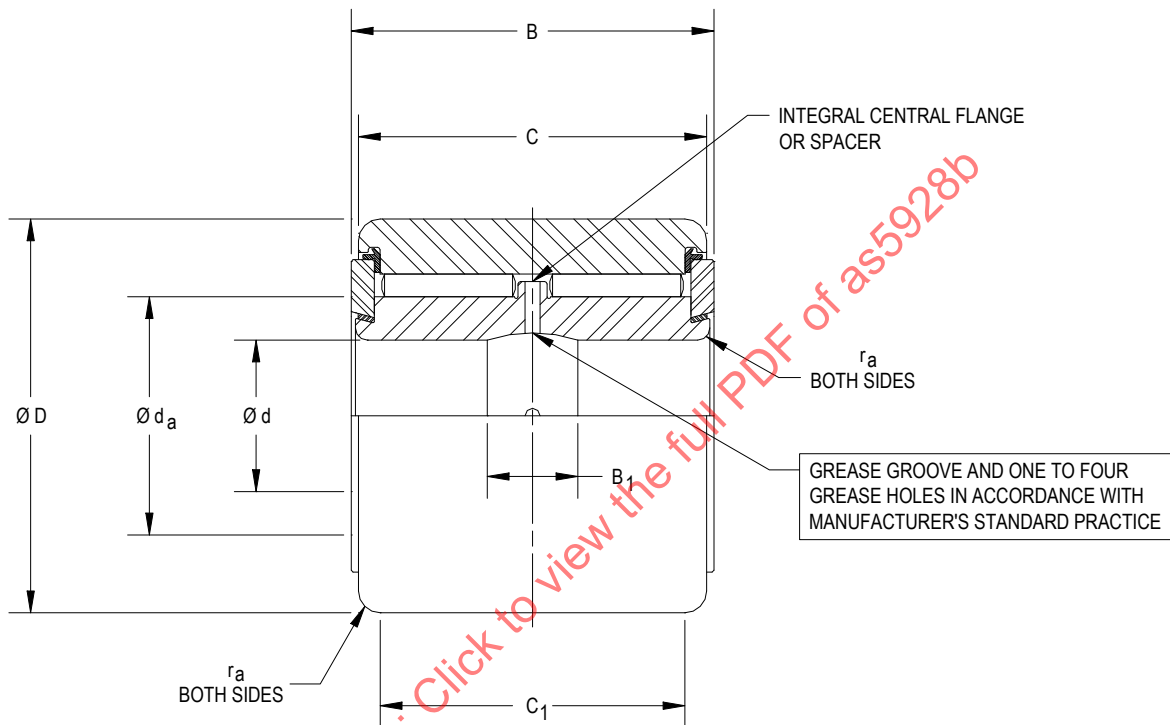


FIGURE 1

For more information on this standard, visit
<https://www.sae.org/standards/content/AS5928B/>

THIRD ANGLE PROJECTION



CUSTODIAN: ACBG

PROCUREMENT SPECIFICATION: AS39901



AEROSPACE STANDARD

BEARING, ROLLER, NEEDLE, DOUBLE ROW, HEAVY DUTY,
TRACK ROLLER, SEALED, TYPE VI, ANTI-FRICTION,
CORROSION RESISTANT NITROGEN (CREN) STEEL, INCH

AS5928™
SHEET 1 OF 3

REV.
B

Copyright 2023 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
Fax: 724-776-0790

Tel: +1 724-776-4970 (outside USA)
Email: CustomerService@sae.org

SAE WEB ADDRESS: <http://www.sae.org>

ISSUED 2005-09 REVISED 2023-11

TABLE 1

DASH NO.	Ød BORE	ØD OUTER RING OD	C OUTER RING WIDTH	B OVERALL WIDTH	Ød _c CLAMPING DIAMETER MINIMUM	R _s RADIUS MINIMUM	B ₁ LUBRICATION GROOVE WIDTH	RADIAL INTERNAL CLEARANCE MAXIMUM	CAPACITY AS A TRACK ROLLER POUNDS	TRACK CAPACITY 40 HRC POUNDS	LIMIT LOAD RATING POUNDS	WEIGHT (APPROX) POUNDS
-104	.2500	.8750	.710	.750	.576	.022	.188	.0018	2310	1480	3100	.12
-106	.3750	1.1250	.940	1.000	.672	.022	.188	.0018	5640	2600	7800	.24
-108	.5000	1.3750	1.190	1.250	.891	.032	.250	.0018	9840	4250	13500	.44
-110	.6250	1.6250	1.440	1.500	1.109	.032	.375	.0018	15750	5650	21500	.73
-112	.7500	1.8750	1.690	1.750	1.281	.032	.375	.0018	22470	7950	30000	1.13
-114	.8750	2.1250	1.940	2.000	1.469	.032	.375	.0018	28900	10650	40000	1.63
-116	1.0000	2.3750	2.190	2.250	1.578	.032	.375	.0018	33600	13200	45000	2.31
-120	1.2500	2.7500	2.440	2.500	1.844	.032	.375	.0018	44700	17300	61000	3.26
-124	1.5000	3.0000	2.690	2.750	1.984	.032	.375	.0018	53600	21200	72000	4.33
-128	1.7500	3.4375	2.940	3.000	2.281	.032	.375	.0018	69000	27000	92000	6.09
-132	2.0000	3.8750	2.940	3.000	2.562	.032	.375	.0018	76600	30400	102000	7.35

TABLE 2

Ød BASIC BORE		ALLOWABLE DEVIATION FROM Ød OF SINGLE MEAN DIAMETER Ø _{dmp}		ALLOWABLE DEVIATION FROM OVERALL WIDTH B		ALLOWABLE DEVIATION FROM LUBRICATION GROOVE WIDTH B ₁		ØD BASIC OUTSIDE DIAMETER		ALLOWABLE DEVIATION FROM ØD OF SINGLE MEAN DIAMETER Ø _{dmp}		ALLOWABLE DEVIATION FROM OUTER RING WIDTH C	
OVER .2500	INCL 2.0000	HIGH 0	LOW -.0007	HIGH 0	LOW -.010	HIGH 0	LOW -.062	HIGH .8750	LOW 3.8750	HIGH +.001	LOW -.001	HIGH 0	LOW -.005

REQUIREMENTS:

1. MATERIAL:

- INNER RING, OUTER RING, AND NEEDLES: CORROSION RESISTANT NITROGEN (CREN) STEEL PER AMS5898, AMS5925, OR 422 STEEL PER AMS5655.
- ENDWASHERS AND SPACER: 420 STEEL PER AMS5506 OR AMS5621, 422 STEEL PER AMS5655, OR CORROSION RESISTANT NITROGEN (CREN) STEEL PER AMS5898 OR AMS5925.
- SEALS: POLYAMIDE (NYLON) PER L-P-410, TYPE 6/6 WEAR RESISTANT GRADE OR ACETAL COPOLYMER WITH LUBRICANT FILLERS PER ASTM D6778.
- RETAINING RINGS (OPTIONAL): BRASS.

2. HEAT TREATMENT:

- INNER AND OUTER RINGS: STEEL PER AMS5898 AND AMS5925 THROUGH HARDEN TO 58 HRC MINIMUM. STEEL PER AMS5655 CASE HARDEN TO 58 HRC MINIMUM AT A CASE DEPTH OF .030.
- NEEDLES: 58 HRC MINIMUM.
- ENDWASHERS AND SPACER: 50-56 HRC.

3. FINISH:

INNER AND OUTER RINGS, NEEDLES, AND ENDWASHERS: PASSIVATE PER AMS2700, METHOD 1, TYPE 2, OR METHOD 2. TEST FOR PASSIVATION PER AMS2700 METHOD 101 OR METHOD 102.

4. SURFACE TEXTURE IN ACCORDANCE WITH ASME B46.1:

- NEEDLE OD – 8 MICROINCHES Ra MAXIMUM
- INNER AND OUTER RACEWAYS – 16 MICROINCHES Ra MAXIMUM
- BORE AND OD – 40 MICROINCHES Ra MAXIMUM
- ENDWASHER FACES – 63 MICROINCHES Ra MAXIMUM



AEROSPACE STANDARD

BEARING, ROLLER, NEEDLE, DOUBLE ROW, HEAVY DUTY,
TRACK ROLLER, SEALED, TYPE VI, ANTI-FRICTION,
CORROSION RESISTANT NITROGEN (CREN) STEEL, INCH

AS5928™
SHEET 2 OF 3

REV.
B