

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be revised, reaffirmed, stabilized, or cancelled. SAE invites your written comments and suggestions.


REV.
A

AS85052/3

FEDERAL SUPPLY CLASS
5340


RATIONALE

AS85052/3A HAS BEEN REAFFIRMED TO COMPLY WITH THE SAE FIVE-YEAR REVIEW POLICY.

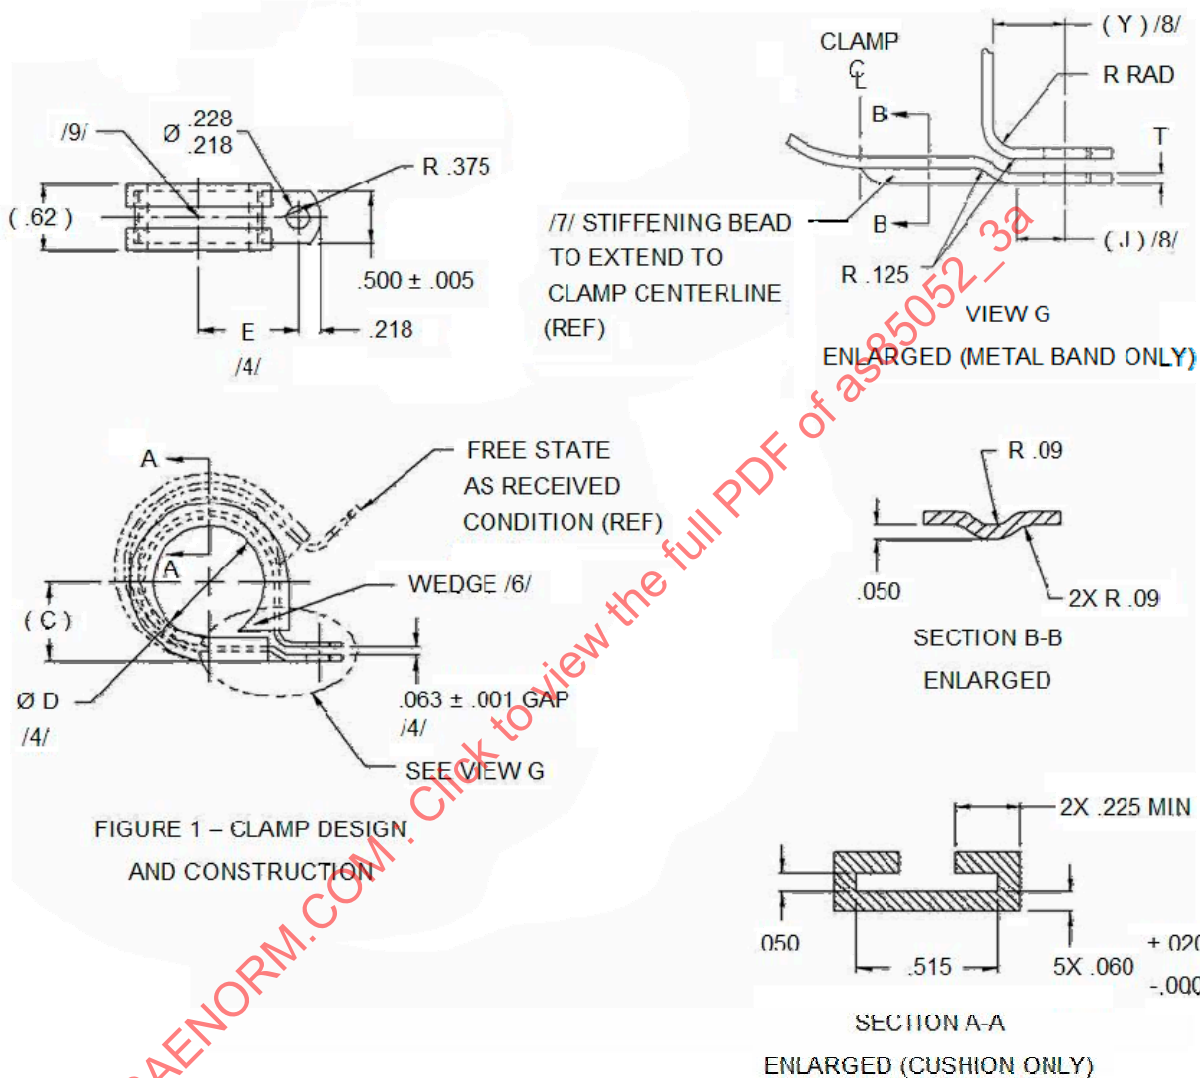

SAE values your input. To provide feedback on this Technical Report, please visit <http://www.sae.org/technical/standards/AS85052/3A>

THIRD ANGLE PROJECTION



CUSTODIAN: G-3/G-3E

PROCUREMENT SPECIFICATION: AS85052 /5/



AEROSPACE STANDARD

(R) CLAMP, LOOP, TUBE 17-7 PH CRES, 500 °F

AS85052/3
SHEET 1 OF 3

REV.
A

TABLE 1 - CLAMP DIMENSIONS

BASIC NO. AS85052/3 SIZE CODE /13/	TUBE SIZE	(C)	ØD	E ±.032	(J)	R RAD ±.010	T TOLERANCE PER AMS2242	(Y)
-02	.125	.192	.125	.468	—	.090	.020	.325
-03	.188	.224	.188	.499	—	.090	.020	.325
-04	.250	.255	.250	.530	.235	.090	.020	.325
-05	.312	.286	.312	.561	.235	.090	.020	.325
-06	.375	.318	.375	.592	.235	.090	.020	.325
-07	.438	.349	.438	.624	.235	.090	.020	.325
-08	.500	.380	.500	.655	.235	.090	.020	.325
-09	.562	.423	.562	.741	.256	.125	.032	.368
-10	.625	.454	.625	.772	.256	.125	.032	.368
-11	.688	.486	.688	.804	.256	.125	.032	.368
-12	.750	.517	.750	.835	.256	.125	.032	.368
-13	.812	.548	.812	.866	.256	.125	.032	.368
-14	.875	.580	.875	.898	.256	.125	.032	.368
-15	.938	.611	.938	.929	.256	.125	.032	.368
-16	1.000	.642	1.000	.960	.256	.125	.032	.368
-17	1.062	.681	1.062	1.001	.262	.125	.040	.370
-18	1.125	.712	1.125	1.032	.262	.125	.040	.370
-19	1.188	.744	1.188	1.064	.262	.125	.040	.370
-20	1.250	.775	1.250	1.095	.262	.125	.040	.370
-21	1.312	.806	1.312	1.126	.262	.125	.040	.370
-22	1.375	.838	1.375	1.158	.262	.125	.040	.370
-23	1.438	.869	1.438	1.189	.262	.125	.040	.370
-24	1.500	.900	1.500	1.220	.262	.125	.040	.370

NOTES:

1. MATERIALS: BAND - 17-7PH, CORROSION RESISTANT STEEL PER AMS5528 OR AMS5529, ANNEALED
- CUSHION - FABRIC REINFORCED SILICONE RUBBER, 65-75 DUROMETER (ON UNREINFORCED MATERIAL), COLOR LIGHT BLUE, PER AMS3316 WITH ADDITIONAL REQUIREMENTS SHOWN ON THIS SPECIFICATION SHEET. THE FABRIC REINFORCING MATERIAL SHALL BE MOLDED INTO THE BAND SIDE OF THE CLAMP CUSHION AT (45°) ANGLE (SEE FIGURE 2)

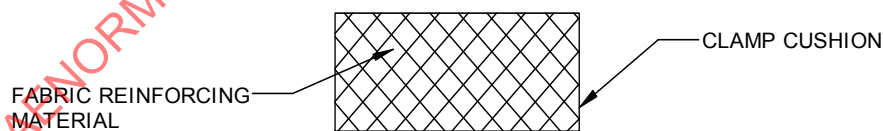


FIGURE 2 - CUSHION REINFORCEMENT

2. HEAT TREATMENT: BAND - STRESS RELIEVE AND HEAT TREAT TO CONDITION TH1100 PER AMS2759/3 AFTER FORMING.
- CUSHION - NONE
3. FINISH: BAND - REMOVE SCALE. PASSIVATE PER AMS2700 TYPE 2 OR 8.
- CUSHION - NONE

	AEROSPACE STANDARD		AS85052/3 SHEET 2 OF 3	REV. A
	(R) CLAMP, LOOP, TUBE 17-7 PH CRES, 500 °F			