

	SURFACE VEHICLE RECOMMENDED PRACTICE	SAE J1325 OCT2011
		Issued 1980-09 Stabilized 2011-10
		Superseding J1325 FEB1994
Test Method for Measuring the Relative Drapeability of Flexible Insulation Materials		

RATIONALE

The technical report covers technology, products, or processes which are mature and not likely to change in the foreseeable future.

STABILIZED NOTICE

This document has been declared "Stabilized" by the SAE Acoustical Materials Committee and will no longer be subjected to periodic reviews for currency. Users are responsible for verifying references and continued suitability of technical requirements. Newer technology may exist.

SAENORM.COM : Click to view the full PDF of J1325 201110

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be revised, reaffirmed, stabilized, or cancelled. SAE invites your written comments and suggestions.

Copyright © 2011 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
 Tel: +1 724-776-4970 (outside USA)
 Fax: 724-776-0790
 Email: CustomerService@sae.org
 SAE WEB ADDRESS: <http://www.sae.org>

**SAE values your input. To provide feedback
 on this Technical Report, please visit
http://www.sae.org/technical/standards/J1325_201110**

Foreword—This Reaffirmed Document has been changed only to reflect the new SAE Technical Standards Board Format.

1. **Scope**—This SAE Recommended Practice describes a method of determining the relative flexibility of padding and/or acoustical composites.
- 1.1 **Purpose**—The purpose of this testing method is to establish a means for measuring the three-dimensional drapeability of flexible insulation materials, such as automotive floor pan insulation composites.
2. **References**—There are no references specified herein.
3. **Apparatus**
 - 3.1 **Cylinder**—Inside diameter 305 mm (12 in), length 305 mm (12 in).
 - 3.2 **Clamps**—Hoffman, screw compressor, open side—maximum opening 19 mm (0.75 in).
 - 3.3 **Scale**—610 mm (24 in) minimum—graduated in millimeters or 0.01 in.
 - 3.4 **Chocks**—Any type capable of preventing the cylinder from rolling.
4. **Test Specimen**—From the material to be tested, cut a 610 mm x 610 mm (24 in x 24 in) specimen.
5. **Conditioning**
 - 5.1 Test for material classification and for arbitration purposes shall be made on material conditioned to a constant weight in a controlled atmosphere of $21\text{ }^{\circ}\text{C} \pm 1\text{ }^{\circ}\text{C}$ ($70\text{ }^{\circ}\text{F} \pm 2\text{ }^{\circ}\text{F}$) and $50\% \pm 5\%$ relative humidity. Quality control tests can be conducted on unconditioned specimens unless otherwise specified by the user.
 - 5.2 Lay the specimen on a flat surface for a minimum of 24 h before conducting the test.
6. **Procedure**
 - 6.1 Lay the cylinder horizontally on top of a table, using the chocks to prevent rolling of the cylinder. See Figure 1.

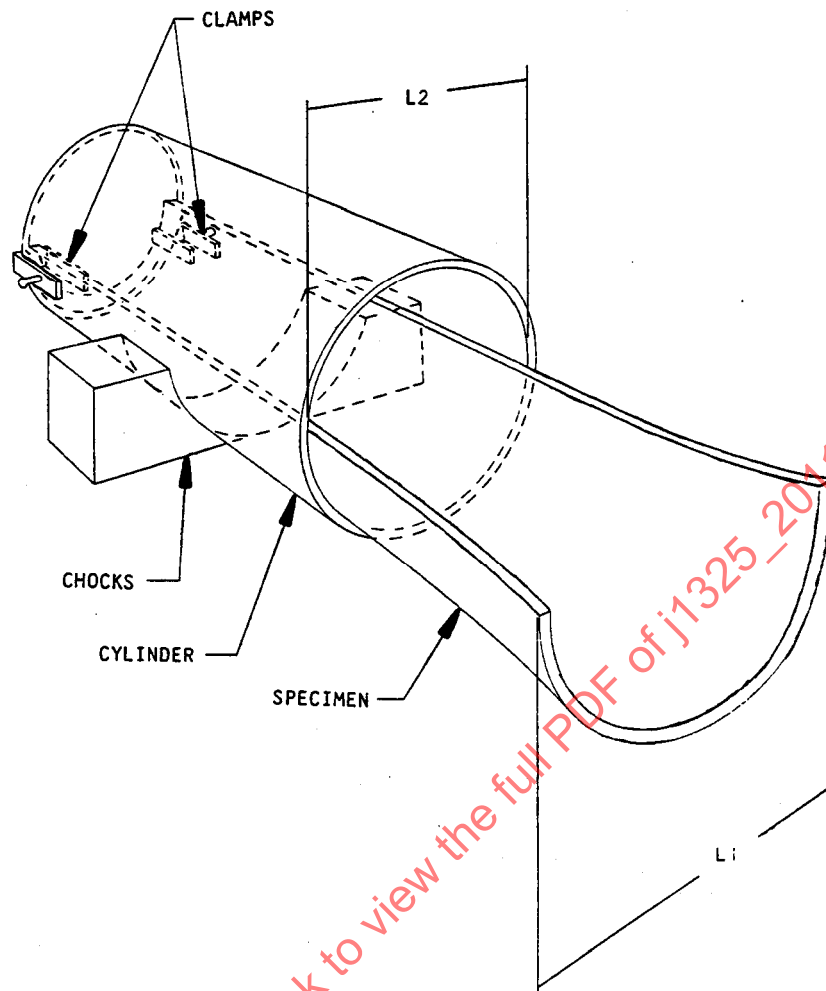


FIGURE 1—DRAPEABILITY APPARATUS

- 6.2 Place the specimen in the interior of the cylinder, matching one end of the specimen with the end of the cylinder.
- 6.3 Orient the specimen so that the surface which would face toward the supporting structure in the proposed application faces downward in the cylinder.
- 6.4 Smooth the specimen against the inner circumference of the cylinder, making sure the sides of the specimen are equidistant from the base of the cylinder.
- 6.5 Securely clamp the corners of the specimen, at the flush end, to the cylinder. See Figure 1.
- 6.6 The specimen should protrude 305 mm (12 in) out of the other end of the cylinder.
- 6.7 Measure the distance (outside dimension) between the corners of the protruding portion of the specimen. Record this distance as L_1 . See Figure 1.
- 6.8 Measure the distance (outside dimension) from edge to edge of the specimen at the end of the cylinder. Record this distance as L_2 . See Figure 1.